

Inverse isotope effects and models for high- T_c superconductivity

David R. Penn

Electron and Optical Physics Division, National Institute of Standards and Technology, Gaithersburg, Maryland 20899

Marvin L. Cohen and Vincent H. Crespi

*Department of Physics, University of California at Berkeley, Berkeley, California 94720
and Materials Sciences Division, Lawrence Berkeley Laboratory, Berkeley, California 94720*

(Received 14 October 1992)

A model for high-temperature superconductivity with a mass-independent electronic mechanism in conjunction with a moderate amount of electron-phonon coupling has previously been shown to be inconsistent with experimental constraints on T_c , the isotope effect exponent, and the electron-phonon coupling. The present work allows for an electronic mechanism with an *inverse* isotope effect. In this case, the model is consistent with the experimental constraints.

A major reason for the proliferation of models involving electronic mechanisms to explain high superconducting transition temperatures is the very small isotope effects observed in the materials with the highest transition temperatures T_c .¹⁻³ It is therefore necessary that models postulating electronic mechanisms explain not only the large values of T_c but also the small isotope effect. At first sight, this seems to be a trivial requirement since for most models, a purely electronic mechanism gives zero isotope effect. However, as stressed in Ref. 4, the isotope shifts are finite albeit small and there are experimental and theoretical estimates that indicate the electron-phonon interaction in these materials is substantial. Thus, any model based on a dominant electronic mechanism for superconductivity must also include the electron-phonon interaction, especially when calculating the isotope shift. The combined electronic and electron-phonon interactions must somehow produce a small isotope effect.

To explore the consequences of this model, the approach taken in Ref. 4 was to solve the Eliashberg equations for combined electronic and phonon-mediated pairing interactions. The electronic mechanism is represented by an attractive interaction at a particular energy, ω_e , with a coupling strength λ_e , while the phonons are represented by an electron-phonon coupling function with a total coupling λ_{ph} . Within the approximation of the McMillan formula for T_c , it was shown that

$$\alpha = \lambda_{ph}/2\lambda, \quad (1)$$

where $\lambda = \lambda_{ph} + \lambda_e$. As expected, α is reduced by the presence of an electronic mechanism.

To determine whether it is possible to produce the observed values of T_c and α for reasonable values of λ_{ph} , we solved the Eliashberg equations for specified T_c and α (taken to be 93 K and 0.02, respectively, for Y-Ba-Cu-O) by choosing an appropriate phonon spectrum consisting of Lorentzian peaks. For a given energy of the electronic mode, ω_e , the strength of this mode relative to that of the phonon modes as well as λ were varied until correct values of T_c and α were obtained. It was found that the λ_{ph} obtained from these calculations increased as ω_e de-

creased. However, even for very small values of ω_e down to 30 meV, the resultant values for λ_{ph} were considerably smaller than theoretical and experimental estimates, which range upwards from $\lambda_{ph} = 0.3$. For still smaller values of ω_e , λ becomes unphysically large; $\lambda \gg 10$. It was concluded that low values of ω_e are necessary for this model because they produce the largest values of λ_{ph} , but that the predicted value of λ_{ph} is still less than half of the smallest estimates of that quantity. Our purpose is to show that an electronic mechanism with an inverse isotope effect is capable of resolving this difficulty. As discussed in Ref. 4, it is possible that the Eliashberg model is not adequate to describe the high- T_c materials because of low-dimensionality effects, a possible non-Fermi-liquid ground state, or a failure to describe the electronic mechanism by the model assumed there. However, it has generally been assumed that many of the central features of superconductivity can be adequately described by the Eliashberg equations and even if this is not the case, it is still instructive to examine the consequences of the conventional theory.

Recently, it has been shown that anharmonic phonons can produce values of T_c and α in agreement with experiment for the high- T_c oxides,⁵ and there has been some experimental evidence for the existence of anharmonic modes. A model with large electron-phonon coupling for the anharmonic modes is capable of explaining the values of $\alpha > \frac{1}{2}$ and the dependence of α on doping in La-Sr-Cu-O.⁵⁻⁷ Anharmonic phonons can also explain site-selective isotope experiments.⁸ Here, we take a different point of view and consider a nonphonon mechanism (e.g., electronic) that couples to the lattice so as to produce a positive isotope shift, (i.e., $\alpha_e < 0$, as opposed to $\alpha_e = 0$ for a purely electronic mechanism or $\alpha_{ph} = 0.5$ for harmonic phonons). This mechanism is modeled as described earlier by an energy ω_e and a coupling strength λ_e relative to the phonon modes which is determined by T_c and α . Unlike previous models, we also assign a positive isotope shift to the mode by considering negative values of α_e . At first sight the model appears to be restricted to the case of a mass-dependent ω_e and mass-independent λ_e . However, for the purposes of calculating α , a mass-dependent

λ_e can be formally incorporated into an effective mass-dependent ω_e which yields the same change in T_c under isotopic shift of just the electronic mode, as will be shown below.

Experimental motivation for consideration of such an inverse isotope effect is provided by site-selective oxygen isotope effect experiments.⁹ A careful choice of exchange conditions allows selective diffusion of plane oxygen sites by exploitation of the different microscopic diffusion rates. An extrapolation of site-selective isotope effect results to perfect site selection implies an *increase* in T_c of 0.32 K for ^{18}O substitution with off-plane oxygen remaining ^{16}O , suggesting the presence of some variety of inverse isotope effect.

To illustrate the changes expected for $\alpha_e \neq 0$, a calculation similar to that which gave Eq. (2) and allowing for a mass-dependent λ_e yields

$$\frac{\lambda_{\text{ph}}}{\lambda} = \frac{\alpha - \alpha_e - \frac{\lambda_M^e}{\lambda}}{\frac{1}{2} - \alpha_e} \quad (2)$$

where α_e measures the isotopic dependence of the electronic mode frequency,

$$\lambda_M^e = -\frac{M}{\lambda_e} \frac{d\lambda_e}{dM}, \quad (3)$$

and $\lambda = \lambda_e + \lambda_{\text{ph}}$. Here we assume harmonic phonons so that $\lambda_M^{\text{ph}} = 0$ and $\alpha_{\text{ph}} = 1/2$. Because $\alpha = 0.02$ is very small, even modest negative values of α_e and λ_M^e can increase $\lambda_{\text{ph}}/\lambda$ substantially, as required to obtain agreement with the estimated values of λ_{ph} . To illustrate this result we consider the case of $\alpha_e < 0$ and $\lambda_e = 0$.

For detailed numerical calculations the phonon spectrum was again modeled by Lorentzian peaks and the Eliashberg equations were solved numerically. The electronic contribution has a strength which depends on its energy ω_e and which is determined by the values $T_c=93$ K and $\alpha = 0.02$, where $\mu^* = 0.12$ is assumed. Results

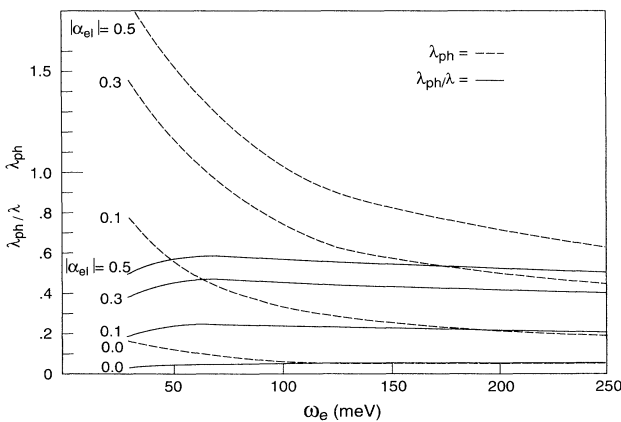


FIG. 1. Values of the electron-phonon coupling strength, λ_{ph} (dashed), and the ratio of the electron-phonon coupling to the total coupling, $\lambda_{\text{ph}}/\lambda$ (solid), vs the energy of the electronic mode for various values of the electronic isotope shift, $|\alpha_e|=0.0, 0.1, 0.3, \text{ and } 0.5$. The curves are determined by the constraints $T_c=93$ K and $\alpha = 0.02$.

of the numerical calculations for $\alpha_e = 0.0, -0.1, -0.3, \text{ and } -0.5$ are shown in Figs. 1 and 2. In all cases, $\lambda_{\text{ph}}/\lambda$ is relatively independent of ω_e as predicted by Eq. (2). Equation (2) is accurate to $\sim 25\%$, even though it was derived for $\mu^* = 0.0$ and $\lambda < 1.5$. The value of λ_{ph} is seen to increase rapidly with increasing $|\alpha_e|$ for a given value of ω_e . The shape of the curves describing λ_{ph} in Fig. 1 are also described well by Eq. (5) since $\lambda_{\text{ph}} \propto \lambda$. The total coupling strength λ must increase with decreasing ω_e as shown in Fig. 2 to maintain a constant T_c ; hence λ_{ph} also increases for decreasing ω_e according to Eq. (5) as shown in Fig. 1. The lower bound on the range of estimates for λ_{ph} in Y-Ba-Cu-O is roughly 0.3. As shown in Fig. 1, the addition of a small negative α_e yields λ_{ph} above this value for a wide range of electronic mode frequencies. A value of $|\alpha_e|$ as small as 0.02 yields $\lambda_{\text{ph}} \sim 0.3$ for an electronic mode at $\omega_e = 30$ meV.

The total coupling strength λ and the gap ratio $2\Delta/kT_c$ increase with decreasing ω_e as shown in Fig. 2, with λ becoming very large for $\omega_e < 30$ meV. The gap ratio is a weakly increasing function of $|\alpha_e|$. Experimental values for the gap ratio up to $2\Delta/kT_c \sim 8$ have been reported and the current calculations yield $2\Delta/kT_c \sim 6$ for $\omega_e \sim 30$ meV. A careful study of Raman phonon frequency shifts at T_c suggests $2\Delta/kT_c \sim 5$,¹⁰ which is consistent with an electronic mode in the frequency range 40–90 meV. These relatively low frequencies are also most conducive to large values of λ_{ph} , suggesting that this frequency range is most plausible for an electronic model of high T_c .

The preceding analysis assumes that $\alpha^2 F(\omega)$ is entirely due to oxygen-atom phonons. A significant portion of the coupling, particularly in the lower frequency range, could arise from nonoxygen vibrations. This situation has been modeled by using the same form for $\alpha^2 F(\omega)$, but assuming the the modes below 26 meV do not shift upon isotopic substitution. Since a portion of λ_{ph} is mass independent, this treatment yields values of λ_{ph} roughly 10% larger than those previously obtained.

The site-selective isotope effect experiments provide an

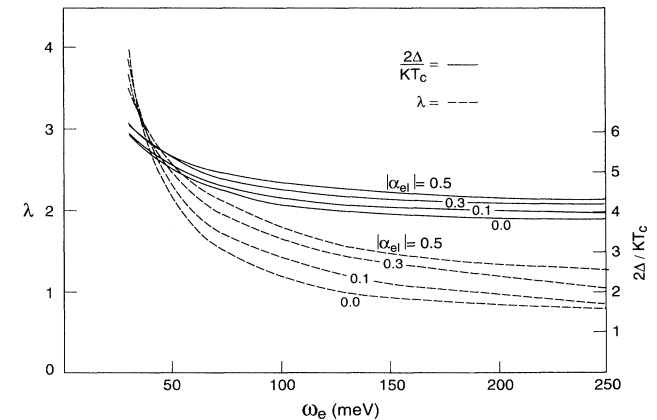


FIG. 2. Values of the total coupling, $\lambda = \lambda_{\text{ph}} + \lambda_e$ (dashed), and $2\Delta/kT_c$ (solid) vs the energy of the electronic mode for various values of the electronic isotope shift, $|\alpha_e|=0.0, 0.1, 0.3, \text{ and } 0.5$. The curves are constrained by the condition $T_c=93$ K and $\alpha = 0.02$.

additional constraint on the model. These measurements are accounted for within the present model by assuming that the mass dependence of the electronic mechanism depends exclusively on the mass of the in-plane oxygen atoms. The site-selective material is modeled by a spectral function in which the electronic contribution is isotopically shifted along with the planar portion of the phonon-mediated contribution. The phonon contribution to $\alpha^2 F(\omega)$ is apportioned between planar oxygen and off-plane oxygen contributions by dividing each of the Lorentzians above 25 meV into two separate peaks, one attributed to planar oxygen phonons and the other off-plane oxygen phonons. The relative strength of these two contributions is varied to obtain agreement with the site-selective isotope effect results. Since the total phonon contribution has not been modified, agreement with the full isotope effect is not affected. For $\alpha_e = -0.3$ or -0.5 , the model is consistent with the site-selective results if $\sim 75\%$ of the oxygen phonon contribution to λ_{ph} arises from planar oxygens. A value of $\alpha_e = -0.1$ implies that $\sim 50\%$ of the oxygen phonon contribution to the electron-phonon coupling arises from in-plane modes. Smaller values of $|\alpha_e|$ require that a larger fraction of the electron-phonon coupling arise from nonplanar phonons.

With a view towards the evaluation of possible physical mechanisms for a negative α_e , we determine the minimal possible values of $|\alpha_e|$ which are consistent with the site-selective isotope effect and the constraint $\lambda_{\text{ph}} > 0.3$. For these calculations μ^* is allowed to vary between 0.1 and 0.2 and the modes in $\alpha^2 F$ below 25 meV are assumed to be nonoxygen. These conditions weaken the experimental constraints on α_e so as to yield a more rigorous lower bound. For electronic mode frequencies below ~ 100 meV, the primary constraint is the site-selective isotope effect, which requires that $|\alpha_e| > 0.05$. Values of $|\alpha_e|$ less than 0.05 imply that less than $\sim 15\%$ of the oxygen contribution to λ_{ph} arises from in-plane modes, a physically implausible situation. (Without the constraint from the site-selective isotope effect, the lower bound on $|\alpha_e|$ for a low-frequency electronic mode is reduced to roughly $|\alpha_e| > 0.02$.) For electronic frequencies above ~ 100 meV, the primary constraint is the requirement that $\lambda_{\text{ph}} > 0.3$. This condition is satisfied for $|\alpha_e| > 0.1$.

It is instructive to examine the way in which our calculations place restrictions on a particular model for an inverse electronic isotope shift. If it is assumed that the shift in T_c is due solely to the fractional change in lattice spacing, $\frac{\delta a}{a}$, under $^{18}\text{O} \rightarrow ^{16}\text{O}$ substitution, then the shift in T_c can be estimated from the pressure dependence of T_c .¹¹ (The variation in T_c with pressure would also involve changes in the phonon spectrum. However, the present model implies that the electronic contribution dominates the superconductivity, suggesting that the increase in T_c under pressure can plausibly be ascribed to changes in an electronic mechanism.) The isotopic shift due to the change in lattice constant can be estimated from the isothermal compressibility and the Gruneisen constants as was done for Ge,¹² and the value $\frac{\delta a}{a} \sim 1 \times 10^{-4}$ at $T = 0$ is obtained. This yields $\alpha_e \sim -0.005$, roughly a factor of 10 smaller than the minimal value required by our calculations. Obviously there are other models possible for an inverse electronic isotope effect which will require a similar analysis. In particular, there may be interesting classes of electronic mechanisms in which $\lambda_M^e \neq 0$.

In summary, we have shown that an electronic mechanism for superconductivity in Y-Ba-Cu-O is consistent with values of $T_c = 93$ K and $\alpha = 0.02$ as well as estimates of λ_{ph} if the electronic mechanism couples to the lattice in such a way as to produce an inverse isotope effect. Electronic models for high-temperature superconductivity should be evaluated in terms of their ability to produce a significant inverse isotope shift.

The authors gratefully acknowledge the contributions of Dr. T. W. Barbee III to computational and scientific aspects of this work. This research was supported by National Science Foundation Grant No. FD91-20269 and by the Director, Office of Energy Research, Office of Basic Energy Sciences, Materials Sciences Division of the U.S. Department of Energy under Contract No. DE-AC03-76SF00098 (M.L.C. and V.H.C.) and under the auspices of the U.S. Department of Energy at the Lawrence Livermore National Laboratory under Contract No. W-7405-ENG-48 (TWB). V.H.C. received partial support from the Department of Defense.

¹L. C. Bourne, A. Zettl, T. W. Barbee III, and M. L. Cohen, Phys. Rev. B **36**, 3990 (1987).

²B. Batlogg, R. J. Cava, A. Jayaraman, R. B. van Dover, G. A. Kourouklis, S. Sunshine, D. W. Murphy, L. W. Rupp, H. S. Chen, A. White, K. T. Short, A. M. Muzsca, and E. A. Rietman, Phys. Rev. Lett. **58**, 2333 (1987).

³L. C. Bourne, M. F. Crommie, A. Zettl, H. zur Loye, S. W. Keller, K. L. Leary, A. M. Stacy, K. J. Chang, M. L. Cohen, and D. E. Morris, Phys. Rev. Lett. **58**, 2337 (1987).

⁴M. L. Cohen, D. R. Penn, and T. W. Barbee III, Solid State Commun. **75**, 971 (1990); T. W. Barbee III, M. L. Cohen, and D. R. Penn, Phys. Rev. B **44**, 4473 (1991).

⁵V. H. Crespi and M. L. Cohen (unpublished).

⁶M. K. Crawford, W. E. Farneth, E. M. McCarron III, R. L.

Harlow, and A. H. Moudden, Science **250**, 1390 (1990).

⁷V. H. Crespi and M. L. Cohen, Phys. Rev. B **44**, 4712 (1991).

⁸V. H. Crespi and M. L. Cohen (unpublished).

⁹J. H. Nickel, D. E. Morris, and J. W. Algers, Phys. Rev. Lett. (to be published).

¹⁰B. Friedl, C. Thomsen, and M. Cardona, Phys. Rev. Lett. **65**, 915 (1990).

¹¹C. W. Chu, P. H. Hor, Y. Y. Xue, G. Lin, R. L. Meng, K. Matsuishi, Z. J. Huang, C. Diaz, and Y. C. Jean, Physica C **185**, 701 (1991).

¹²R. C. Buschert, A. E. Merlini, S. Pace, S. Rodriguez, and M. H. Grimsditch, Phys. Rev. B **38**, 5219 (1988).