

Evaluation of Sustainable High-Volume Fly Ash Concretes

A. Durán-Herrera¹, C. A. Juárez, P. Valdez

Academic Group on Concrete Technology
Facultad de Ingeniería Civil, and
Centro de Innovación, Investigación y Desarrollo en Ingeniería y Tecnología (CIIDIT)
Universidad Autónoma de Nuevo León
San Nicolás de los Garza, N.L, México 66450

D. P. Bentz

National Institute of Standards and Technology
100 Bureau Drive, Stop 8615
Gaithersburg, MD 20899-8615 USA

Abstract

In many countries like México, despite the potential benefits of a superplasticized fly ash (FA) concrete being well disseminated in the technical literature, the potential benefits of these two ingredients and their synergetic effect are not exploited by the concrete industry. This article presents results of an experimental research work oriented to develop practical tools for the regional concrete industry, as well as to illustrate the potential benefits of the synergetic effect of an ASTM C 618 Class F FA produced in the Northeast of México and a polycarboxylate superplasticizer (SP) in the production of conventional concrete. The different concretes considered in this study were produced with water/binder (w/b) ratios between 0.5 and 0.6, mass substitutions of cement by FA between 15 % and 75 %, and a target slump of 20 cm \pm 2 cm. Sustainability is a key issue in this work; in this regard, the approach was to improve the ability of concrete to diminish its ecological impact, and is based on two main aspects: the highest water reduction through the use of an optimum SP dosage that resulted in reductions of 18 %, 15 % and 11 % respectively for the reference mixtures of $w/b=0.5$, $w/b=0.55$, and $w/b=0.6$, which leads to the same reductions of cement; and the use of conventional to high volumes of FA. Key parameters in the fresh and hardened states were characterized to establish tools that can facilitate the use of these concretes in practice. Heat release and heat flow were analyzed through isothermal and semi-adiabatic calorimetry, illustrating that heat release per unit mass of cement is independent of w/b , contrasting with the time of setting results that vary by several hours between the three different w/b ratios. The paper highlights the beneficial effect of the SP in terms of cement reduction and slump retention. Correlations between the FA substitution and slump loss, setting times, compressive strength and static modulus of elasticity (E) were established and they represent very useful potential tools for practical applications of the results. Compressive strength developments up to an age of 56 d are also reported, as well as correlations between the modulus of rupture and compressive strength or splitting tensile strength at an age of 28 d.

Keywords: Fly ash, isothermal calorimetry, modulus of elasticity, modulus of rupture, splitting tensile strength, sustainability.

1. Introduction

Currently, one of the greatest challenges facing the concrete industry is to redirect its products towards the achievement of sustainable development [1]. In this regard, many steps can be improved in the concrete production process, and one of the first steps is to optimize the mixture proportions by the adoption of technological developments that haven't been exploited as they could be in countries with emerging economies such as México. Two technological developments that took place within the last century, and that can improve the ability of the material to maintain ecological processes in the future, are the incorporation of fly ash (FA) into the concrete, and

¹ Corresponding author: alejandro.duranhr@uanl.edu.mx, Tel: (81)83529873/83524969
Fax: (81)83760477

the use of a superplasticizer (SP). There are several publications that explain the technical details for the adoption of these technological developments; however, the process has been slow [2-6].

A significant number of companies from the ready mix concrete industry in México are aware of the benefits of using FA, SP and low water/binder ratios (w/b), but the combination of these three ingredients is rarely found in practice because such concretes are commercialized as special concretes that are not demanded by the potential clients due to their cost. From statistics provided by the National Cement Association of México [7], the production of cement in 2008 was 37.1×10^6 tons and the consumption was 35.1×10^6 tons; the ready mix concrete industry consumed 19 % of this yearly consumption. The other cement consumers were: government (11 %), precast concrete and masonry industry (7 %), formal contractors (15 %) and self construction (48 %). The 81 % integrated by the last four segments represents the potential users for the exploitation of this research.

By itself, the use of FA or SP in conventional concrete improves the behavior of concrete in both its fresh and hardened states, but when they are used together the results in terms of mechanical properties, durability and sustainability can be significantly improved [8-14]. The majority of the referenced works deals with superplasticized FA concrete with w/b ratios below 0.4. Conversely, the w/b for this project was fixed between 0.5 and 0.6, a range that is more familiar for the potential users of the results. This work considered two main aspects of sustainability: the use of a SP to reduce water requirements and consequently reduce the cement content for a target slump of $200 \text{ mm} \pm 20 \text{ mm}$, and the effect of incorporating a wide range of FA substitutions on various fresh and hardened state properties of concrete.

In concrete construction, thermal stresses and strains within the concrete will be highly influenced both by the heat transfer conditions between the curing concrete and its environment and by the concrete mixture proportions; in this scenario, one key concrete material property is the energy generated within the concrete element due to the exothermic cement hydration and pozzolanic reactions [15]. Because the w/b directly controls the volume of water available for hydration and pozzolanic activity per unit volume of binder and also establishes the initial interparticle spacing between binder particles, it can influence semi-adiabatic temperature rise [16].

The results of this project will give valuable information for the practical application of these concretes in a wide range of projects through useful and friendly tools for many concrete construction segments of the national concrete industry in México and elsewhere.

2. Materials and Methods

2.1 Materials

The following materials were used to produce the different concretes considered in the experimental program.

Cement: Blended hydraulic cement (designated as CPC 30R by the Mexican standard NMX-C-414-ONNCCE-2004 [17]) that meets ASTM C 595-08 specification for a Type IP (MS) cement [18]. The physical properties and chemical composition are listed in Table 1. The measured particle size distribution is provided in Figure 1.

Fly Ash (FA): Class F fly ash according to ASTM C 618-08 [18] with an average particle diameter of $80 \mu\text{m}$. The fly ash was obtained from the José Lopez Portillo carboelectric plant located in the state of Coahuila in the Northeast of México, which has a monthly average production of 141,000 metric tons, from which only 4,700 metric tons are currently used. Physical properties and chemical composition are listed in Table 1 and the measured particle size distribution is given in Figure 1. It should be noted that the particle sizes of this particular fly ash may improve particle packing by efficiently filling in the particle sizes between the cement and the fine aggregate.

Fine aggregate: Locally available crushed limestone sand that meets the grading requirements of the ASTM C 33-07 specification [18]. It has a specific gravity of 2.65, a fineness modulus of 3.1, and a water absorption of 1.25 %.

Coarse aggregate: Locally available crushed limestone coarse aggregate with a maximum size of 19 mm that meets the grading requirements of the ASTM C 33-07 # 67 specification [18]. The specific gravity and the water absorption were 2.72 and 0.44 %, respectively. For both aggregates, properties were determined according to standard procedures described in the corresponding ASTM test methods.

Water: Potable water that meets the requirements of ASTM C 1602-06 [18] was used to mix the concrete and cure the specimens. Mixtures were prepared at three different w/b of A) 0.5, B) 0.55, and C) 0.60.

Superplasticizer (SP): A polycarboxylate based high-range water reducer or superplasticizer conforming to ASTM C 494-92 Class A and Class F [18] in aqueous form was used to reduce the paste content and improve workability. The SP has a specific gravity of 1.03 and a total solids content of 22 % by mass.

2.2 Test Methods

For the concrete mixture production, the general procedure described in ASTM C 192-07 was followed [18]. The proportions were optimized by homogeneity and consistency, and were established for the reference mixtures through trial batches for a target slump of $200 \text{ mm} \pm 20 \text{ mm}$. The following steps describe the procedure that was used to establish the proportions for all the mixtures in a single series:

- The optimization of the SP dosage was established through the saturation point criteria using the Marsh cone test [19,20].
- The initial combination of coarse and fine aggregate was established by the combination that gave the minimum voids content or maximum loose unit weight. At the first trial batch, if necessary, the paste content and aggregates combination were modified to obtain an appropriate homogeneity and the target slump. In order to establish the optimized proportions for the reference mixture, SP was added just before the last mixing period.
- Then, the cement was substituted by FA in mass. The mixtures were identified by a three character code in which the first character indicates the series (w/b) and the second and third characters the FA substitution; A0, B0 and C0 were used to identify the reference mixtures in each series. The resulting difference in absolute volume originating from the differences in specific gravity between the cement and the FA was deducted from the fine aggregate to maintain the design yield. Table 2 presents the mixture proportions for the 18 concrete mixtures studied.

The characterization of all the concrete mixtures in the fresh state consisted of the determination of slump (ASTM C 143-08), unit weight (ASTM C 138-08), air content (ASTM C 231-08b, Class B), times of setting (ASTM C 403-08) and slump loss; this last property was monitored through the procedure described in ASTM C 143-08 [18]. The results for these properties are presented in Table 3. The precisions of the various ASTM test methods are as follows: single laboratory standard deviations of 10 mm for slumps of 160 mm and higher, 10.4 kg/m^3 for unit weight, 0.28 % for air content, and 3.5 min and 4.4 min for initial and final setting times, respectively.

Heat of hydration was measured under isothermal conditions (isothermal calorimetry) during the course of 7 d on pre-mixed (as opposed to being mixed in situ in the calorimeter cells) sealed paste samples (cement, FA, water, and SP) with a mass between 4.2 g and 4.6 g [15,16]. For a subset of the eighteen pastes, semi-adiabatic calorimetry was conducted during the course of 2 d, for single specimens with a mass of about 250 g [15,16]. Previous results have indicated a standard deviation of $1.4 \text{ }^\circ\text{C}$ in the maximum specimen temperature achieved during a 3 d test [15].

The characterization of the concrete properties in its hardened state consisted of the determination of the compressive strength (ASTM C 39-05), the chord static modulus of elasticity (ASTM C 469-02), the modulus of rupture using a simple beam with three point loading (ASTM C 78-08) and the splitting tensile strength (ASTM C 496-04) on standard cured specimens [18]. The precisions of these ASTM test methods are as follows: single laboratory (operator) coefficients of variation of 3.2 % for compressive strength, 4.25 % for static modulus of elasticity, 5.7 % for modulus of rupture, and 5 % for splitting tensile strength. Compressive strength results at the ages of (1, 3, 7, 14, 21, 28, and 56) d are presented in Table 4. Table 5 presents the results of modulus of rupture and splitting tensile strength and Table 6 those for static modulus of elasticity. For compressive and splitting tensile strength determinations, standard cylindrical specimens with a diameter of 100 mm were used, while for static modulus of elasticity standard cylindrical specimens with a diameter of 150 mm were used.

3. Results and Discussion

3.1 Concrete fresh state properties

Slump – At the end of each mixing program, the slump was determined for each mixture and the results of these tests are reported in Table 3. From the results, it can be observed that for the three series, the increase in FA substitution generally leads to higher slump values in the range of 10 mm to 40 mm.

Slump loss – Fig. 2 presents the slump loss for concretes of series A; this property was monitored for two hours, and during this period, mixtures A0, A15, and A30 presented a similar average slump loss trend of 80 mm per hour. In the same time period, mixtures A45, A60 and A75 presented a similar average slump loss trend of 43 mm per hour. In concretes of series A, FA substitutions of 45 %, 60 %, and 75 % improved the slump loss by 50 % compared with mixtures A0, A15, and A30. Figs. 3 and 4 illustrate the slump loss of concretes for series B and C. Reference mixtures in both series presented a slump loss of 80 mm per hour, similar to that of the A reference mixture. Concretes with FA in series B presented slump loss rates between 60 mm per hour and 40 mm per hour and in series C between 40 mm per hour and 23 mm per hour. Figs. 2, 3, and 4 also illustrate that as the FA substitution increases, the slump loss decreases.

Setting times – It is well known that FA substitutions may produce retardation in the setting times of concretes; as was expected, the higher retardation times were obtained for the concretes with the higher FA substitutions. For this specific FA, we can observe from Table 3 that the studied concretes presented retardations of the initial setting times of 2:20, 2:05, and 3:30 (h:min) for series A, B, and C respectively, and for final setting times, retardations of 3:17, 4:09, and 6:32 (h:min), for the 75 % substitution of cement by fly ash. Figs. 5 and 6 illustrate respectively the influence of the different FA substitutions on the initial and final setting times; these graphs clearly illustrate that as the w/b and FA substitution increases, the times of setting increases.

Calorimetry - Isothermal calorimetry results are presented in Fig. 7 and illustrate that during the first 24 h, the reference and fly ash pastes hydrate in a similar fashion, indicating that while setting times are delayed, the fly ash is not retarding the hydration of the cement. It is simply that there is less cement to percolate the solid backbone and cause setting when FA is incorporated into the mixture and/or w/b is increased. Bentz et al. have attributed this disparity between calorimetry and setting to fundamental differences between a physical process such as setting and heat release which is purely a quantification of chemical reaction [16].

The heat flow can be further quantified by plotting the cumulative heat release to see how much the fly ash is contributing to the overall reactions; Fig. 8 shows the heat flow development for the three series over the course of the 7 d test on a per gram of cement basis for the three w/b , indicating in each case a small contribution of the pozzolanic reactions, but almost no contribution during the first 24 h (where the curves basically overlap one another). These results illustrate that fly ash additions, through their dilution effect, should significantly reduce the peak temperature achieved in concrete structures. Semi-adiabatic calorimetry executed on a subset of the pastes has verified that this is indeed the case (Fig. 9). For large structures, this reduction in peak temperature should significantly reduce the propensity for early-age cracking due to thermal issues.

3.2 Hardened state properties

Compressive strength development –Table 4 presents the compressive strength development for all the concretes considered in the study; at ages up to 3 d, some values are not included because the concrete was too weak to be tested at those ages. For ages of (1, 3, 7, 14, 21, 28, and 56) d it can be observed from this table that as the FA content increases the compressive strength decreases, and also as a result of the pozzolanic activity of the FA, that as the age increases, the difference between the compressive strength of the concretes with FA and the reference concretes tends to decrease. In practice, usually the compressive strength of the concrete is specified at the age of 28 d. Figs. 10 and 11 are intended to illustrate the wide range of potential compressive strengths for concretes made with this particular cement and FA, with a wide range of substitutions. At an age of 28 d, Fig. 10 illustrates that for concretes with w/b of 0.50, 0.55, and 0.6 and FA substitutions between 0 % and 75 %, strengths between 45.0 MPa and 5.0 MPa can be obtained. In this regard, Fig. 11 illustrates that at an age of 56 d the compressive strengths ranged between 47.0 MPa and 7.0 MPa for the studied concretes.

In Figs. 10 and 11, one can observe that there was a good linear relationship between strength and FA replacement level for these concretes, with correlation coefficients (R^2) of 0.98 in all the cases, and that the slopes of these linear relationships were the same at both ages, being -0.48, -0.42, and -0.37 for series A, B, and C, respectively.

Modulus of Rupture – Table 5 presents the results of modulus of rupture at an age of 28 d, measured on standard cured specimens for series A, B and C; these results were used to establish a linear relationship between modulus of rupture and compressive strength that had a correlation coefficient (R^2) of 0.93, as shown in Fig. 12.

Splitting tensile strength – Table 5 presents the results of splitting tensile strength at an age of 28 d, measured on standard cured specimens for series A, B and C; these results were used to establish a linear relationship between modulus of rupture and splitting tensile strength that had a correlation coefficient (R^2) of 0.96, as shown in Fig. 13.

Modulus of elasticity – Table 6 presents the results of static modulus of elasticity at an age of 28 d, measured on standard cured specimens. For series A, B and C, concretes with an FA substitution of 15 % produced E values between 1 % and 8 % higher than the corresponding reference concretes. With the information contained in this table, a cubic regression of the form $y = ax^3 + bx^2 + cx + d$ was established and appears in Fig. 14. This figure presents two curves that illustrate the relations between the modulus of elasticity and the FA contents in percentage of the total cementitious material for the results obtained by the ASTM procedure, and for the corresponding values obtained with the equation provided by ACI 318-08 [21], section 8.5. For FA substitutions between 15 % and 75 %, E diminished at a rate of 1.0 % and 0.7 %, respectively for the ASTM procedure and the ACI equation. The ACI equation produces conservative estimates compared with the values obtained through the ASTM procedure. For the whole range of FA substitutions, the differences in modulus of elasticity between the two cubic regressions obtained by the two methods were between 5.4 GPa and 8.5 GPa.

In summary, Figs. 10 to 14 represent useful tools for practical applications of these concretes in a wide variety of projects, as well as a useful argument to encourage potential users to improve the sustainability approach of their concrete construction practices.

4. Conclusions

For the studied materials, proportions and based on the aforementioned results and discussion, the following conclusions can be drawn:

1. For these particular cement-FA combinations, the observed correlations represent a practical tool to select initial proportions for target properties including compressive strength, modulus of rupture, splitting tensile strength, and static modulus of elasticity.
2. For the range of FA substitutions studied in this work, the slump was increased by 10 mm to 40 mm.
3. The incorporation of FA, originated an average slump loss reduction of 50 % in comparison to the characteristic slump loss rate obtained for all the reference mixtures.
4. As the w/b and FA substitution increases, the setting times increase. A maximum retardation in final set of 6:32 (h:min) was obtained for w/b of 0.6 and FA substitution of 75 %.
5. Fly ash additions do not retard the hydration reactions of the cement but through dilution do significantly reduce the heat release-peak temperature at early-ages under semi-adiabatic conditions.
6. FA substitutions of 15 % increased the modulus of elasticity by up to 8 % in comparison with the reference concrete.
7. For the range of FA substitutions studied in this work, the ACI equation to calculate the modulus of elasticity produces conservative estimates when compared with the values obtained through the ASTM procedure. Depending on the FA substitution, the difference between the average values obtained by the ASTM procedure and the ACI equation ranged from 5.4 GPa to 8.5 GPa.

Acknowledgements

The authors would like to acknowledge the partial funding from the Program to support Scientific and Technological Research at the Universidad Autónoma de Nuevo León (PAICYT-UANL-2007, CA1482-07). Special appreciation is extended to the Undergraduate students of the Facultad de Ingeniería Civil of UANL who participated in concrete production and specimens testing, and to the companies that provided the materials used in

this work: to Cementos Moctezuma S.A. de C.V., for providing the cement, to BASF Mexicana S.A. de C.V. for providing the superplasticizer, to the Federal Commission of Electricity of México (CFE) for providing the fly ash and to Industrializadora de Caliza, S.A. de C.V. for providing the aggregates.

References

1. Mehta PK. Global concrete industry sustainability. *Concr Inter* 2009; 31:45-8.
2. Malhotra VM, Mehta PK. High performance, high-volume fly ash concrete. ISBN0-9731507-2-6, 2nd ed. Ottawa, Canada: Supplementary Cementing Materials for Sustainable Development Inc.; 2005.
3. Spiratos N, Page M, Mailvaganam N P, Malhotra V M, Jolicoeur C. Superplasticizers for concrete. ISBN 0-9731507-1-8, Ottawa, Canada: Supplementary Cementing Materials for Sustainable Development Inc.; 2003.
4. Rixom R, Mailvaganam N. Chemical admixtures for concrete. ISBN: 0203017242, London: E. & F. N. Spon; 1999.
5. Ramachandran VS (editor) Concrete admixtures handbook. ISBN: 1591240387, Park Ridge, NJ: Noyes Publications; 1995.
6. Wesche K (editor) Fly ash in concrete. ISBN: 0419157905, New York: Van Nostrand Reinhold; 1991.
7. Web address of the National Cement Association of México; <http://www.canacem.org.mx/canacem.htm>
8. Sisomphon K, Franke L. Carbonation rates of concretes containing high volume of pozzolanic materials. *Cem Concr Res* 2007;37:1647–53.
9. Felekoglu B. Utilization of Turkish fly ashes in cost effective HVFA concrete production. *Fuel* 2006;85:1944–49.
10. McCarthy MJ, Dhir RK. Development of high volume fly ash cements for use in concrete construction. *Fuel* 2005; 84:1423–32.
11. Bouzoubaa N, Zhang MH, Malhotra VM. Mechanical properties and durability of concrete made with high-volume fly ash blended cements using a coarse fly ash. *Cem Concr Res* 2001;31:1393–1402.
12. Malhotra VM, Zhang MH, Read PH, Ryell J. Long-term mechanical properties and durability characteristics of high-strength/high-performance concrete incorporating supplementary cementing materials under outdoor exposure conditions. *ACI Mater J* 2000;97:518-25.
13. Poon CS, Lam L, Wong YL. A study on high strength concrete prepared with large volumes of low calcium fly ash. *Cem Concr Res* 2000;30:447-55.
14. Khayat KH, Manai K, Trudel A. In situ mechanical properties of wall elements cast using self-consolidating concrete. *ACI Mater J* 1997;94:491-500.
15. Bentz DP, Sant G, Weiss WJ. Early-age properties of cement-based materials: I. Influence of cement fineness. *ASCE J Mater Civ Eng* 2008;20:502-8.
16. Bentz DP, Peltz MA, Winpiger J. Early-age properties of cement-based materials: II. Influence of water-to-cement ratio. *ASCE J Mater Civ Eng* 2009;21:512-7.
17. Mexican Cement Standard NMX-C-414-ONNCCE-2004. “Building industry – Hydraulic cement – Specifications and testing methods”, ONNCCE, S.C., México, D.F; 2004.
18. ASTM International. Annual book of ASTM standards. West Conshohocken, PA: ASTM International; 2009.
19. Jayasree C, Gettu R. Experimental study of the flow behavior of superplasticized cement paste. *Materials and Structures* 2008; 41:1581–93.
20. Roussel N, Le Roy R. The Marsh cone: A test or a rheological apparatus? *Cem Concr Res* 2005;35:823–30.
21. ACI 318-08. Building code requirements for structural concrete and commentary. Farmington Hills, MI: American Concrete Institute; 2008.

Table 1: Physical properties and chemical analysis of cement and FA.

| Physical Properties | | | Cement | FA |
|--|------|--|--------------|--------------|
| Fineness – passing 45 μm , % | | | 97.2 | not measured |
| Blaine, m^2/kg | | | 482 | not measured |
| Specific gravity | | | 3.13 | 2.38 |
| Compressive strength of 50-mm cubes, MPa (Psi) | | | | |
| | 3 d | | 20.5 (2 973) | 21.6 (3 132) |
| | 7 d | | 24.1 (3 495) | 23.7 (3 437) |
| | 28 d | | 35.6 (5 162) | 30.5 (4 423) |
| Chemical Composition, % by mass | | | | |
| SiO ₂ | | | 19.6 | 62.3 |
| Al ₂ O ₃ | | | 4.5 | 22.0 |
| Fe ₂ O ₃ | | | 4.0 | 6.0 |
| CaO | | | 58.8 | 3.4 |
| MgO | | | 1.6 | 1.0 |
| SO ₃ | | | 3.0 | 0.2 |
| Na ₂ O | | | 0.4 | 0.8 |
| K ₂ O | | | 1.4 | 1.6 |
| Loss of ignition | | | 6.4 | 1.6 |

FA = Fly ash

Table 2. Mixture proportions for series A, B and C.

| Series | FA, (%) | W/(C+FA) (w/b) | Water, (kg/m ³) | Cement, (kg/m ³) | FA, (kg/m ³) | SSD Aggregates, (kg/m ³) | | SP* (L/m ³) |
|--------|---------|----------------|-----------------------------|------------------------------|--------------------------|--------------------------------------|------|-------------------------|
| | | | | | | Coarse | Fine | |
| A | 0 | 0.50 | 211 | 425 | ---- | 734 | 990 | 2.2 |
| | 15 | | | 361 | 64 | 728 | 972 | |
| | 30 | | | 298 | 128 | 741 | 963 | |
| | 45 | | | 234 | 191 | 752 | 934 | |
| | 60 | | | 170 | 255 | 743 | 923 | |
| | 75 | | | 106 | 319 | 735 | 914 | |
| B | 0 | 0.55 | 222 | 405 | ---- | 774 | 959 | 1.3 |
| | 15 | | | 344 | 61 | 772 | 941 | |
| | 30 | | | 284 | 122 | 771 | 940 | |
| | 45 | | | 223 | 182 | 770 | 904 | |
| | 60 | | | 162 | 243 | 767 | 884 | |
| | 75 | | | 101 | 304 | 770 | 904 | |
| C | 0 | 0.60 | 222 | 370 | ---- | 785 | 973 | 0.6 |
| | 15 | | | 315 | 56 | 785 | 928 | |
| | 30 | | | 259 | 111 | 787 | 921 | |
| | 45 | | | 204 | 167 | 793 | 917 | |
| | 60 | | | 148 | 222 | 785 | 883 | |
| | 75 | | | 93 | 278 | 794 | 886 | |

FA = Fly ash, C = Cement, SSD = Saturated surface dry

* Superplasticizer

Table 3. Fresh concrete properties for series A, B, and C.

| Series | FA (%) | Unit Weight (kg/m ³) | Slump (mm) | Air (%) | Setting Times (h:min) | |
|--------|--------|----------------------------------|------------|---------|-----------------------|-------|
| | | | | | Initial | Final |
| A | 0 | 2350 | 220 | 2.5 | 4:45 | 6:13 |
| | 15 | 2333 | 250 | 1.6 | 4:53 | 6:24 |
| | 30 | 2332 | 250 | 1.9 | 5:02 | 7:08 |
| | 45 | 2308 | 260 | 2.0 | 5:35 | 7:41 |
| | 60 | 2296 | 250 | 2.3 | 6:30 | 8:25 |
| | 75 | 2257 | 230 | 3.2 | 7:05 | 9:30 |
| B | 0 | 2353 | 220 | 1.7 | 5:10 | 6:18 |
| | 15 | 2320 | 230 | 1.8 | 5:15 | 6:35 |
| | 30 | 2314 | 235 | 1.9 | 5:30 | 7:15 |
| | 45 | 2296 | 245 | 2.0 | 6:00 | 7:50 |
| | 60 | 2271 | 225 | 2.2 | 6:50 | 9:40 |
| | 75 | 2260 | 255 | 1.9 | 8:10 | 10:27 |
| C | 0 | 2344 | 210 | 2.0 | 5:15 | 6:23 |
| | 15 | 2331 | 235 | 2.0 | 5:25 | 7:00 |
| | 30 | 2316 | 240 | 1.8 | 6:02 | 8:00 |
| | 45 | 2305 | 245 | 1.5 | 6:30 | 8:55 |
| | 60 | 2292 | 245 | 2.0 | 8:25 | 11:32 |
| | 75 | 2288 | 250 | 1.5 | 8:45 | 12:55 |

FA = Fly Ash

Table 4. Compressive strength development on concrete specimens cured under standard conditions for series A, B, and C.

| Series | FA (%) | Compressive strength (MPa) | | | | | | |
|--------|--------|----------------------------|------|------|------|------|------|------|
| | | Age (d) | | | | | | |
| | | 1 | 3 | 7 | 14 | 21 | 28 | 56 |
| A | 0 | 15.0 | 26.9 | 35.1 | 38.8 | 41.4 | 43.5 | 44.9 |
| | 15 | 15.6 | 24.8 | 27.6 | 29.3 | 30.5 | 36.8 | 40.1 |
| | 30 | 11.7 | 21.2 | 24.1 | 26.2 | 30.0 | 32.5 | 35.5 |
| | 45 | 6.4 | 14.0 | 18.6 | 19.2 | 23.7 | 23.8 | 26.8 |
| | 60 | 4.4 | 7.2 | 10.1 | 11.9 | 13.8 | 16.8 | 17.2 |
| | 75 | 1.1 | 3.2 | 4.1 | 5.4 | 6.4 | 7.0 | 9.9 |
| B | 0 | 19.4 | 26.8 | 30.4 | 30.9 | 33.7 | 37.0 | 38.4 |
| | 15 | 12.5 | 24.3 | 27.9 | 29.8 | 30.2 | 32.4 | 35.7 |
| | 30 | 10.6 | 18.7 | 20.7 | 22.8 | 24.0 | 25.4 | 27.0 |
| | 45 | 5.7 | 11.4 | 12.9 | 18.0 | 19.0 | 19.6 | 21.5 |
| | 60 | 3.8 | 5.9 | 7.8 | 9.5 | 11.6 | 13.1 | 14.0 |
| | 75 | -- | 2.6 | 3.4 | 4.3 | 5.5 | 6.0 | 7.9 |
| C | 0 | 16.1 | 22.5 | 26.3 | 31.9 | 29.0 | 32.1 | 34.5 |
| | 15 | 8.8 | 17.4 | 19.8 | 24.9 | 26.9 | 27.5 | 29.3 |
| | 30 | 7.5 | 11.6 | 16.7 | 18.5 | 20.1 | 21.3 | 24.5 |
| | 45 | 3.1 | 6.9 | 9.1 | 10.7 | 12.1 | 13.4 | 16.6 |
| | 60 | -- | 4.6 | 6.7 | 7.9 | 9.4 | 9.8 | 12.6 |
| | 75 | -- | -- | 2.6 | 3.8 | 4.2 | 5.0 | 6.7 |

FA= Fly Ash

Table 5. Modulus of rupture and splitting tensile strength on specimens cured for 28 d under standard conditions for series A and B.

| Series | FA (%) | MR (MPa) | STS (MPa) |
|--------|--------|----------|-----------|
| A | 0 | 4.9 | 4.4 |
| | 15 | 4.6 | 3.9 |
| | 30 | 4.4 | 3.7 |
| | 45 | 3.7 | 2.8 |
| | 60 | 2.8 | 2.1 |
| | 75 | 2.2 | 1.2 |
| B | 0 | 4.6 | 3.6 |
| | 15 | 4.3 | 3.5 |
| | 30 | 3.6 | 3.2 |
| | 45 | 2.8 | 2.4 |
| | 60 | 2.4 | 1.3 |
| | 75 | 1.1 | 0.6 |
| C | 0 | 3.7 | 2.8 |
| | 15 | 3.2 | 2.6 |
| | 30 | 3.0 | 2.5 |
| | 45 | 2.8 | 2.0 |
| | 60 | 2.1 | 1.4 |
| | 75 | 1.0 | 0.8 |

FA = Fly ash

MR = Modulus of rupture

STS = Splitting tensile strength

Table 6. Static Modulus of Elasticity determined on specimens cured for 28 d under standard conditions for series A, B, and C.

| Static Modulus of Elasticity (GPa) | | | |
|------------------------------------|--------|------|------|
| FA (%) | Series | | |
| | A | B | C |
| 0 | 35.4 | 30.2 | 29.3 |
| 15 | 37.1 | 32.7 | 29.7 |
| 30 | 31.5 | 28.2 | 27.0 |
| 45 | 28.0 | 23.3 | 24.9 |
| 60 | 24.3 | 20.6 | 16.2 |
| 75 | 15.7 | 11.8 | 10.6 |

FA = Fly Ash

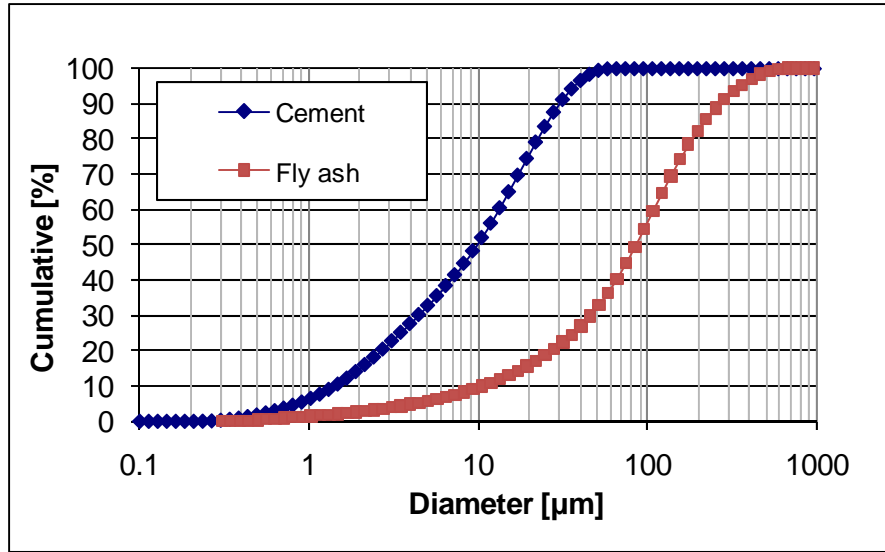


Fig. 1 Measured particle size distributions for the cement and fly ash employed in the current study.

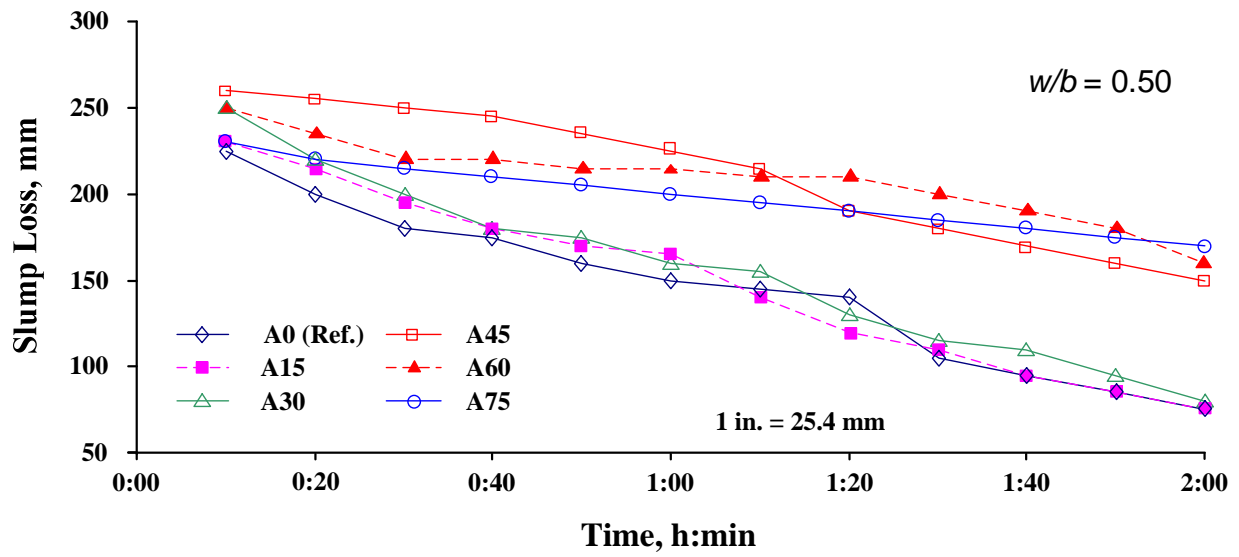


Fig. 2 Slump loss of series A concretes.

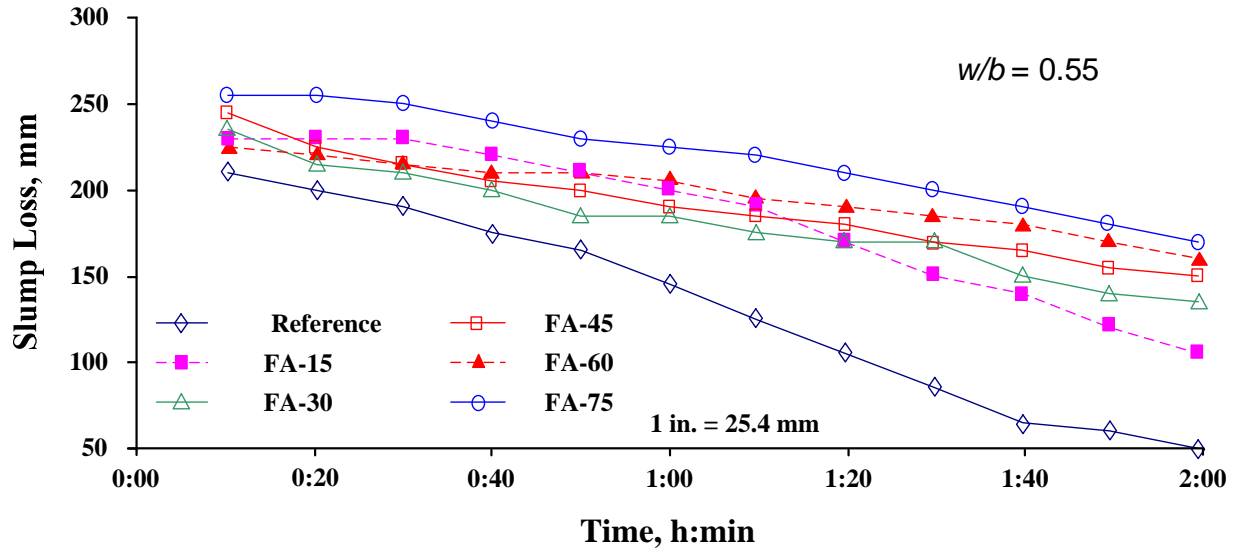


Fig. 3 Slump loss of series B concretes.

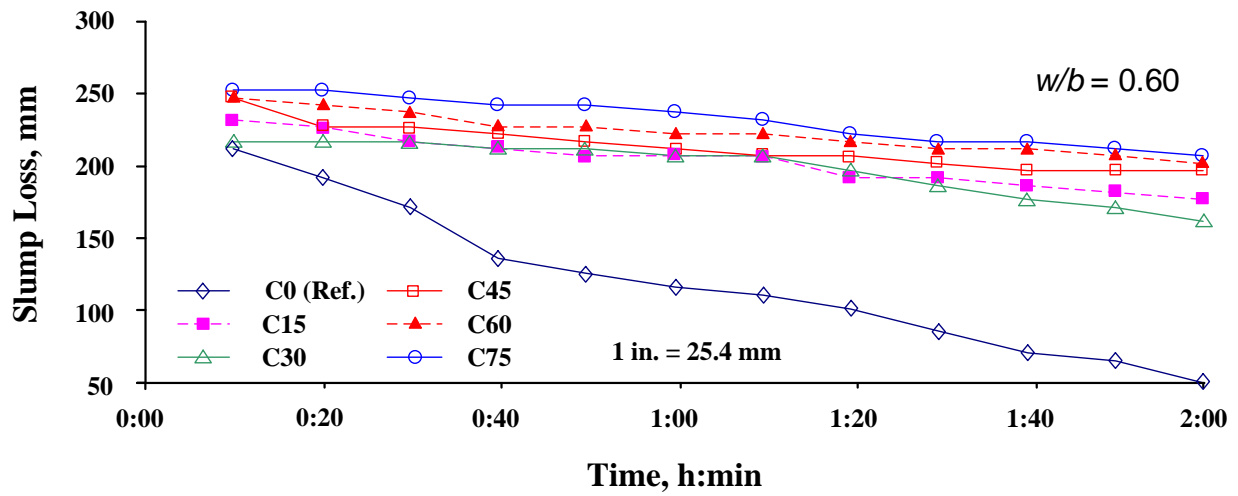


Fig. 4 Slump loss of series C concretes.

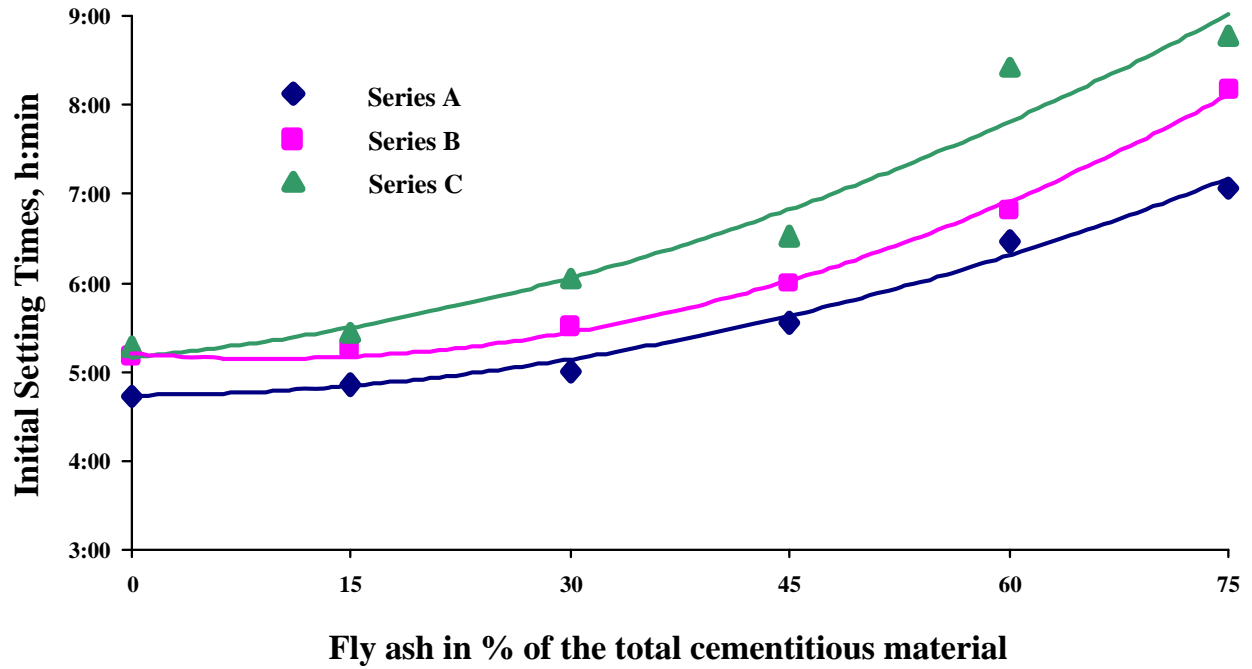


Fig. 5 Initial setting times vs fly ash content in % of the total cementitious material.

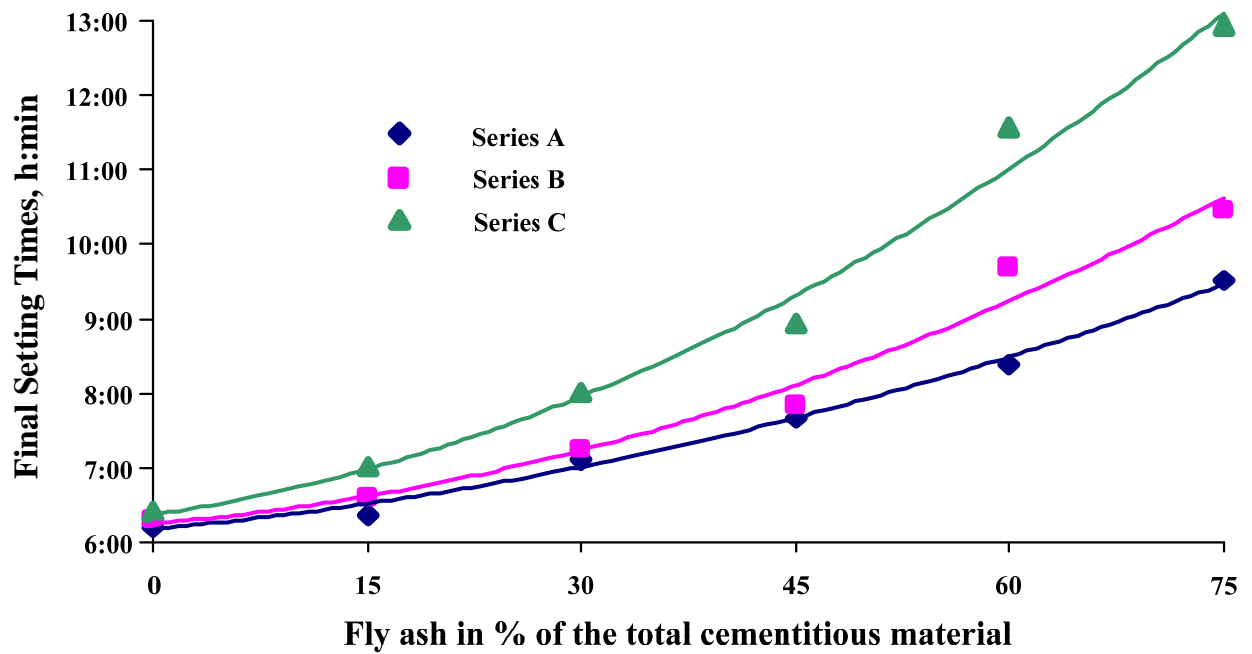


Fig. 6 Final setting times vs fly ash content in % of the total cementitious material.

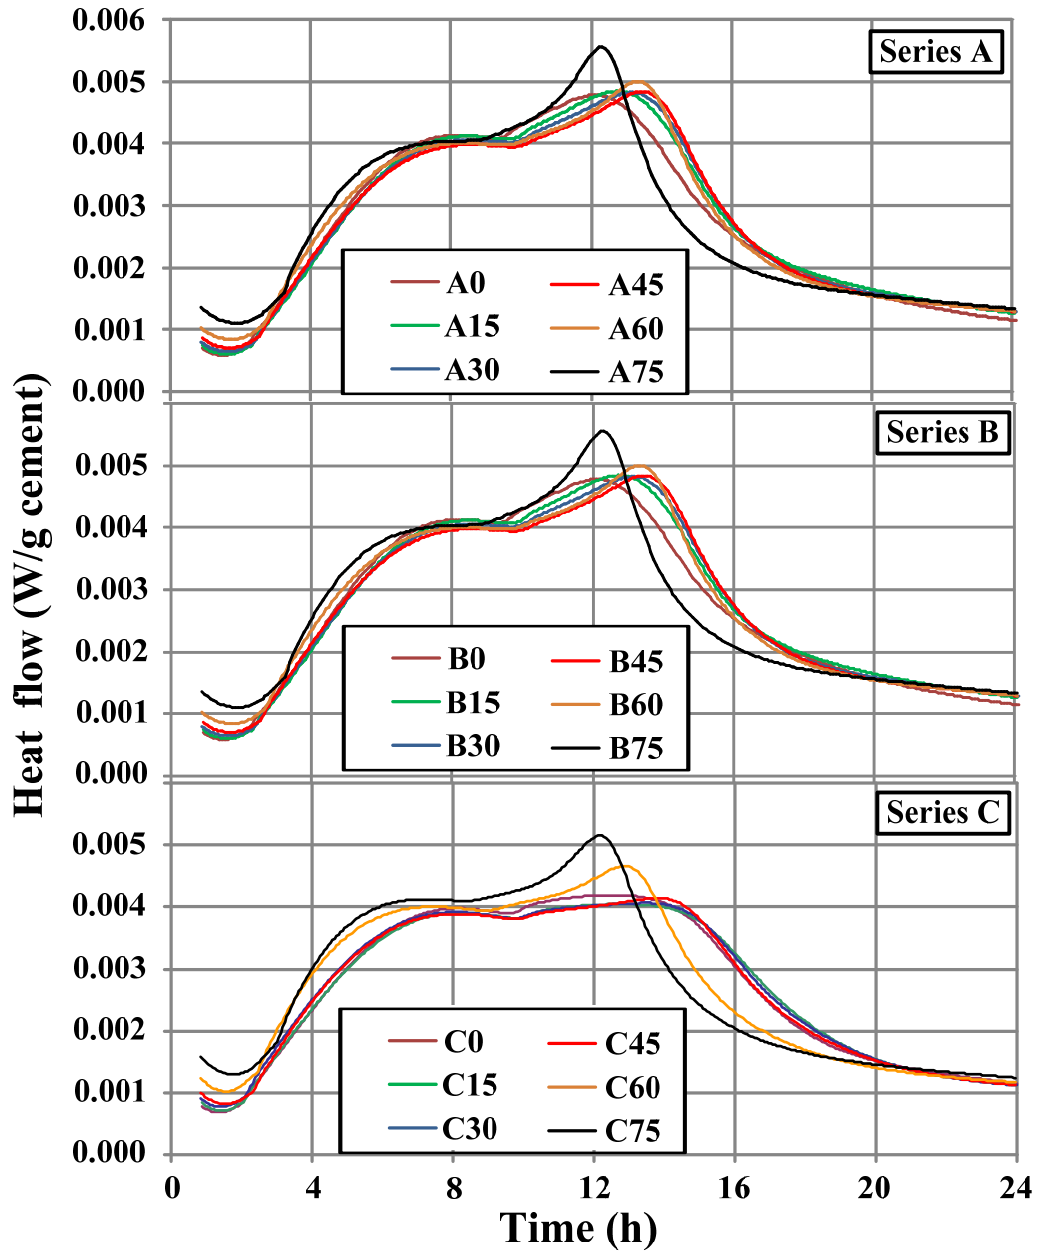


Fig. 7 Early-age heat release rates from isothermal calorimetry for the cement pastes reproduced according to the w/b of series A, B and C. Replicates for A0 (not shown) overlap one another and cannot be distinguished as individual curves.

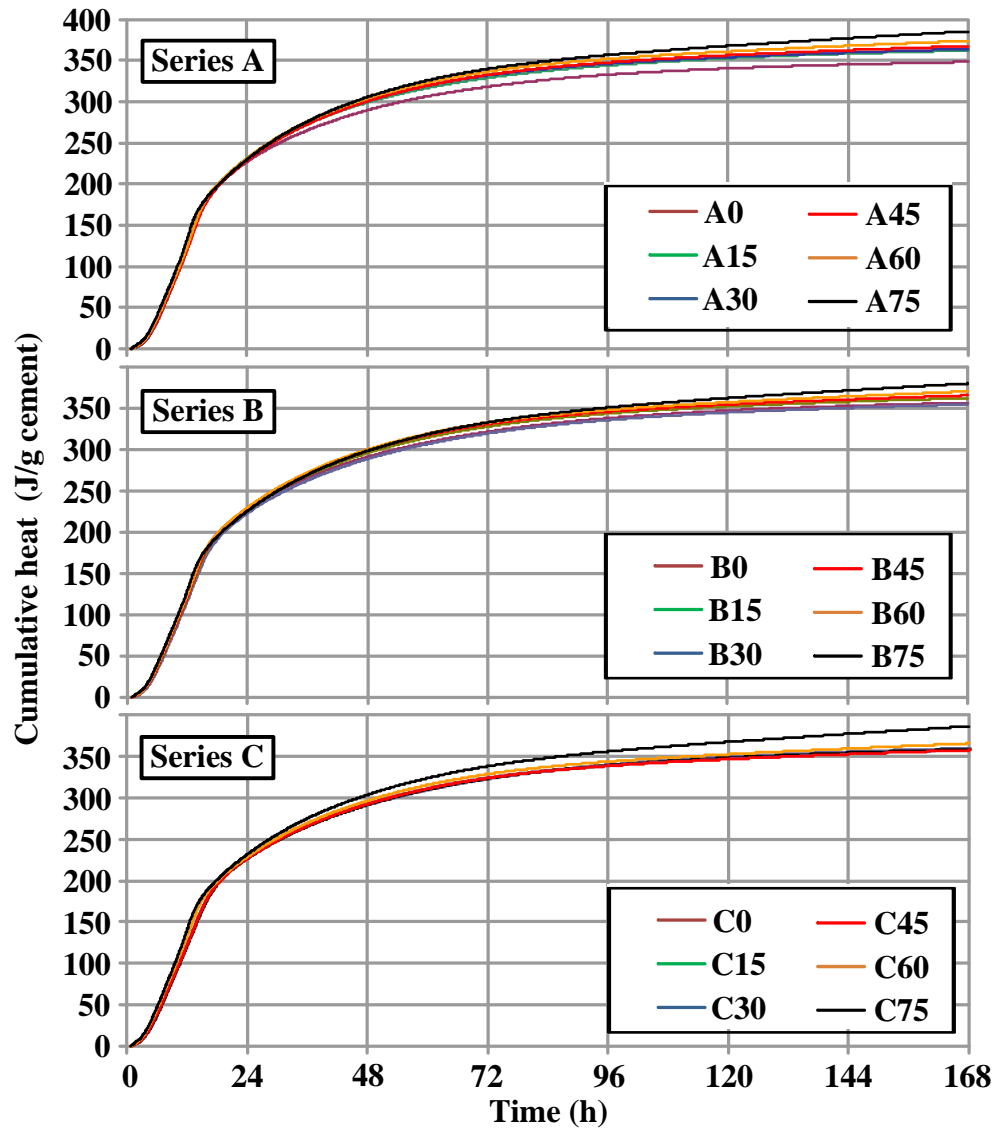


Fig. 8 Cumulative heat release for 7 d from isothermal calorimetry for the cement pastes reproduced according to the w/b of series A, B and C.

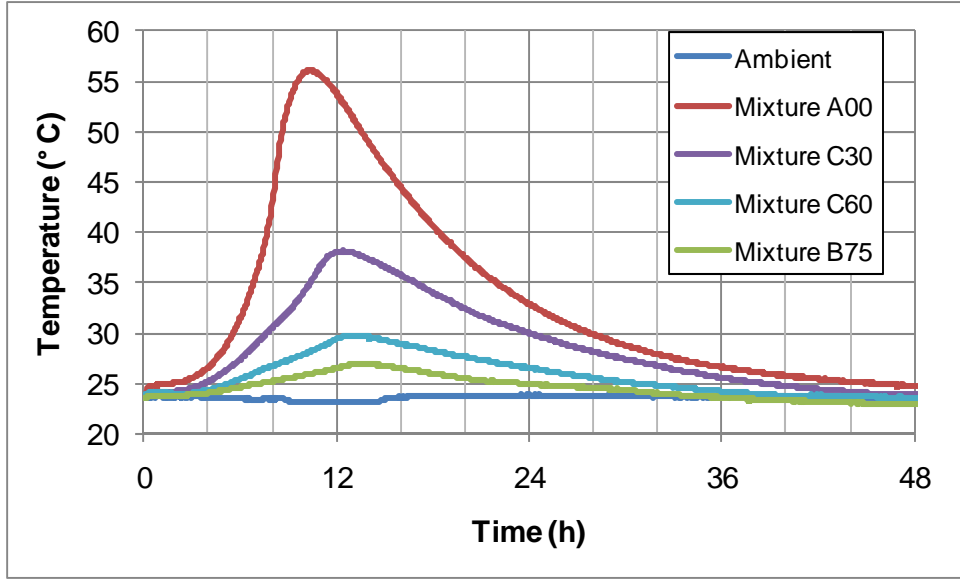


Fig. 9 Semi-adiabatic calorimetry curves for four of the pastes examined in this study.

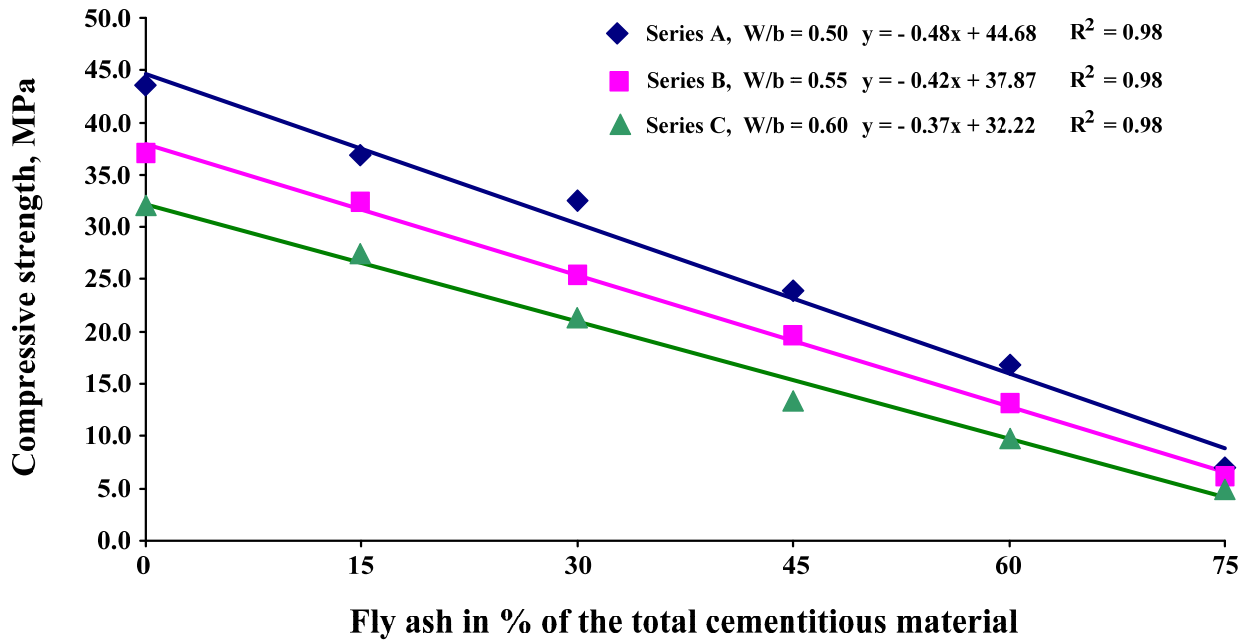


Fig. 10 Compressive strength at 28 d vs. fly ash content in % of the total cementitious material.

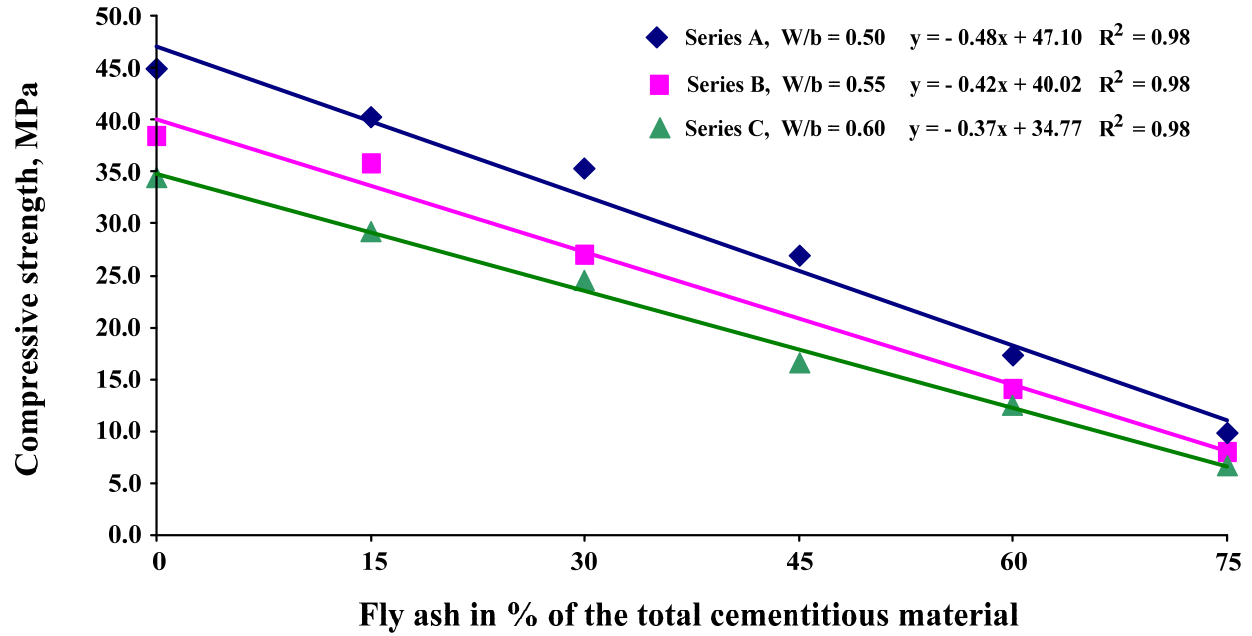


Fig. 11 Compressive strength at 56 d vs. fly ash content in % of the total cementitious material.

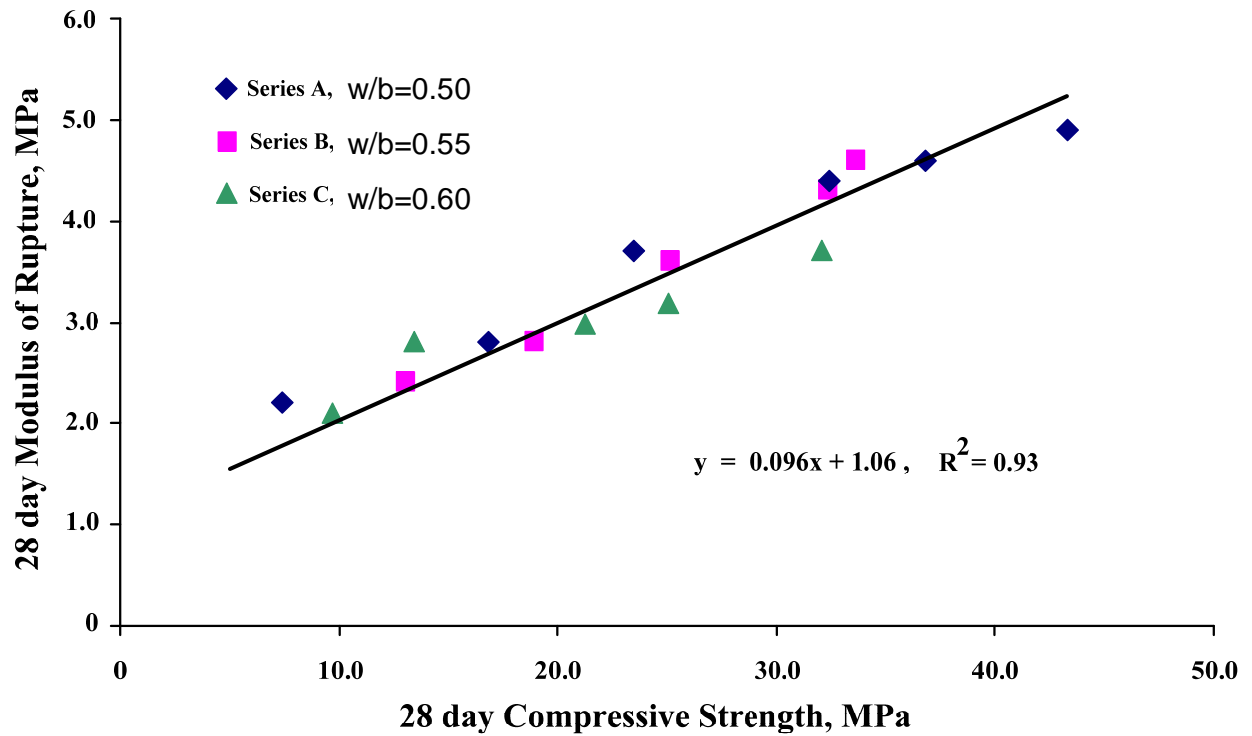


Fig. 12 Modulus of rupture vs. compressive strength at 28 d for series A, B, and C.

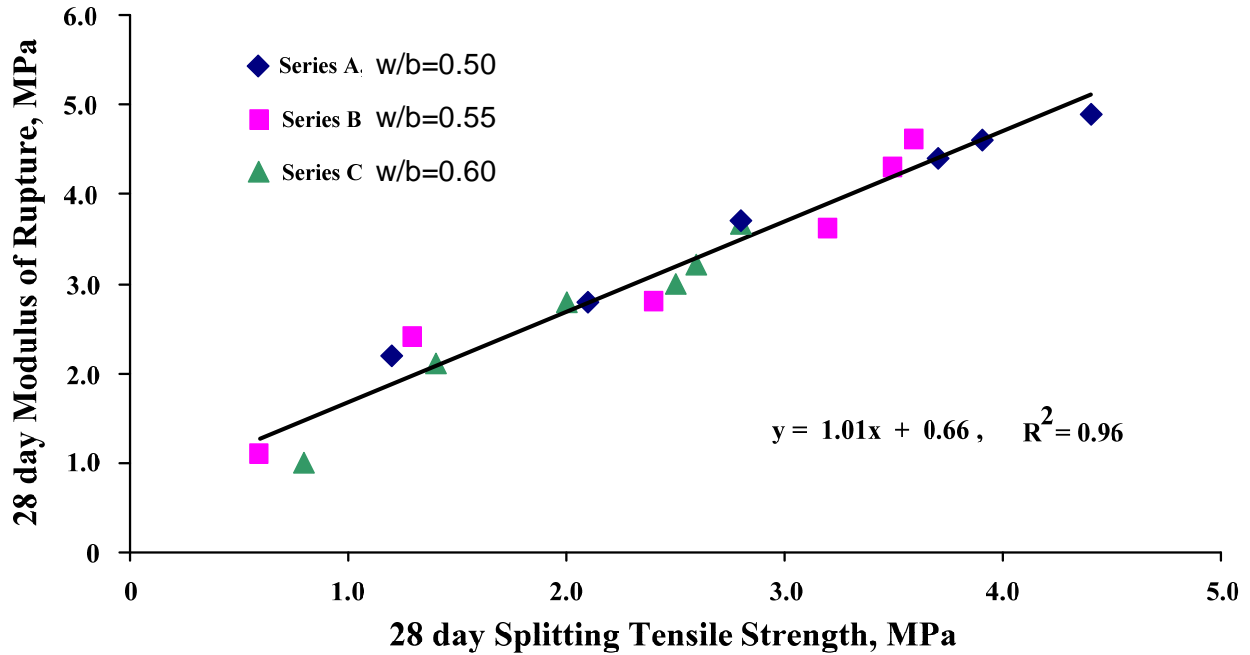


Fig. 13 Splitting tensile strength vs. modulus of rupture at 28 d for series A, B, and C.

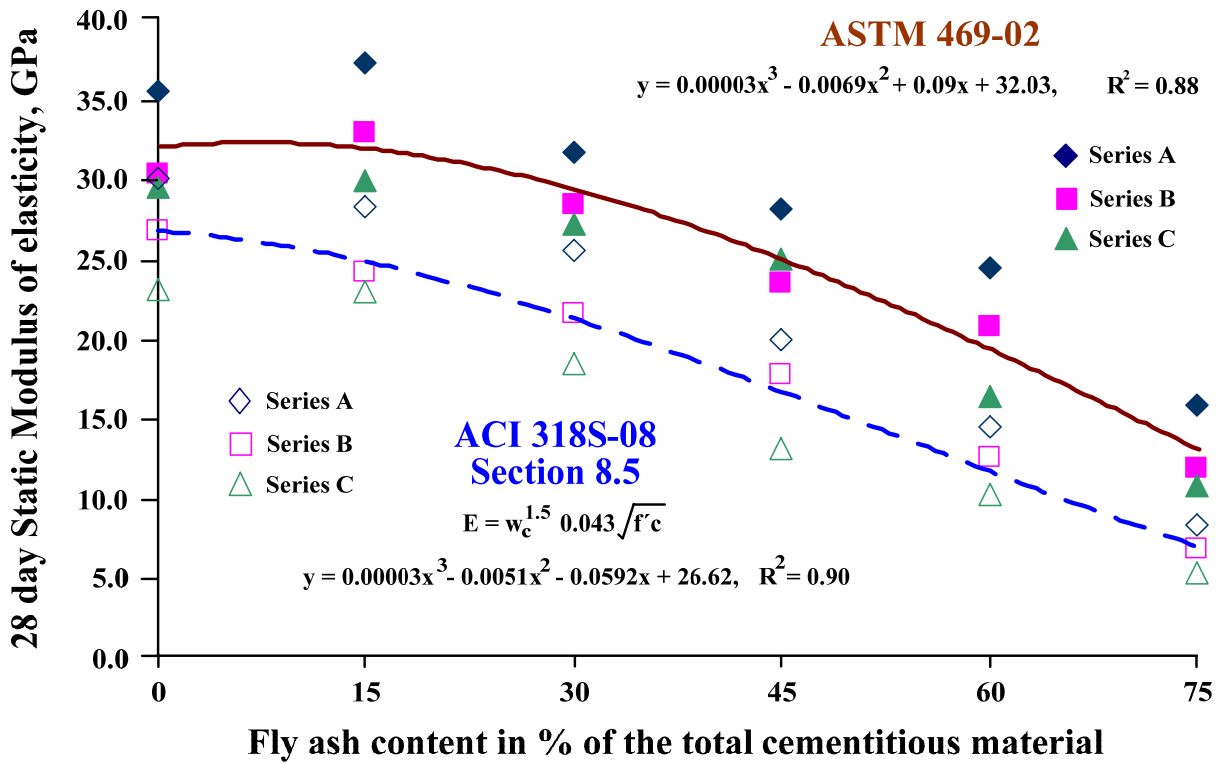


Fig. 14 Static modulus of elasticity (E) at 28 d vs. fly ash content in % of the total cementitious material.