

Revealing Electronic Signature of Lattice Oxygen Redox in Lithium Ruthenates and Implications for High-Energy Li-ion Battery Material Designs

Yang Yu^{a,*}, Pinar Karayaylali^b, Stanisław H. Nowak^c, Livia Giordano^{b,d}, Magali Gauthier^{d,†}, Wesley Hong^a, Ronghui Kou^e, Qinghao Li^f, John Vinson^g, Thomas Kroll^c, Dimosthenis Sokaras^{c,*}, Cheng-Jun Sun^e, Nenian Charles^d, Filippo Maglia^h, Roland Jung^h, Yang Shao-Horn^{a,b,d,*}

^a Department of Materials Science and Engineering, MIT, Cambridge, MA 02139, USA

^b Department of Mechanical Engineering, MIT, Cambridge, MA 02139, USA

^c SLAC National Accelerator Laboratory, Menlo Park, CA, 94025, USA

^d Research Laboratory of Electronics, MIT, Cambridge, MA 02139, USA

^e Advanced Photon Source, Argonne National Laboratory, Argonne, IL 60439, USA

^f Advanced Light Source, Lawrence Berkeley National Laboratory, CA 94720, USA

^g National Institute of Standards and Technology, Gaithersburg, Maryland 20899, USA

^h BMW Group, Petuelring 130, 80788 Munich, Germany

[†] Current address: M.G.: LEEL, NIMBE, CEA, CNRS, Université Paris-Saclay, CEA

Saclay 91191 Gif-sur-Yvette, France.

Corresponding Authors

* Yang Yu (yuy@mit.edu)


* Dimosthenis Sokaras (dsokaras@slac.stanford.edu)

* Yang Shao-Horn (shaohorn@mit.edu)

Abstract

Anion redox in lithium transition metal oxides such as Li_2RuO_3 and Li_2MnO_3 , has catalyzed intensive research efforts to find transition metal oxides with anion redox that may boost the energy density of lithium-ion batteries. The physical origin of observed anion redox remains debated, and more direct experimental evidence is needed. In this work, we have shown electronic signatures of oxygen-oxygen coupling, direct evidence central to lattice oxygen redox ($\text{O}^{2-}/(\text{O}_2)^{n-}$), in charged $\text{Li}_{2-x}\text{RuO}_3$ after Ru oxidation ($\text{Ru}^{4+}/\text{Ru}^{5+}$) upon first-electron removal with lithium de-intercalation. Experimental Ru L_3 -edge high-energy-resolution fluorescence detected X-ray absorption spectra (HERFD-XAS), supported by *ab-initio* simulations, revealed that the increased intensity in the high-energy shoulder upon lithium de-intercalation resulted from increased O-O coupling, inducing (O-O) σ^* -like states with π overlap with Ru d -manifolds, in agreement with O K-edge XAS spectra. Experimental and simulated O K-edge X-ray emission spectra (XES) further supported this observation with the broadening of the oxygen non-bonding feature upon charging, also originated from (O-O) σ^* states. This lattice oxygen redox of $\text{Li}_{2-x}\text{RuO}_3$ was accompanied by a small amount of O_2 evolution in the first charge from differential electrochemistry mass spectrometry (DEMS) but diminished in the subsequent cycles, in agreement with the more reduced states of Ru in later cycles from Ru L_3 -edge HERFD-XAS. These observations indicated that Ru redox contributed more to discharge capacities after the first cycle. This study has pinpointed the key spectral fingerprints related to lattice oxygen redox from a molecular level and constructed a transferrable framework to rationally interpret the spectroscopic features by combining advanced experiments and theoretical calculations to design materials for Li-ion batteries and electrocatalysis applications.

TOC

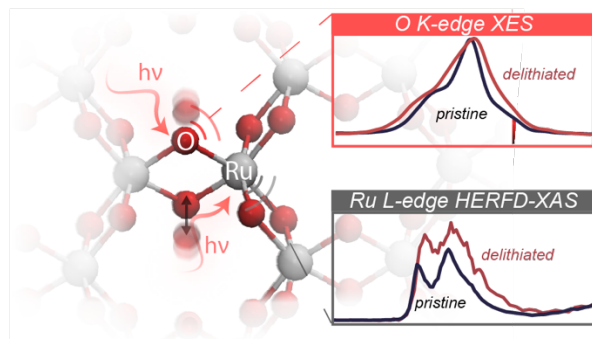

1. Introduction

The redox process of positive electrode materials largely dictates the energy density and cycling stability of the Li-ion batteries. Conventional positive electrode materials including LiCoO_2 and $\text{LiNi}_x\text{Mn}_y\text{Co}_z\text{O}_2$, with layered structures, hinge on the reversible redox couples of $3d$ transition metals including $\text{Co}^{3+}/\text{Co}^{4+}$,¹⁻² $\text{Ni}^{2+}/\text{Ni}^{4+}$ (or $\text{Ni}^{3+}/\text{Ni}^{4+}$)³⁻⁴ and $\text{Mn}^{3+}/\text{Mn}^{4+}$,⁵⁻⁶ accompanied by lithium (de-)intercalation, delivering a capacity of around 140 mAh/g,¹⁻⁶ upon charging to 4.3 V with respect to Li metal (V_{Li}). This redox process is rooted in the electronic structure of lithium early transition metal oxides. Due to their large electronegativity difference, oxygen $2p$ -states lie well below the transition metal d -states, hence, the Fermi level has a predominantly metallic character, and the transition metals mainly undertake the burden of the redox reaction.⁷⁻⁹ For most transition metals, this cationic redox scenario usually provides one electron per metal site and poses significant limitations on the energy density of positive electrode materials for mobile devices and automotive applications.⁹ However, as we move from early to late transition metals, or to higher valence metal states via lithium de-intercalation, we increase the electronegativity of the transition metal species.¹⁰ This results in a larger degree of energetic overlap between

the metal *d*-states and the oxygen *p*-states, and therefore a more covalent interaction between the transition metal and oxygen.^{8-9, 11} In this scenario a direct extraction/replenishment of the electron density from the oxygen density of states can occur.^{7-8, 12} This scenario is usually referred to as anionic redox, in contrast with conventional cationic redox. The notion of anion redox arose for the first time in LiCoO₂ in the 1990s, where oxygen release was observed upon charging up to 4.4 V_{Li}.¹³ Ceder *et al.*¹² explained this finding using density functional theory (DFT) calculations in which both metal and oxygen contribute to the redox processes at high potentials.¹² Within the 3*d* metals family, going from early transition metals to late transition metals, this oxygen charge compensation mechanism is augmented due to a more covalent metal-oxygen framework¹².

Li-rich layered oxides, Li₂MO₃ (*M* = Ru, Ir, Mn),^{8, 11, 14-22} have been studied extensively and offer much higher energy density than LiMO₂ by providing more lithium for (de-)intercalation. These oxides can be written generally as Li(Li_{1/3}M_{2/3})O₂, with 1/3 of the transition metal sites within the transition metal layer occupied by Li. This Li excess allows a higher transition metal valence (4+) , compared to LiMO₂ (3+), and therefore leads to more overlap between transition metal and oxygen states, resulting in a highly covalent *M*-O bonding.^{7, 10, 12} These reported Li-rich metal oxides can be divided into two classes. The first class is represented by oxides derived from Li₂MnO₃,^{17-18, 21, 23-37} which exhibits a relatively poor reversibility attributed to oxygen redox (oxidation) into molecular oxygen, leading to oxygen loss. Although Li₂MnO₃ can yield a first cycle discharge capacity higher than 200 mAh/g, upon charging to 4.8 V_{Li},^{25, 29-32, 34-35} it suffers from a poor cycling performance.^{23, 29-31} Considerable oxygen loss occurs upon charging Li₂MnO₃^{17,32}, where

0.125 oxygens can be released per unit of extracted Li³⁰. The Li₂MnO₃ derived compounds such as Li(Li_xMn_yNi_zCo_{1-x-y-z})O₂ (Li-rich Mn-rich NMC) introduce additional redox couples (Ni²⁺/Ni⁴⁺ and Co³⁺/Co⁴⁺) that may boost both cationic and lattice oxygen redox, reaching a reversible capacity of around 300 mAh/g.³⁶⁻³⁸ Although their cycling stability is much improved compared to pure Li₂MnO₃ electrodes, they still suffer from a significant voltage decay over subsequent cycles³⁷, and the oxygen redox contribution to the redox process is diminished upon extended cycling.³⁷ The second group of Li-rich metal oxides is derived from noble metals including Li₂RuO₃^{11, 39-41} and Li₂IrO₃,⁴²⁻⁴³ which show reversible capacities with a two-electron transfer process and a high cycle life. For example, Tarascon and co-workers^{15-16, 39-40} have shown that Li₂Ru_{1-x}Mn_xO₃ and Li₂Ru_{1-x}Sn_xO₃ deliver first discharge capacities as high as 250 mAh/g,^{16, 39-40} and capacity retention of higher than 80 % after 100 cycles.^{16, 39} It has been proposed that the capacity corresponding to the second electron transfer results from reversible lattice oxygen oxidation into peroxo- and superoxo- like species in the bulk.^{11, 16, 39-40}

The mechanism giving rise to the reversible capacities associated with the lattice oxygen redox is not well understood. Unambiguous experimental evidence or an electronic structure signature for lattice oxygen redox for these Mn-, Ir- and Ru- based oxides is missing. There are primarily two schools of thought on the physical origin of lattice oxygen redox in Li-rich oxides. The first class of proposed mechanisms argues that anion redox induces the formation of (O₂)ⁿ⁻ peroxo-like species,^{11, 39-41, 43} and the redox couple O²⁻/(O₂)ⁿ⁻ can proceed reversibly upon cycling. A certain M-O bond covalency is required for reversible oxidation of the anion as proposed by Doublet, Tarascon and coworkers.^{11, 41} Tarascon *et al.* have proposed the existence of peroxo-like O₂ⁿ⁻ species for Li_{2-x}RuO₃ at 4.6

V_{Li} during the first cycle via X-ray photoelectron spectroscopy (XPS) studies.^{16, 39} The formation of such peroxo-like species is accompanied by Ru reduction which is referred to as a reductive coupling mechanism.^{11, 40} The Ru^{6+} species are stabilized by modifying the coordination sphere of Ru through oxygen-oxygen bond formation and the transfer of extra electrons to the transition metal for reduction, eventually forming $Ru^{5+}-(O_2)^{2-}$ peroxo-species or $Ru^{4+}-(O_2)^{-}$ superoxo-species. However, we should note that the XPS measurement has a penetration depth of only 5 nm to 10 nm⁴⁴. Therefore, the evidence provided by XPS is from the surface and subsurface of the materials which is likely not representative of the bulk. Moreover, the XPS fingerprint is not clear and cannot be unequivocally assigned to peroxo-like species, but might also come from surface electrolyte decomposition products. Hence, there is no unambiguous experimental evidence from an electronic structure perspective to support this proposed redox process. The formation of peroxo-like species is further demonstrated and visualized by McCalla *et al.*⁴³ using high-resolution transmission electron microscopy and neutron diffraction in delithiated $Li_{2-x}IrO_3$, where an O-O bond distance of around 2.4 Å has been shown.⁴³ In addition, Saubanère *et al.*¹¹ have reported from crystal orbital overlap population (COOP) analysis that the covalent bonding between Ru-O stabilizes the peroxo-like species in $Li_{2-x}RuO_3$ upon oxidation. In contrast, the Mn-O bond has less covalency, resulting in further oxidation of peroxo-like species and eventually evolving molecular oxygen. This idea has also been further explored by Bruce and coworkers.³⁶ Their O K-edge resonant inelastic X-ray scattering (RIXS) study on Li-rich Mn-rich NMC showed an increased intensity of the elastic peak (around 531 eV) upon charging to around 4.4 V_{Li} , a fingerprint they assigned to formation of oxygen-localized electron holes.³⁶ However, the rationale for such

an assignment remains unclear. Moreover, there is no strong indication of true peroxide or superoxide species formation since there is no clear Raman signal from 800 cm^{-1} to 1100 cm^{-1} in *ex-situ* charged Li-rich NMC samples,³⁶ the characteristic wavenumber range for metal peroxide and superoxides.³⁶ Bruce and coworkers have concluded that the reversibility of anionic redox relies on more delocalized O holes, which require more delocalized M-O bonds from higher M-O covalency.

In the second school of thought, the oxygen redox of Li-rich oxides is attributed to the reversible oxidation and reduction of the non-bonding oxygen density of states created by Li-O-Li configuration,⁴⁵⁻⁴⁶ unique to Li-excess or disordered oxides. Due to the high ionicity of Li-O interaction, the oxygen 2*p* orbital bond with lithium resembles a lone-pair non-bonding oxygen, and its density of states lies at a higher electron energy level compared to the corresponding ones of transition metal bonded oxygen (bonding oxygen), thus providing a more facile electron transfer from oxygen.⁴⁵ Therefore, oxygen redox can be represented as a redox couple of O^{2-}/O^- , where electron density is directly taken from non-bonding oxygen 2*p* states. However, there is no unequivocal experimental evidence that oxygen redox proceeds as a redox couple of O^{2-}/O^- without oxygen sub-lattice distortion. This mechanism is further extended by Gent and Chueh^{38, 47}, where they proposed that anionic redox is a dynamic process, requiring synergistic transition metal migration and O^{2-}/O^- redox couple. *In-situ* X-ray diffraction (XRD) and RIXS³⁸ on Li-rich and Mn-rich NMC ($\text{Li}_{1.2}\text{Mn}_{0.54}\text{Ni}_{0.13}\text{Co}_{0.13}\text{O}_2$) demonstrated that the oxygen redox and the transition metal migration are coupled. The oxygen-bonded transition metal migrates to a tetrahedral site, creating non-bonding oxygen 2*p* states on the de-coordinated oxygen. Similar to what Seo *et al.*⁴⁵ have proposed, this non-bonding oxygen can perform O^{2-}/O^-

redox, coupled with continuous transition metal migration. In particular, a RIXS feature with an emission energy of 523.7 eV, different from the 525 eV emission feature for conventional O^{2-} species, could be assigned to the anionic redox state in both Li-ion and Na-ion battery electrodes.^{38, 48} However, although further theoretical study shows that this specific RIXS feature corresponds to excitations into unoccupied O-2*p* states, *e.g.*, oxidized oxygen because 2*p* orbitals of O^{2-} are full occupied, a simple extension of a peroxide model into transition-metal oxide material remains questionable⁴⁹.

In this study, we find unambiguous evidence of lattice oxygen redox upon lithium de-intercalation from Li_2RuO_3 . By coupling hard and soft X-ray absorption (XAS) and X-ray emission spectroscopy (XES) experimental studies with *ab-initio* Bethe-Salpeter equation (BSE) spectroscopy calculations⁵⁰, we capture the redox processes of both oxygen and ruthenium in $Li_{2-x}RuO_3$ upon the first charge, which contrasts the redox process of conventional battery materials including $LiCoO_2$ and $LiNi_{1/3}Mn_{1/3}Co_{1/3}O_2$. This detailed characterization of the redox process allows us to qualify different previously proposed hypotheses and experimental studies regarding lattice oxygen redox. Furthermore, combining the redox process with differential mass spectrometry (DEMS) measurements, we evaluate the reversibility of the anionic redox of Li_2RuO_3 and discuss the implications for the design of high-energy positive electrode materials leveraging anionic redox.

2. Result and Discussion

Electronic signatures of oxygen-oxygen coupling in $Li_{2-x}RuO_3$

XAS and XES on the charged oxide-only pellet electrodes, without conductive carbon and binder, revealed electronic structure evidence of oxidation of non-bonding oxygen in Li_2 -

Li_2RuO_3 . Both O K-edge XAS total fluorescence yield (TFY) and Ru L₃-edge high-energy-resolution fluorescence detected (HERFD)-XAS of the pristine electrode (Li_2RuO_3) were composed of two major peaks (*c.a.* 528.8 eV and 530.8 eV for the O K-edge in Figure 1(a) and 2841.1 eV and 2843.6 eV for the Ru L₃-edge in Figure 1(b)). *Ab-initio* theoretical calculations with OCEAN⁵⁰⁻⁵¹ using the pristine Li_2RuO_3 structure ($C2/c$)⁵²⁻⁵³ resulted in simulated O K-edge (Figure 1(a)) and Ru L₃-edge (Figure 1(b)) spectra that agree well with the experimental spectral fingerprints of the pristine electrode. Furthermore, these calculations also enabled us to visualize the electron densities corresponding to specific excited state features. The low-energy peak can be attributed to a t_{2g} feature, having a metal $4d_{xy}$ (degenerate with $4d_{yz}$ and $4d_{zx}$) orbital with a π overlap with O $2p$ states, whereas the high-energy peak can be attributed to the e_g^* states, comprising the σ^* overlap between transition metal $4d_{x^2-y^2}$ states and O $2p$ states, as shown in Figure 1(c). Here we should note that the computed spectra have slightly larger t_{2g} and e_g splitting compared to the experimental spectra, which indicates we have an overestimation of the ligand field. Moreover, as we might note that in the pristine experimental Ru L₃-edge XAS spectra of Li_2RuO_3 (Figure 1(b)), there is a small high-energy shoulder which is not understood, which might potentially come from mixed oxidation states⁵⁴⁻⁵⁶, and/or surface reacting with moisture undergoing proton and lithium ions exchange.⁵⁷ Worth notably, this feature has never been reported by previous Ru L₃-edge measurements of Ru-based oxides⁵⁸ and complexes⁵⁴⁻⁵⁵ since they were limited by the significant core-hole lifetime broadening and therefore such small feature was not resolved, which requires further studies.

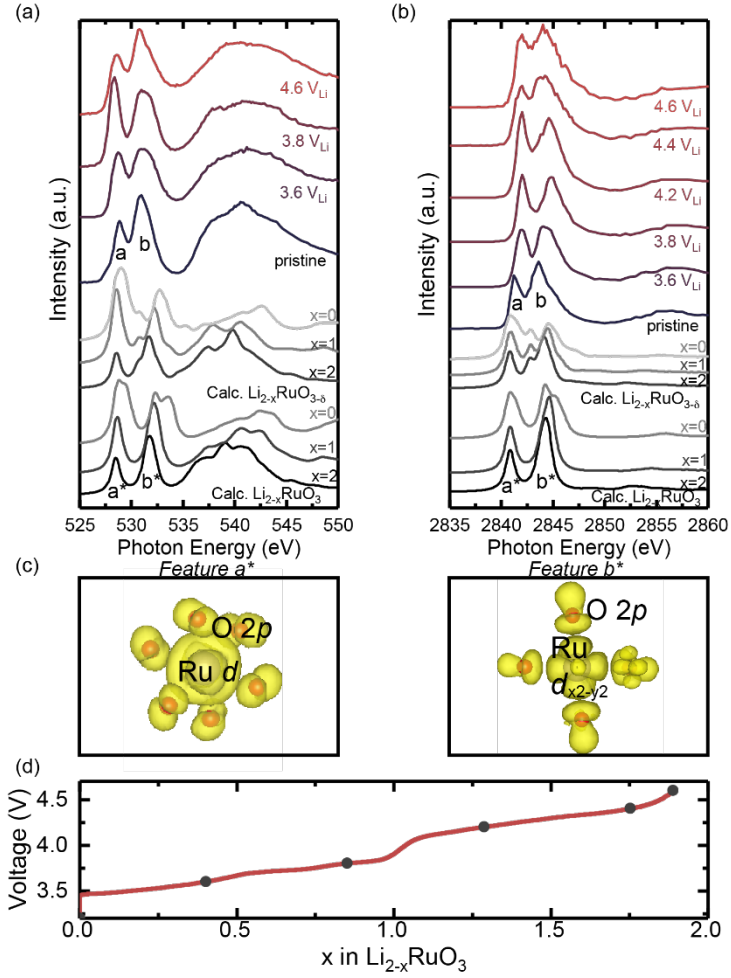


Figure 1: (a) O K-edge XAS collected in TFY mode, and (b) Ru L₃-edge HERFD-XAS spectra of Li_{2-x}RuO₃ pellets as a function of charging potential (3.6 V_{Li}, 3.8 V_{Li}, 4.2 V_{Li}, 4.4 V_{Li}, and 4.6 V_{Li}). Corresponding simulated spectra of the Li₂RuO₃, Li₁RuO₃, Li₀RuO₃ as well as Li₂RuO_{3-δ}, Li₁RuO_{3-δ}, Li₀RuO_{3-δ} (δ = 1/4), are also shown for comparison, representing the structures with oxygen vacancies. The calculated O K-edge and Ru L₃-edge spectra are shifted by 528 eV and 2884 eV, respectively, to allow for a direct comparison with the experimental spectra. The computed features labeled “a*” and “b*” match with the experimental features “a” and “b” in the pristine Li₂RuO₃. (c) Visualization of charge densities that corresponds to a* and b* of the computed spectra of pristine Li₂RuO₃; a* can be assigned to the *t*_{2g} feature comprised of Ru *d*- manifolds and O 2*p* state with a *π* overlap, and b* can be assigned to *e*_g* feature composed of Ru 4*d*_{x²-y²} and O 2*p* orbitals with a *σ** overlap. (d) The voltage profile of Li_{2-x}RuO₃ pellets in the first cycle show two major plateaus at 3.6 V_{Li} and 4.2 V_{Li} in line with previous works.^{16, 39-40} The closed black circles indicate the voltages where the *ex-situ* samples were collected. The fitted peak intensities of *t*_{2g} and *e*_g peak at each state of charge is shown in Figure S1, and the fitted peaks for O K-edge and Ru L-edge are shown in Figure S2 and S3, respectively.

Upon charging, the low-energy t_{2g} peak intensity (integrated area) gradually increased up to 3.8 V_{Li}, and then decreased, relative to that of the high-energy e_g feature, in both O K-edge XAS (Figure 1(a) and Figure S1(a)) and Ru L-edge HERFD XAS (Figure 1(b) and Figure S1(b)). The increase of the t_{2g} peak integrated area up to 3.8 V_{Li}, which corresponds to the first lithium de-intercalation per formula from Li₂RuO₃ in the low-voltage plateau as shown in Figure 1(d), can be attributed to the removal of approximately one t_{2g} electron upon oxidation of Ru⁴⁺ to Ru⁵⁺ in Li_{2-x}RuO₃. Similar spectroscopic changes have been reported for oxides relying predominantly on cationic redox including LiCoO₂⁵⁹⁻⁶⁰ and LiNi_{1/3}Mn_{1/3}Co_{1/3}O₂⁶¹, where the metal L-edge shifts monotonically and the pre-peak area in O K-edge XAS increased,⁵⁹⁻⁶¹ marking the removal of the electron from transition metal d states upon lithium de-intercalation. On the other hand, upon charging to voltages greater than 3.8 V_{Li}, the e_g feature in both Ru L₃-edge and O K-edge spectra were found to grow relative to the low-energy t_{2g} peak and broaden considerably on the high-energy side (Figure 1(a), (b), and Figure S1). Through DFT calculations, we determined the most energetically favorable structures at different lithium contents of Li_{2-x}RuO₃ by enumerating all possible configurations (computational details shown in Methods section). Simulated Ru L₃-edge (Figure 2(a) and (b)) and O K-edge (Figure S4) spectra of Li_{2-x}RuO₃ revealed the appearance of a high-energy shoulder in the vicinity of the e_g feature for Li_{0.5}RuO₃ and Li₀RuO₃, which could potentially account for the broadening observed in the experimental spectra. Aided by a charge density visualization at the shoulder peak energy, we assigned this feature to a stronger oxygen-oxygen (O-O) σ^* – like antibonding states with a π^* overlap with transition metal d -manifolds (Figure 2(b)). This combined experimental and simulated approach for the Li_{2-x}RuO₃ revealed electronic structure evidence for the

antibonding state of oxygen-oxygen coupling associated with lattice oxygen redox in bulk proposed previously from DFT studies.¹¹

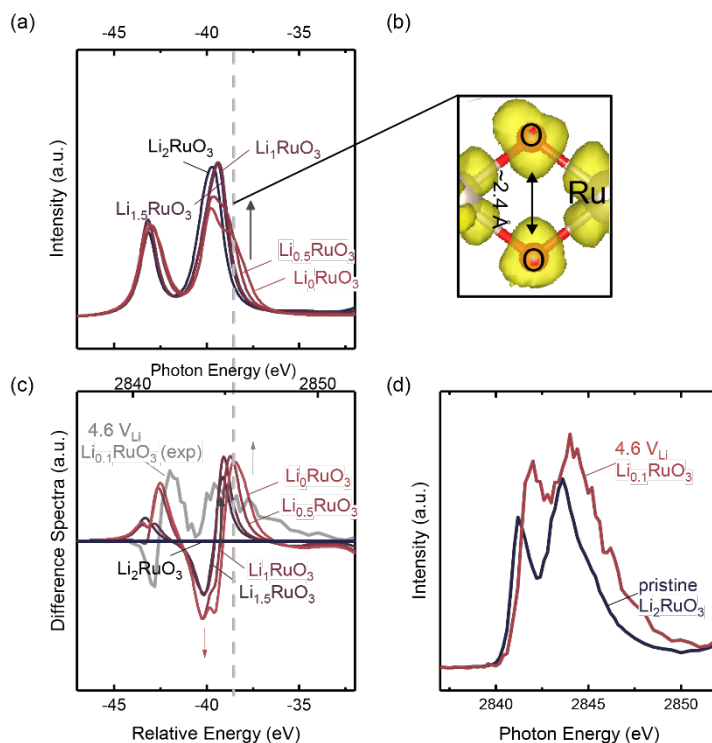


Figure 2: (a) Calculated Ru L₃-edge HERFD XAS and (c) calculated and experimental difference spectra of Li_{2-x}RuO₃. Upon delithiation, an additional peak appears at a photon energy just above the e_g feature. The electron density of this excitation shows it to be an (O-O) σ^* -like feature hybridized with Ru d-manifolds due to oxygen cage distortion and shortening of the O-O bond from 2.8 Å to 2.4 Å upon delithiation, as shown in the schematic in (b). (d) Experimental Ru L₃-edge HERFD XAS of Li_{2-x}RuO₃ charged to 4.6 V_{Li} (red) and pristine Li_{2-x}RuO₃ (black), where a broadening of e_g peak was observed with higher intensity at higher photon energy, matching with the observation in the computed spectra, and can be attributed to the creation of (O-O) σ^* -like feature. The voltage profile determined from the DFT-calculated structure of Li_{2-x}RuO₃ is shown in comparison with the experimental profile in Figure S5.

Theoretical spectra simulations of other candidate structures show that the experimentally observed changes in the O K- and Ru L-edge XAS spectra cannot be solely explained by introducing oxygen vacancies in Li_{2-x}RuO₃, which is known to evolve oxygen gas at voltages around 4.2 V_{Li},⁴⁰ nor by true peroxo (d_{O-O} ≈ 1.5 Å)⁶² or superoxo- (d_{O-O} ≈ 1.2 Å –

$1.3 \text{ \AA})^{63}$ species of oxygen with bond length of less than $1.8 \text{ \AA}$. The high-energy peak shoulder observed in the experimental XAS spectra of $\text{Li}_{2-x}\text{RuO}_3$ obtained from the $4.2 \text{ V}_{\text{Li}}$ plateau cannot be explained by the presence of lattice oxygen vacancies. The simulated O K-edge (Figure 1(a) and Figure S6) and Ru L_3 -edge (Figure 1(b) and Figure S7) of $\text{Li}_{2-x}\text{RuO}_{3-\delta}$ with $\delta = 0.25$ oxygen vacancies per formula unit in the bulk led to additional features between the t_{2g} and e_g peaks, as well as a significant decrease in the intensity of the e_g relative to the t_{2g} feature, which were not clearly experimentally observed (Figure 1(a), (b) and Figure S1). Moreover, we have also performed a test calculation on Ru L -edge XAS of a surface Ru atom surrounded by surface oxygen vacancies as in Figure S7(d), and a similar trend as the bulk oxygen vacancy calculations was also observed. Here, we saw a more intense feature between t_{2g} and e_g peaks and more depressed e_g peaks due to larger degree of Ru reduction, compared to the cases with bulk oxygen vacancies. (Figure S7(a)) However, we cannot rule out the presence of oxygen vacancy formation as we have also observed a slight rise of the feature between e_g and t_{2g} , and this observation could potentially coming from oxygen vacancies formed in the oxides upon charging, but the additional features at high photon energy cannot be solely explained by oxygen vacancy formation. Previous computational work on $\text{Li}_{2-x}\text{RuO}_3$ and $\text{Li}_{2-x}\text{IrO}_3$ showed the presence of distorted oxygen cages with an oxygen distance around $2.4 \text{ \AA}$,^{40, 43} and refined neutron diffraction data in chemically delithiated $\text{Li}_{2-x}\text{IrO}_3$ samples also confirmed an oxygen-oxygen distance of around $2.4 \text{ \AA}$.⁴³ This O-O bond distance does not support the presence of true peroxide or superoxide species. We performed Ru L_3 -edge and O K-edge spectra simulations by reducing the oxygen-oxygen bond distance from $2.4 \text{ \AA}$ to $1.8 \text{ \AA}$ in Li_0RuO_3 where we forced two oxygen atoms closer together while keeping the position of other

atoms the same. This led to increased high-energy shoulder intensities for both Ru L₃-edge and O K-edge, indicating a stronger oxygen-oxygen coupling, as shown in Figure S8 and Figure S9(a). However, a further reduction of the O-O bond distance from 1.8 Å to 1.2 Å, so to form a true superoxide, led to a drastic reduction in the e_g intensity compared to the t_{2g} peak. This could be the result of reduced σ overlap between Ru 4*d* and O 2*p* states coming from a smaller O-Ru-O bond angle associated with shorter O-O bonds. As such changes were not observed in the experimental XAS data in Figure 1, the formation of peroxo-like and superoxo-like species with an O-O bond length less than 1.8 Å in bulk Li_{2-x}RuO₃ ($1 \leq x \leq 2$) is also not likely based on our combined experimental and simulated study. Moreover, as we force the O-O bond distance from 2.4 Å to 1.8 Å and 1.2 Å, we induced an energy penalty of above 3 eV respectively, which also indicates that from an energetic standpoint, forming such short O-O bond distance in Li_{2-x}RuO₃ is not possible.

The oxygen-oxygen coupling in Li_{2-x}RuO₃ ($1 \leq x \leq 2$) is further supported by O K-edge valence XES, which probes the projected occupied local density of state (DOS) with O-2*p* symmetry. The XES spectra of the pristine electrode in Figure 3(a) and Figure 3(b) consisted of three major features: one major peak centered at ≈ 523 eV and two shoulders located at ≈ 521 eV and ≈ 526 eV, respectively. When comparing these, on a binding energy scale, with valence band XPS data from Li₂RuO₃, similar features are observed with different relative intensities due to different selection rules dictating valence XES and XPS (Figure 3(a)).⁶⁴ In line with previous work on perovskite materials that have comparable O K-edge XES spectra⁶⁴, we assign the major XES peak to non-bonding oxygen, and the high- and low-energy shoulders to anti-bonding and bonding Ru-O bonds, respectively.⁶⁴ This assignment is supported by the DFT projected DOS of Ru 4*d* and oxygen 2*p* in Figure

3(a), where the high-energy shoulder reflects Ru-O bonding states (≈ 6 eV in the DOS) with a predominantly oxygen character, the low-energy shoulder reflects anti-bonding Ru-O states with mostly metal character (≈ 1 eV in the DOS), and the center peak indicates non-bonding oxygen states without significant contribution of Ru *d*-electrons (≈ 2.5 eV in the DOS). Here, we should note that the center non-bonding peak position of computed ground-state DOS had some discrepancies with experimental O K-edge XES spectra (Figure 3(a)). When charging $\text{Li}_{2-x}\text{RuO}_3$ up to $3.8 V_{\text{Li}}$, there was no significant change observed for the O K-edge XES spectra (Figure 3(b)), in agreement with corresponding simulated O K-edge XES spectra of $\text{Li}_{2-x}\text{RuO}_3$ ($0 \leq x \leq 1$) in Figure 3(c). The O K-edge XES indicates that there is no oxygen participation upon first lithium removal. In contrast, upon charging $\text{Li}_{2-x}\text{RuO}_3$ to $4.2 V_{\text{Li}}$ and beyond a spectral broadening was observed (Figure 3(b)), indicative of changes to the probed oxygen states. This broadening was also found in the *ab-initio* calculated XES spectra of $\text{Li}_{0.5}\text{RuO}_3$ and Li_0RuO_3 (Figure 3(c)), especially for the oxygen non-bonding peak. Here we should note that for OCEAN simulation of O K-XES, since no core-hole effect is considered, the energy is referenced to the Fermi level, and the relative energy scale is the same as $E-E_f$ scale. Using the crystal orbital overlap population (COOP), in line with previous work,^{11, 41, 65-66} the broadening in the oxygen non-bonding feature can be attributed to an increased O-O antibonding character (by showing negative COOP intensity) in the energy range where we observed the broadening in computed spectra (from -2 eV to 0 eV vs. the Fermi level) in Figure 4(d). Furthermore, by visualizing the charge density in the same energy range, we observed that the charge density also resembled a (O-O) σ^* interaction with a nodal plane in the middle as shown in Figure 3(d). This finding further supports the formation of oxygen-oxygen coupling

upon charging $\text{Li}_{2-x}\text{RuO}_3$ in the high-voltage plateau of 4.2 V_{Li}. The peak broadening in the XES data most likely came from the (O-O) σ^* antibonding states (Figure 3(d)). These states are different from those with an additional π^* participation from Ru 4d electrons which are responsible for the increased intensity at the high-energy shoulder found in the XAS spectra (Figure 2). Here, we captured the creation of both “non-bonding” (O-O) σ^* in the O K-edge XES (Figure 3(d)) in contrast with “anti-bonding” (O-O) σ^* with metal (Ru) π^* contribution in XAS, shown in the charge density in Figure 2(a). Furthermore, such broadening in the experimental XES spectra was not observed in charged $\text{Li}_{1-x}\text{CoO}_2$ (Figure S12) and $\text{Li}_{1-x}\text{Ni}_{1/3}\text{Mn}_{1/3}\text{Co}_{1/3}\text{O}_2$ (Figure S12). Their largely unchanged peak widths indicate the absence of lattice oxygen-oxygen coupling (Figure 4(e)). However, broadening in the XES spectra was observed in substituted $\text{Li}_{2-x}\text{Ru}_{1-y}\text{M}_y\text{O}_3$ such as $\text{Li}_{2-x}\text{Ru}_{0.5}\text{Mn}_{0.5}\text{O}_3$ (Figure 4(e) and Figure S12) as well as $\text{Li}_{2-x}\text{MnO}_3$ derived materials including Li-rich Mn-rich NMC probed by RIXS,³⁶ where the central peak of the RIXS spectra broadened upon charging. This broadening in O K-edge XES appears concurrently with changes in the O K-edge absorption, including broadening and the creation of an additional feature around 531 eV, but not in metal L-edges as in Ru cases.³⁸ This observation is in agreement with previous COOP analysis performed by Saubanère *et al.* on Li_2MnO_3 ,¹¹ where upon lithium deintercalation, a stronger O-O coupling exists, inducing (O-O) π and σ states. However, contrary to the present Ru case, the (O-O) σ^* states of Li_2MnO_3 have no Mn contribution,¹¹ and therefore the additional states did not appear in Mn L-edge spectra of the charged electrodes from previous experimental measurement, where upon charging, the Mn L-edge spectra of $\text{Li}_{2-x}\text{MnO}_3$ did not show significant change.⁶⁷ This suggested that for the Ru-based material, the (O-O) σ^* is

stabilized through π overlap with Ru d -manifolds because of the much more delocalized d states. In contrast, for the Mn scenario, this (O-O) σ^* is not coordinated with any transition metal, and oxygen is released due to more weakened metal oxygen coordination. This observation suggests that strongly covalent Ru-O bonds is critical to enable lattice oxygen-oxygen coupling.^{11, 41}

Moreover, the broadening observed in the O K-edge XES spectra cannot be explained by the creation of oxygen vacancies in the structure as shown by the simulated O K-XES spectra of $\text{Li}_{2-x}\text{RuO}_{3-\delta}$ ($\delta=1/4$) in Figure 3(c) and Figure S6, where only a small shift of the nonbonding peak towards lower energy was observed, whereas in the experimental spectra a positive shift was observed for $\text{Li}_{2-x}\text{RuO}_{3-\delta}$ upon charging. In addition, such broadening also cannot come from the formation of true peroxo- or superoxo- species with O-O bond length less than 1.8 Å. Simulated XES spectra of Li_0RuO_3 with equilibrium O-O bond distance of 2.4 Å and shortened distance of 1.8 Å and 1.2 Å in Figure S9(b) reveal distinctive new peak features in the simulated XES spectra for the 1.2 Å case, potentially coming from fingerprints of σ, π, π^* of the O-O bonding, which were clearly not observed experimentally in this case. Our experimental and simulated XAS and XES revealed unambiguous electronic structure signatures for lattice oxygen redox in form of oxygen-oxygen coupling upon first charge of $\text{Li}_{2-x}\text{RuO}_3$ on the 4.2 V_{Li} plateau, which include 1) the growth of the e_g peak shoulder in the O K-edge and Ru L_3 -edge XAS spectra originated from the (O-O) σ^* -like states with π overlap with Ru d -manifolds and 2) the broadening of non-bonding oxygen originated from the (O-O) σ^* states (without Ru d hybridization). Simulated XAS data further revealed that such O-O coupling in $\text{Li}_{2-x}\text{RuO}_3$ has an oxygen-oxygen distance not smaller than 1.8 Å, namely much longer than those in true molecular

oxygen dimers, peroxide and superoxide, which is in agreement with previous proposal by Doublet *et al.*⁴¹ that the fully de-coordinated oxygen couples can escape from the lattice.

XAS Spectroscopy evidence of reductive coupling in $\text{Li}_{2-x}\text{RuO}_3$

We further examined the electronic structure signature for the reductive coupling in $\text{Li}_{2-x}\text{RuO}_3$,^{11, 39, 41} in which the reduction of Ru is accompanied by the oxidation of lattice oxygen (or lattice oxygen-oxygen coupling) in the 4.2 V_{Li} plateau. Upon charging $\text{Li}_{2-x}\text{RuO}_3$ to 3.8 V_{Li} , the ratio of the integrated peak intensities between the t_{2g} and e_g features, in both Ru L₃-edge and O K-edge XAS spectra (Figure 4(a)), indicated electron removal from the t_{2g} states upon oxidation of Ru. This assignment is supported by simulated Ru L₃-edge (Figure 2(b)) and O K-edge XAS spectra (Figure S4) of $\text{Li}_{2-x}\text{RuO}_3$ obtained from BSE calculations, which show the increase of the low-energy t_{2g} peak relative to the high-energy e_g peak with de-intercalation of one lithium per formula unit from Li_2RuO_3 to LiRuO_3 . Ru oxidation within the 3.8 V_{Li} plateau is further evidenced by positive shifts in the edge photon energy of the Ru L₃-edge (Figure 4(b)) and Ru K-edge XAS (Figure S14), greater energy splitting between t_{2g} and e_g features in Ru L₃-edge XAS (Figure 4(b)) coming from larger ligand fields associated with higher oxidation states⁵⁴⁻⁵⁶, and shortened Ru-O bonds obtained from the extended X-ray absorption fine structure (EXAFS) analysis of the Ru K edge in Figure 4(c), matching with previous observations from Mori *et al.*⁵⁸ Upon further charging within the 4.2 V_{Li} plateau, the ratio of integrated peak intensities of t_{2g} to e_g features in both Ru L₃-edge and O K-edge XAS spectra began to decrease (Figure 4(a)), accompanied by negative shifts in the onset energy of the Ru L₃ edge (Figure 4(b)) and K edge (Figure S14), as well as a smaller energy splitting between t_{2g} and e_g features in Ru L-edge XAS (Figure 4(b)), indicative of Ru reduction. The trend observed in the Ru L₃-

edge shift (Figure 4(b)) is consistent with other metrics to estimate Ru oxidation states used in previous work⁶⁸. For example, the centroid and the pre-peak position of Ru L₃-edge shifted towards higher photon energies during charging up to 3.8 V_{Li}, and towards lower energies at 4.2 V_{Li} and above (Figure S17). Such trend of energy splitting between t_{2g} and e_g is also evidenced from the computed Ru L₃-edge XAS spectra (Figure 2(a)) where as we remove the first Li⁺, the crystal field splitting increases slightly, and then decreases after removing the second Li⁺ per formula unit. Therefore, experimental Ru L₃- and O K-edge XAS data of Li_{2-x}RuO₃ during the first charge along with simulated XAS spectra support the simultaneous Ru reduction and oxygen-oxygen coupling in the 4.2 V_{Li} plateau reported previously as reductive coupling.^{11, 39-40, 43} Similarly, slight reduction of Ir has been reported by Hong *et al.*⁴⁷ using Ir L-edge XAS, accompanied by proposed lattice oxygen oxidation in fully de-intercalated Sn-substituted Li_xIr_ySn_{1-y}O₃ (x = 0, y = 0.5 and 0.75).⁴⁷ While the Ru oxidation state reduction in the 4.2 V_{Li} plateau did not yield a statistically significant increase in the Ru-O bond length from Ru K-edge EXAFS (Figure 4(d)), the Debye-Waller factor (σ_{Ru-O}^2) associated with the Ru-O bond was increased markedly at 4.2 V_{Li} and above, indicating increased variances of Ru-O bond length and angles as well as a distorted Ru-O cage, which requires further study.

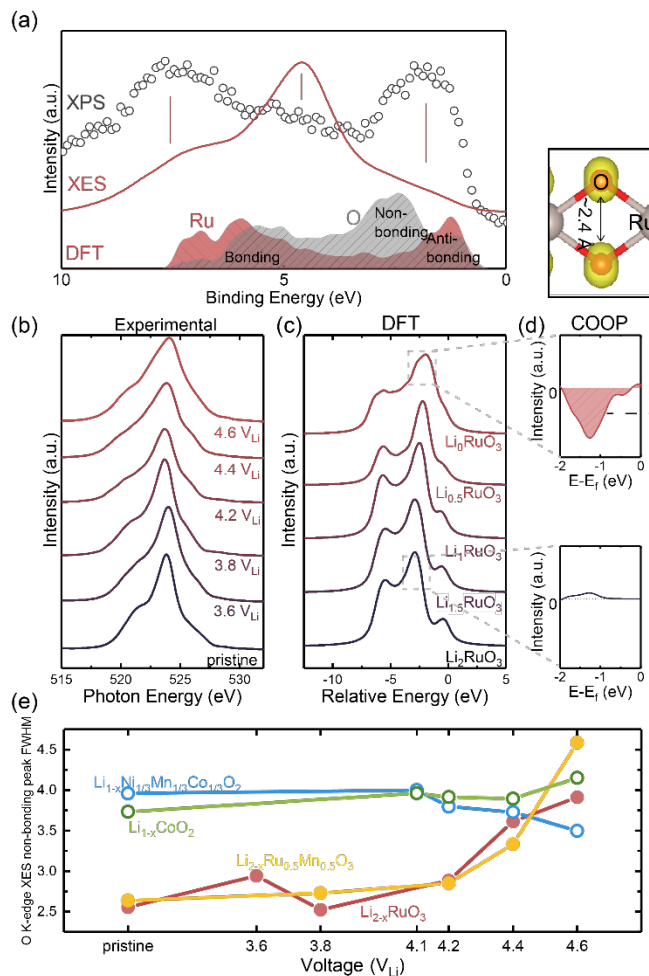


Figure 3: (a) Alignment of the O K-edge XES to XPS valence band measurement on the binding energy scale and comparison of ground-state DFT projected orbital-wise density of state calculation for Ru 4d and O 2p. In the XES spectra the three features can be assigned to bonding, non-bonding, anti-bonding oxygen states from low to high photon energy, respectively. (b) O K-edge XES of Li_{2-x}RuO₃ as a function of state of charge. (c) Simulated O K-edge XES of Li_{2-x}RuO₃ as a function of lithium content, where peak broadening was noted for Li_{0.5}RuO₃ and Li₀RuO₃. (d) Crystal orbital overlap population (COOP) of Li_{2-x}RuO₃ (bottom x = 0 and top x = 2), where, upon delithiation, Li₀RuO₃ showed a stronger O-O σ^* feature around the non-bonding region in the experimental and computed spectra compared to the fully-lithiated case of Li₂RuO₃. (e) Non-bonding peak full width at half maximum (FWHM) as a function of charging potential of different positive electrode materials: LiCoO₂ (LCO), LiNi_{1/3}Mn_{1/3}Co_{1/3}O₂ (NMC), Li₂RuO₃ (LRO) and Li₂Ru_{0.5}Mn_{0.5}O₃ (LRMO). The materials claimed to have anionic redox (closed symbol) were observed to have significant peak broadening upon charging in contrast with LCO and NMC (open symbol), which utilize predominantly cationic redox activity upon oxidation. Here, the FWHM was extracted based on the width at the half height of the most predominant peak (non-bonding peak) as the other shoulder peaks are much smaller than non-bonding peak, thus we assume that the shoulder peaks evolution will not have significant effect on the FWHM of the center non-bonding peak, the FWHM extraction

procedure is also shown schematically in Figure S10. The ground-state projected DOS of the fully lithiated and delithiated $\text{Li}_{2-x}\text{RuO}_3$ is shown in Figure S11 (a) and (b), respectively, and the COOP analysis of full energy range of Li_2RuO_3 and Li_0RuO_3 is shown in Figure S11(c). Raw XES data of LCO, NMC and LRMO is shown in Figure S12 and more detailed analysis is shown in Figure S13.

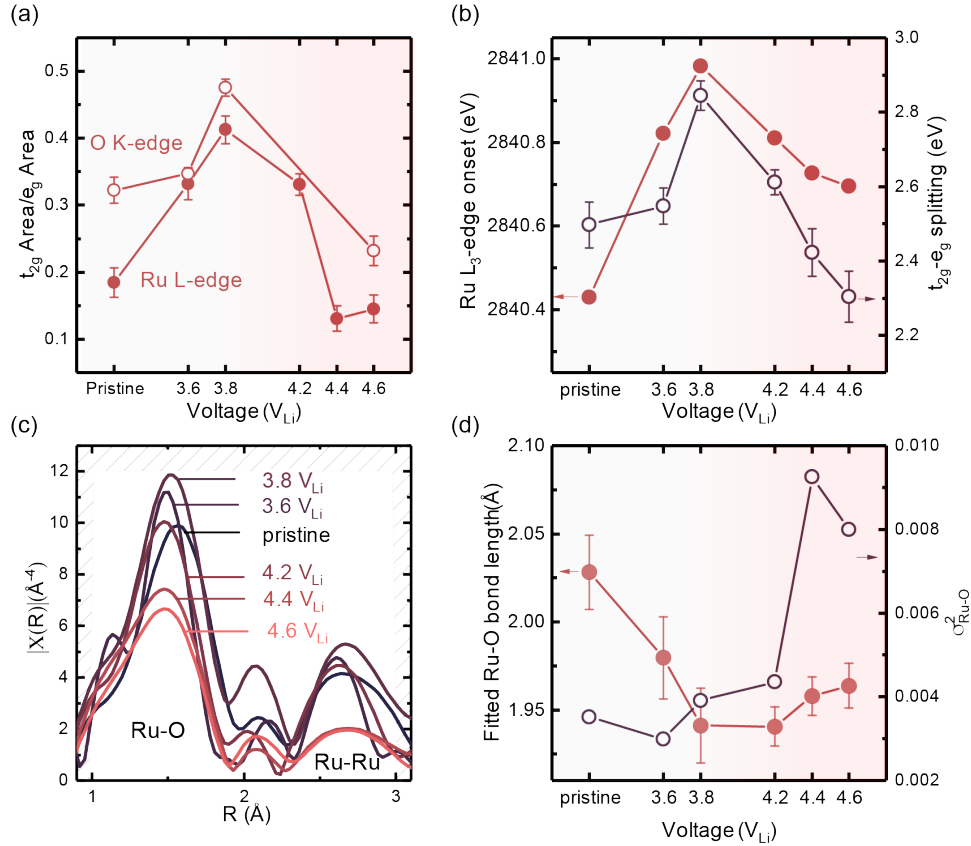


Figure 4 (a) Ratio of integrated peak area of the t_{2g} peak (feature a in Figure 1) and e_g peak (feature b in Figure 1) of O K-edge (open circle) and Ru L-edge (closed circle) from XAS spectra. Detailed fitting results are shown in Figure S1-S3. (b) Ru L-edge edge shift (closed circle) and t_{2g} (feature a in Figure 1) and e_g (feature b in Figure 1) features splitting (open circle). (c) Raw EXAFS data, Fourier-transformed $\chi(R)$ as a function of R (reduced distance) of $\text{Li}_{2-x}\text{RuO}_3$ in the first charge as a function of state of charge including 3.6 V_{Li}, 3.8 V_{Li}, 4.2 V_{Li}, 4.4 V_{Li}, and 4.6 V_{Li}, showing two major features, one centered around 1.5 $\text{\AA}$ (reduced distance), representing Ru-O interaction, and another centered around 2.6 $\text{\AA}$ (reduced distance), representing Ru-Ru interaction. The k -range for Fourier transformation is 1 $\text{\AA}^{-1}$ to 11 $\text{\AA}^{-1}$. (d) Fitted Ru-O bond length (closed circle) and Debye-Waller factor ($\sigma_{\text{Ru-O}}^2$) from Ru K-edge EXAFS shown in Figure 2(c). In the first plateau, Ru is monotonically oxidized with increasing t_{2g} and e_g splitting, accompanied by Ru-O bond contraction. Upon charging to 4.2 V_{Li}, Ru metal is slightly reduced with less t_{2g} and e_g splitting, and there is an increase in the Ru-O bond length and disorder in the system. The raw EXAFS data in k -space and fitting results are shown in Figure S15 and S16, and the summary of the EXAFS fitting parameter is shown in Table S1. Summary of alternative EXAFS fitting parameter by only using the first coordination shell is shown in Table S2.

The XAS spectral evidence of reductive coupling at the 4.2 V_{Li} plateau during the first charge was diminished in subsequent cycles. The voltage profile of Li_{2-x}RuO₃ in the subsequent charges was also markedly different from the first cycle. In fact, the first charge distinct voltage plateaus at 3.8 V_{Li} and 4.2 V_{Li} were replaced by a sloppy voltage profile with an average potential of around 3.6 V_{Li} in subsequent cycles, as shown in Figure 5(a). During the third charge, the Ru L₃-edge onset energy was found to increase monotonically with increasing lithium de-intercalation. This is in contrast to behavior during the first charge with first an increase and then a decrease in the edge onset energy (Figure 5(a) and Figure 4(b)), characteristic of reductive coupling (reduction of Ru) with an enhanced oxygen-oxygen interaction. This observation suggests that reductive coupling, and potentially oxygen-oxygen coupling, is substantially diminished in subsequent cycles, and Ru redox was largely responsible for reversible capacities. This postulate is supported by a much lower photon energy onset at comparable lithium content in Li_{2-x}RuO₃ in the third charge (Figure 5(a) bottom panel) compared to the first charge (Figure 5(a) top panel). Further support comes from the DEMS in Figure 5(b), where an irreversible oxygen redox (oxygen oxidation) generated oxygen in the first charge at around 4.2 V_{Li}, but in subsequent cycles oxygen evolution fell below the detection limit. The amount of oxygen evolution can only be translated to a molar oxygen deficiency fraction of 2 %. From the DEMS measurement, we can also capture the first onset of CO₂ evolution at ≈ 3.9 V_{Li}, potentially due to residual Li₂CO₃ from the synthesis precursor.⁶⁹⁻⁷⁰ Upon charging to 4.2 V_{Li}, lattice oxygen redox was accompanied by pronounced electrolyte oxidation to generate CO₂ evolution (2.0 % mole fraction), which was also reduced considerably in subsequent cycles.

Previous online electrochemistry mass spectrometry (OEMS)^{4, 71} on NMC and Li-rich NMC has attributed part of the CO₂ evolution to singlet oxygen evolved from electrolyte decomposition at the cathode surface. Even by attributing all the CO₂ evolution to the oxide lattice (although this is unlikely), we would only create around 0.4 mol of oxygen vacancies (0.8 mol of electron transfer) per formula unit of oxide during the 4.2 V_{Li} plateau. Accounting for the charge associated with the simultaneous Li-removal in this stage (≈ 0.8 mol Li⁺ and e⁻), oxygen and CO₂ evolution alone cannot explain the reduction of transition metal within the high-voltage plateau observed in Ru L₃- and O K-edge XAS in Figure 4 (a) and (b), and Figure 5(a) in the first charge. As a result, during the first cycle, the redox process proceeded with Ru^{4+/5+} accompanied by oxygen-oxygen coupling and transition metal reduction, whereas in subsequent cycles the high reversibility of Li_{2-x}RuO₃ most likely relied heavily on reversible Ru redox of Ru^{3.x+/5+} (where x is closer to 1 than 0), which surprisingly resembles the trends found in 3d transition metal systems in both Li-rich and Na-ion compounds^{37, 48}

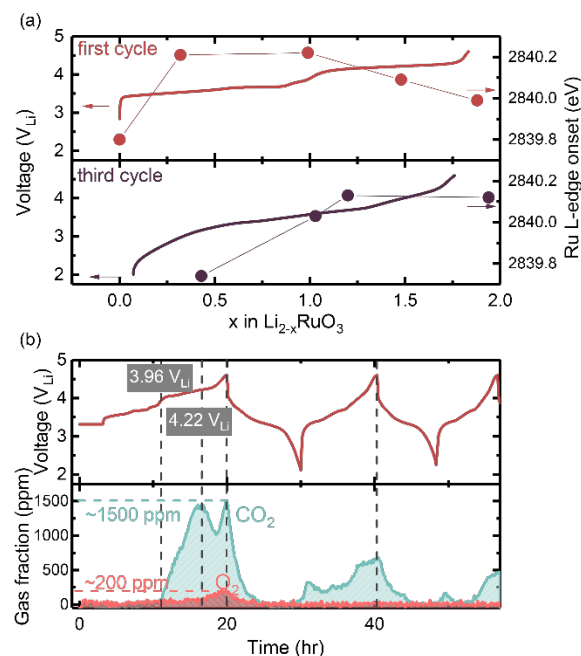


Figure 5: (a) Voltage profiles of Li_2RuO_3 composite electrodes during the first (dark red) and third (purple) charge cycle with current density of 16.35 mA per gram of fully lithiated oxide (g_{oxides}) or 0.088 mA per cm^2 of the electrode cross-section (cm_{geo}^2), and the Ru-L₃ HERFD XAS edge onset of the corresponding composite electrodes as a function of lithium content indicated in filled circle (Figure S18). The lithium content was calculated based on the current applied and time of charge/discharge process and the charge transferred during the 5 h potential holding at the end-of-charge, which can be translate to how many lithium ions per formula unit (de-)intercalate upon cycling. (b) Differential electrochemistry mass spectrometry (DEMS) of Li_2RuO_3 during the first three cycles, where on the top panel is the voltage profile with a current density of 16.35 mA/ g_{oxides} (0.049 mA/ cm_{geo}^2) and the bottom panel is the CO_2 and O_2 evolution as a function of time during the first three cycles.

Implications in oxygen redox reported for other oxides

The electronic structure signature of oxygen-oxygen coupling associated with lattice oxygen oxidation in $\text{Li}_{2-x}\text{RuO}_3$ revealed that non-bonding oxygen is primarily being oxidized,⁴⁵ giving rise to characteristic features in the O K-edge and Ru L₃-edge XAS as well as to the O K-edge XES. The oxidized non-bonding species can be formed through oxygen sublattice distortion which also has a transition metal (Ru) coordination, where this

intermediate O-O dimer-like species can be stabilized through metal oxygen covalency,^{11, 40} in contrast with Mn-based oxides exhibiting anionic redox.^{47, 67} The electronic fingerprints and the physical origin proposed in this work can be applied to explain spectroscopic data of Li-excess materials reported previously. For charged $\text{Li}_x\text{Ir}_y\text{Sn}_{1-y}\text{O}_3$, the appearance of an additional spectral feature, *i.e.* at ≈ 523 eV in O K-edge XES and at ≈ 531 eV in O K-edge XAS, as well as the broadening of the e_g feature (≈ 531 eV) for charged Li_2IrO_3 have been previously attributed to oxygen redox without any specific electronic structure details. Similarly, for Li_2MnO_3 and its derivative materials including Li-rich Mn-rich NMC, researchers have observed similar increased intensities at the high-energy peak of ≈ 531 eV of O K-edge^{36, 38}. This peak has been proposed to be the fingerprint of oxygen redox, but no specific physical origin has been assigned to it. Based on this work, this feature can be assigned to the π/σ states of (O-O) bonding from enhanced oxygen coupling, providing electronic structure details for oxygen redox. While spectral changes of Ir L-edge XAS and O K-edge XAS spectra of $\text{Li}_x\text{Ir}_y\text{Sn}_{1-y}\text{O}_3$ are expected to be similar to those of Ru found in this work (Figure 1), previous Ir L-edge measurements^{47, 72} suffered from significant peak broadening due to the much shorter core-hole lifetime of Ir⁷³ and failed to detect any spectroscopic changes. High-energy resolution L-edge XAS is critical to follow any changes in such $4d$ and $5d$ transition metal oxides. Importantly, in Li_2MnO_3 ⁶⁷ and Li-rich Mn-rich NMC³⁸, even though similar changes have been observed in O K-edge spectra, no simultaneous broadening or additional peak is reported in the Mn L-edge upon charging,⁶⁷ which suggest that this (O-O) peroxo-like state did not have any metallic contribution, and therefore is more prone to oxygen evolution compared to metal-hybridized peroxo-like species as in Li_2RuO_3 . Similarly, an emerging peak at ≈ 531 eV was

observed in the O K-edge XAS of charged $\text{Li}_{1.2}\text{Ti}_{0.4}\text{M}_{0.4}\text{O}_2$ ($M = \text{Fe}, \text{Mn}$)⁷⁴ and $\text{Li}_{1.3}\text{Nb}_{0.3}\text{M}_{0.4}\text{O}_2$ ($M = \text{Fe}, \text{Mn}$)⁷⁵, while minimal differences were noted for transition metal L edges,⁷⁴⁻⁷⁵ indicating the (O-O) coupled states in these compounds are not hybridized with the transition metal, resulting in lower capacity retention compared to Ru and Ir-based materials.

The observed electronic structure fingerprints for oxygen redox in Li_2RuO_3 and implications are discussed with respect to different proposed mechanisms for oxygen redox in the literature. The finding on oxidation of non-bonding oxygen can be related to the DFT studies of oxygen redox in Li_2MnO_3 , $\text{Li}_2\text{Ru}_{0.5}\text{Sn}_{0.5}\text{O}_3$ and Li-excess disordered rocksalt reported by Seo and Ceder,⁴⁵ where the oxidation of non-bonding oxygen (the oxygen bound to Li) was proposed. However, similar to what Tarascon, Doublet and coworkers claim,^{11,40} we argue that the strong hybridization between Ru and O_2^{n-} is critical to stabilize the oxidized oxygen species otherwise oxygen-oxygen coupling would form molecular oxygen, causing capacity loss (irreversible oxygen redox). In addition, transition metal migration can create under-coordinated oxygen, which can facilitate the coupling between transition metal migration and oxygen redox in Li-rich Mn-rich NMC ($\text{Li}_{1.2}\text{Mn}_{0.54}\text{Ni}_{0.13}\text{Co}_{0.13}\text{O}_2$) observed by Gent and Chueh.³⁸ Nevertheless, such oxygen, without transition metal coordination, is prone to be released and would not contribute to capacities in later cycles, as shown by hard XAS data from Hu *et al.*³⁷, where the capacity contribution from oxygen redox of such materials is diminished to 50 mAh/g in the 83rd cycle compared to 120 mAh/g in the first cycle.³⁷ Moreover, we show that in such covalent oxides with a 4d transition metal, even though stable (O-O) coupling can be formed in the

first charge, the capacity attributed to oxygen redox can be overwhelmed by a more significant contribution from cation redox in subsequent cycles.

3. Conclusions

In this work, by combining O K-edge XAS, Ru L₃-edge HERFD-XAS and O K-edge XES spectroscopy with *ab-initio* theoretically calculated spectra, we have captured and rationalized electronic structure fingerprints that reveal an enhanced O-O coupling in Li_{2-x}RuO₃ in the 4.2 V_{Li} plateau during the first charge after removing $\approx 50\%$ of the lithium. This observation provides direct evidence central to lattice oxygen redox ($\text{O}^{2-}/(\text{O}_2)^{n-}$) in charged Li_{2-x}RuO₃ after Ru oxidation (Ru⁴⁺/Ru⁵⁺). Such oxygen-oxygen coupling (lattice oxygen redox) of Li_{2-x}RuO₃ was also accompanied with simultaneous Ru reduction that cannot be solely explained by oxygen vacancy formation in the oxides at high potentials. Upon the first charge, the lattice oxygen redox is accompanied by a small amount of O₂ evolution in the first charge (captured by DEMS), which is diminished in subsequent cycles. This observation is in agreement with the changes in Ru L₃-edge HERFD-XAS. Ru was found to be in a more reduced state in later cycles despite similar lithium content, indicating that the Ru redox contributed more to discharge capacities in later cycles than in the first cycle. This study has provided theoretical insights on previously reported spectroscopic features in resonant inelastic X-ray scattering spectroscopy and O K-edge XAS across different materials families exhibiting anionic redox. This work highlights the importance of combining with the state-of-the-art core-level measurements and *ab-initio* excited-state Bethe-Salpeter equation calculations in order to interpret the spectroscopic features. The presented approach can be used as a transferable framework to monitor the spectroscopy

changes of metal oxides undergoing redox/electrochemical reactions for Li-ion and electrocatalysis applications.

4. Methods

Experimental methods

Solid-state synthesis The pristine Li_2RuO_3 was synthesized through the solid-state route previously undertaken by Goodenough et al.⁷⁶ and Tarascon et al.⁴⁰ Li_2CO_3 and RuO_2 precursors are first dried under air flow at 300 °C for 4 h. The precursors were then mixed in stoichiometric amounts, but with a Li excess of 10 %, with a mortar and a pestle for 1 h in a argon-filled glovebox (H_2O , $\text{O}_2 < 0.1\text{ppm}$). The resultant powder was pelletized under 1 MPa and calcined and sintered at 1000 °C and 900°C under air with heating rate of 2 °C/min for 24 h and 48 h, respectively, with intermediate grinding. The phase purity of Li_2RuO_3 is confirmed through X-ray diffraction (XRD) with PANalyt'cal X'Pert PRO (Figure S19).

Positive electrode preparation The pellet electrode was prepared by pelletizing around 48 mg of active material using 6 mm diameter pressing die set (Across International) for 15 mins. The pellets were then sintered under air at 900 °C for 6 hours. The cooling and heating rates were 2 °C/min. The pellet electrodes were then broken into pieces of around 3 mg each and dried in vacuum under 120 °C overnight before being transferred into an Argon-filled glovebox ($<0.5\text{ ppm}$ of H_2O and O_2). The pellet electrodes were used for the X-ray measurements to remove any ambiguities introduced by conductive carbon and binder.

Composite electrodes were prepared by mixing active material (80 % mass fraction), 10 % acetylene black (AB) and 10 % polyvinylidene fluoride (PVDF) (Kynar) dispersed in N-Methyl-2-pyrrolidone (NMP) with Fritsch Minimill 23 homogenizer. The slurry was then blade-coated onto an aluminum sheet with a gap of 5 μm . The composite electrodes were punched into 1.27 cm disc and pressed at $5.7 \times 10^4 \text{ kg/cm}^2$ under a hydraulic press, to embed the powder into the aluminum disc. Finally, the electrodes were completely dried at 120 °C under vacuum for 12 h before being transferred into Argon-filled glovebox (<0.5 ppm of H_2O and O_2). The active loading of the composite electrodes for the cycling experiments is around 3 mg/cm^2 . Composite electrodes for DEMS experiments were prepared with a slurry dispersed in less NMP to make a more viscous slurry. The resultant slurry was then blade-coated onto a stainless steel 304 mesh with an opening of 20 μm with a wire diameter of 0.2 mm with an aluminum sheet underneath, and with a gap of 15 μm . The electrodes were then dried and separated from the aluminum sheet underneath and punched into 15 mm diameter discs. The DEMS electrodes were pressed at $4.11 \times 10^4 \text{ kg/cm}^2$ under a hydraulic press. Finally, the electrodes were completely dried at 120 °C under vacuum for 12 h before being transferred into an Argon-filled glovebox (<0.5 ppm of H_2O and O_2). The active loading of the composite electrodes for the DEMS experiments was around 5.27 mg/cm^2 , which is higher than the loading of composite electrodes for XAS measurements to ensure that enough gaseous species were evolved to be detected during cycling.

Electrochemical measurements Electrochemical behavior of the pellet electrodes was confirmed by galvanostatic measurements in two-electrode cells (Tomcell type TJ-AC). Cells were assembled in an argon-filled glovebox (<0.5 ppm of H_2O and O_2) and comprised a lithium metal foil as the negative electrode and the positive electrode, separated by two

pieces of polypropylene separator (2500 Celgard), impregnated with 150 μL of LP57 (1M LiPF_6 in a 3:7 ethylene carbonate (EC): ethylmethyl carbonate (EMC) electrolyte (BASF)). After assembly, the cells rested for 6 h prior to measurement and then were charged with different end-of-charge potentials (3.6 V_{Li} , 3.8 V_{Li} , 4.2 V_{Li} , 4.4 V_{Li} , and 4.6 V_{Li}) at a rate of $\approx 1.64 \text{ mA/g}$. This rate of charge corresponds to a rate of C/100 based on the theoretical capacity calculated assuming one lithium extraction per Li_2RuO_3 . The cell was held at the end-of-charge potential for 5 h before disassembly inside the glovebox. The composite electrode was charged in a two-electrode coin cell (Hohsen CR2016) with Li metal foil as the negative electrode. The positive and negative electrodes were separated by two pieces of polypropylene separator (2500 Celgard), impregnated with 100 μL of LP57. The coin cells were charged at a rate of C/10 (16.35 mA/g) with different end-of-charge potential (first cycle: 3.6 V_{Li} , 3.8 V_{Li} , 4.2 V_{Li} and 4.6 V_{Li} , third cycle: 3 V_{Li} , 3.4 V_{Li} , 4 V_{Li} , and 4.6 V_{Li}). The cells were held at the end-of-charge potential for 5 h before being disassembled inside the glovebox. The collected pellets and composite electrodes were rinsed in 1 mL EMC solution with stirring for 24 h to remove the residual electrolyte and electrolyte decomposition products on the surface. The pellets and composite electrodes were then dried in vacuum for 4 h before further characterization using XAS and XES.

Differential electrochemistry mass spectrometry measurements The DEMS setup was constructed in-house based on the design reported by McCloskey *et al.*⁷⁷ and used for the detection of gas evolution including CO_2 and O_2 in the head space of the electrochemistry cell along with pressure monitoring. Details on the DEMS setup and cell design are documented in Harding *et al.*⁷⁸ The cell volume is around 6.7 cm^3 for the measurement and Argon (Airgas, 99.999 % pure, O_2 , H_2O , $\text{CO}_2 < 1 \text{ ppm}$) was used as a carrier gas. The

DEMS cells were prepared inside an argon-filled glovebox (<0.5 ppm of H_2O and O_2) and comprised a lithium metal foil as the negative electrode and the DEMS positive electrodes, separated by two pieces of polypropylene separator (2500 Celgard), impregnated with 150 μL of LP57. The cell was first pressurized with argon to around 150 kPa and allowed to rest for 8 h prior to electrochemical measurements to check for any potential leakage. DEMS measurement started 4 h after pressurization with a time interval of 10 min of collecting the gas from the headspace to obtain a CO_2 evolution background from evaporated EMC fragments. The gas evolution profile upon charge/discharge as a function of time presented in this work were already background subtracted by fitting the gas evolution profile collected in the open circuit voltage stage after pressurizing with a polynomial function. The electrochemical measurements were carried out at a current density of 16.35 mA/g (0.088 mA/cm²) for charge and discharge (corresponding to a C/10 rate), and a time interval of 10 min was set between each DEMS sequence.

Synchrotron measurements After rinsing and drying, the dried pellet electrodes were mixed with sucrose or BN powder to make 10 mm pellets. The pellets were wrapped around with Kapton tape for protection during transportation for hard X-ray absorption measurements.

High-energy resolution fluorescence detected Ru L₃-edge XAS was conducted at the Stanford Synchrotron Radiation Lightsource (SSRL) at SLAC National Accelerator Laboratory. The measurements were performed with a high-resolution tender x-ray spectrometer developed on a dispersive Johansson geometry in a 500 mm Rowland circle using a Si(111) analyzer.⁷⁹ The spectrometer recorded in dispersive mode the overall Ru L α emission line; for extracting the HERFD spectrum, the peak intensity of the L α emission

line is plotted as a function of the incident photon energy. By using the Si(111) monochromator of SSRL beamline 6-2, an overall energy resolution of 0.6 eV was achieved enabling the sharpening of the Ru-L₃ XAS features when compared to conventional x-ray absorption spectroscopy, *i.e.*, total fluorescence yield or transmission mode XAS (comparison shown in Figure S20). The incident beam was about 400 μm x 800 μm (FWHM) and the photon flux $\approx 10^{12} \text{ sec}^{-1}$. The dried electrode material was mixed with sucrose to minimize any self-absorption effects across the very intense Ru L₃-edge resonances, resulting in pressed pellets with an active material mass fraction concentration of 0.5 %.

Ruthenium K-edge EXAFS was conducted at beamline 20-BM-B of the Advanced Photon Source (APS) at Argonne National Laboratory in transmission mode with an active materials mass fraction of 10 %, diluted with boron nitride. A Ru metal foil was used as reference. O K-edge XAS and XES were conducted at the Advanced Light Source (ALS) on beamline 8.0.2. All spectroscopy data were normalized and processed using the ATHENA software package.⁸⁰

Computational Methods

DFT calculations We used the Perdew-Burke-Ernzerhof (PBE)⁸¹ formulation of the density functional and projected augmented wave (PAW) potentials implemented in Vienna Ab-initio Simulation Package (VASP)⁸²⁻⁸⁴, with Dudarev’s rotationally invariant Hubbard-type U^{85} applied on the transition metal where we applied a $U_{\text{eff}} = 4 \text{ eV}$ on Ru 4*d* orbital as reported from previous work.^{11, 45} A k-point per reciprocal atom of 8000 was used. The delithiated structures were generated with a primitive cell with 4 formula unit of Li₂RuO₃, where for each different lithium content, the most energetically favorable configuration

was taken. The voltage profile calculated using the energetics from the delithiated structures is shown in Figure S5, where the computed voltage profile matched relatively well with experimental charging curve. However, we should note that to compute the true ground-state at each lithium content along the convex hull, a cluster expansion approach should be employed.⁸⁶ The surface calculations in Figure S7(d) was conducted with VASP using a stoichiometric slab model with slab thickness of 5 Å and a vacuum thickness of 10 Å to avoid any spurious interactions across the periodic boundary. For simplicity, a surface orientation of (001) was chosen for the test, and a k-point grid of $7 \times 7 \times 1$ was used. We fully relaxed the surface structure before the OCEAN calculations.

The XAS and XES simulations were performed with the OCEAN 2.5.2 code^{50 51}, which combines ground-state density-functional theory and the Bethe-Salpeter equation (BSE) to account for the core-hole presence and to properly capture the spin-orbit interactions of transition metals. The ground-state charge density and wave functions used in the core-hole screening and BSE calculations were obtained using Quantum Espresso.⁸⁷ Norm-conserving pseudopotentials from the ABINIT⁸⁸ distribution were used. The k-point grid used to solve the Kohn-Sham states was typically $6 \times 6 \times 3$ for the pristine Li_2RuO_3 (24 atom cell). Similar values were used for all structures. The screening calculations used a $2 \times 2 \times 2$ k-point grid. The number of unoccupied bands used for the BSE calculation was 250, and the screened core-hole potential calculation included 750 bands. A spectral broadening of 0.5 eV was applied and dipole and quadrupole transitions were considered. To enable easy spectroscopic feature comparison, the core-level shift was not turned on for the OCEAN calculations. Given the polycrystalline type of our samples, all simulated spectra were obtained by averaging the contribution from all photon polarizations.

Supporting Information

The Supporting Information is available free of charge on the ACS Publications website at DOI: XXXX

Supplementary XRD spectra, electrochemical data, and additional analysis and *ab-initio* calculations of O K-edge, Ru L₃-edge, and Ru K-edge XAS, O K-edge XES of the charged Li_{2-x}RuO₃ pellets, and the raw data of Ru L₃-edge of charged Li_{2-x}RuO₃ composite electrodes are included in the supporting information. The table of the fitting parameters for Ru K-edge EXAFS and raw data in the k- and R- space are also included in the supporting information.

Conflicts of interest

There are no conflicts to declare.

ACKNOWLEDGMENT

This work made use of the MRSEC Shared Experimental Facilities at MIT, supported by the National Science Foundation under award number DMR-1419807. Research at MIT related to this work was supported financially by BMW. This research used resources of the National Energy Research Scientific Computing Center (NERSC), a DOE Office of Science User Facility supported by the Office of Science of the U.S. Department of Energy under Contract No. DE-AC02-05CH11231. This work also used resources of the Extreme Science and Engineering Discovery Environment (XSEDE)¹¹⁹, which is supported by National Science Foundation grant number ACI-1548562. Use of the Stanford Synchrotron Radiation Lightsource (SSRL), SLAC National Accelerator Laboratory, was supported by the US Department of Energy, Office of Science, Office of Basic Energy Sciences (contract No. DE-AC02-76SF00515). Part of the instrument used for this study was supported by U.S. Department of Energy, Office of Energy Efficiency & Renewable Energy, Solar Energy Technology Office BRIDGE Program. This research used resources of the Advanced Photon Source, an Office of Science User Facility operated for the U.S.

Department of Energy (DOE) Office of Science by Argonne National Laboratory, and was supported by the U.S.DOE under Contract No. DE-AC02-06CH11357, and the Canadian Light Source and its funding partners. This research used resources of the Advanced Light Source, which is a DOE Office of Science User Facility under contract no. DE-AC02-05CH11231. Certain commercial equipment, instruments, or materials are identified in this paper in order to specify the experimental procedure adequately. Such identification is not intended to imply recommendation or endorsement by NIST, nor is it intended to imply that the materials or equipment identified are necessarily the best available for the purpose.

Reference

1. Mizushima, K.; Jones, P.; Wiseman, P.; Goodenough, J. B., Li_xCoO_2 ($0 < x < 1$): A new cathode material for batteries of high energy density. *Materials Research Bulletin* **1980**, *15* (6), 783-789.
2. Amatucci, G.; Tarascon, J.; Klein, L., Cobalt dissolution in LiCoO_2 -based non-aqueous rechargeable batteries. *Solid State Ionics* **1996**, *83* (1-2), 167-173.
3. Broussely, M.; Pertion, F.; Biensan, P.; Bodet, J.; Labat, J.; Lecerf, A.; Delmas, C.; Rougier, A.; Peres, J., Li_xNiO_2 , a promising cathode for rechargeable lithium batteries. *Journal of power sources* **1995**, *54* (1), 109-114.
4. Jung, R.; Metzger, M.; Maglia, F.; Stinner, C.; Gasteiger, H. A., Oxygen Release and Its Effect on the Cycling Stability of $\text{LiNi}_x\text{Mn}_y\text{Co}_z\text{O}_2$ (NMC) Cathode Materials for Li-Ion Batteries. *Journal of The Electrochemical Society* **2017**, *164* (7), A1361-A1377.
5. Koetschau, I.; Richard, M.; Dahn, J.; Soupart, J.; Rousche, J., Orthorhombic LiMnO_2 as a High Capacity Cathode for Li-Ion Cells. *Journal of the Electrochemical Society* **1995**, *142* (9), 2906-2910.
6. Vitins, G.; West, K., Lithium intercalation into layered LiMnO_2 . *Journal of the Electrochemical Society* **1997**, *144* (8), 2587-2592.
7. Goodenough, J. B.; Kim, Y., Challenges for rechargeable Li batteries. *Chemistry of materials* **2009**, *22* (3), 587-603.
8. Grimaud, A.; Hong, W.; Shao-Horn, Y.; Tarascon, J.-M., Anionic redox processes for electrochemical devices. *Nature materials* **2016**, *15* (2), 121.
9. Assat, G.; Tarascon, J.-M., Fundamental understanding and practical challenges of anionic redox activity in Li-ion batteries. *Nature Energy* **2018**, *1*.
10. Li, K.; Xue, D., Estimation of electronegativity values of elements in different valence states. *The Journal of Physical Chemistry A* **2006**, *110* (39), 11332-11337.
11. Saubanère, M.; McCalla, E.; Tarascon, J.-M.; Doublet, M.-L., The intriguing question of anionic redox in high-energy density cathodes for Li-ion batteries. *Energy & Environmental Science* **2016**, *9* (3), 984-991.
12. Ceder, G.; Aydinol, M.; Kohan, A., Application of first-principles calculations to the design of rechargeable Li-batteries. *Computational materials science* **1997**, *8* (1-2), 161-169.

13. Jansen, A.; Kahaian, A.; Kepler, K.; Nelson, P.; Amine, K.; Dees, D.; Vissers, D.; Thackeray, M., Development of a high-power lithium-ion battery. *Journal of power sources* **1999**, *81*, 902-905.
14. Perez, A. J.; Jacquet, Q.; Batuk, D.; Iadecola, A.; Saubanère, M.; Rousse, G.; Larcher, D.; Vezin, H.; Doublet, M.-L.; Tarascon, J.-M., Approaching the limits of cationic and anionic electrochemical activity with the Li-rich layered rocksalt Li_3IrO_4 . *Nature Energy* **2017**, *2* (12), 954.
15. Sathiya, M.; Leriche, J.-B.; Salager, E.; Gourier, D.; Tarascon, J.-M.; Vezin, H., Electron paramagnetic resonance imaging for real-time monitoring of Li-ion batteries. *Nature communications* **2015**, *6*, 6276.
16. Sathiya, M.; Ramesha, K.; Rousse, G.; Foix, D.; Gonbeau, D.; Prakash, A.; Doublet, M.; Hemalatha, K.; Tarascon, J.-M., High Performance $\text{Li}_2\text{Ru}_{1-y}\text{Mn}_y\text{O}_3$ ($0.2 \leq y \leq 0.8$) Cathode Materials for Rechargeable Lithium-Ion Batteries: Their Understanding. *Chemistry of Materials* **2013**, *25* (7), 1121-1131.
17. Armstrong, A. R.; Holzapfel, M.; Novák, P.; Johnson, C. S.; Kang, S.-H.; Thackeray, M. M.; Bruce, P. G., Demonstrating oxygen loss and associated structural reorganization in the lithium battery cathode $\text{Li}[\text{Ni}_0.2\text{Li}_0.2\text{Mn}_0.6]\text{O}_2$. *Journal of the American Chemical Society* **2006**, *128* (26), 8694-8698.
18. Johnson, C.; Kim, J.; Lefief, C.; Li, N.; Vaughey, J.; Thackeray, M., The significance of the Li_2MnO_3 component in 'composite' $\text{xLi}_2\text{MnO}_3 \cdot (1-x)\text{LiMn}_{0.5}\text{Ni}_{0.5}\text{O}_2$ electrodes. *Electrochemistry Communications* **2004**, *6* (10), 1085-1091.
19. Johnson, C. S.; Li, N.; Lefief, C.; Vaughey, J. T.; Thackeray, M. M., Synthesis, Characterization and Electrochemistry of Lithium Battery Electrodes: $\text{xLi}_2\text{MnO}_3 \cdot (1-x)\text{LiMn}_{0.333}\text{Ni}_{0.333}\text{Co}_{0.333}\text{O}_2$ ($0 \leq x \leq 0.7$). *Chemistry of Materials* **2008**, *20* (19), 6095-6106.
20. Kim, S.; Aykol, M.; Hegde, V. I.; Lu, Z.; Kirklin, S.; Croy, J. R.; Thackeray, M. M.; Wolverton, C., Material design of high-capacity Li-rich layered-oxide electrodes: Li_2MnO_3 and beyond. *Energy & Environmental Science* **2017**, *10* (10), 2201-2211.
21. Thackeray, M. M.; Johnson, C. S.; Vaughey, J. T.; Li, N.; Hackney, S. A., Advances in manganese-oxide 'composite' electrodes for lithium-ion batteries. *Journal of Materials Chemistry* **2005**, *15* (23), 2257-2267.
22. Thackeray, M. M.; Wolverton, C.; Isaacs, E. D., Electrical energy storage for transportation—approaching the limits of, and going beyond, lithium-ion batteries. *Energy & Environmental Science* **2012**, *5* (7), 7854-7863.
23. Dong, X.; Xu, Y.; Yan, S.; Mao, S.; Xiong, L.; Sun, X., Towards low-cost, high energy density Li_2MnO_3 cathode materials. *Journal of Materials Chemistry A* **2015**, *3* (2), 670-679.
24. Lee, E.; Blauwkamp, J.; Castro, F. C.; Wu, J.; Dravid, V. P.; Yan, P.; Wang, C.; Kim, S.; Wolverton, C.; Benedek, R., Exploring Lithium-Cobalt-Nickel Oxide Spinel Electrodes for ≥ 3.5 V Li-Ion Cells. *ACS applied materials & interfaces* **2016**, *8* (41), 27720-27729.
25. Croy, J. R.; Park, J. S.; Dogan, F.; Johnson, C. S.; Key, B.; Balasubramanian, M., First-cycle evolution of local structure in electrochemically activated Li_2MnO_3 . *Chemistry of Materials* **2014**, *26* (24), 7091-7098.
26. Croy, J. R.; Balasubramanian, M.; Gallagher, K. G.; Burrell, A. K., Review of the US department of energy's "deep dive" effort to understand voltage fade in Li-and Mn-rich cathodes. *Accounts of chemical research* **2015**, *48* (11), 2813-2821.
27. Croy, J. R.; Iddir, H.; Gallagher, K.; Johnson, C. S.; Benedek, R.; Balasubramanian, M., First-charge instabilities of layered-layered lithium-ion-battery materials. *Physical Chemistry Chemical Physics* **2015**, *17* (37), 24382-24391.
28. Kim, S.; Kim, C.; Jhon, Y.-I.; Noh, J.-K.; Vemuri, S. H.; Smith, R.; Chung, K. Y.; Jhon, M. S.; Cho, B.-W., Synthesis of layered-layered $0.5\text{Li}_2\text{MnO}_3 \cdot 0.5\text{LiCoO}_2$ nanocomposite electrode materials by the mechanochemical process and first principles study. *Journal of Materials Chemistry* **2012**, *22* (48), 25418-25426.
29. Kalyani, P.; Chitra, S.; Mohan, T.; Gopukumar, S., Lithium metal rechargeable cells using Li_2MnO_3 as the positive electrode. *Journal of power sources* **1999**, *80* (1), 103-106.
30. Denis, Y.; Yanagida, K.; Kato, Y.; Nakamura, H., Electrochemical activities in Li_2MnO_3 . *Journal of The Electrochemical Society* **2009**, *156* (6), A417-A424.

31. Kim, S.; Noh, J.-K.; Yu, S.; Chang, W.; Chung, K. Y.; Cho, B.-W., Effects of transition metal doping and surface treatment to improve the electrochemical performance of Li_2MnO_3 . *Journal of Electroceramics* **2013**, *30* (3), 159-165.
32. Robertson, A. D.; Bruce, P. G., Mechanism of electrochemical activity in Li_2MnO_3 . *Chemistry of Materials* **2003**, *15* (10), 1984-1992.
33. Johnson, C. S., Development and utility of manganese oxides as cathodes in lithium batteries. *Journal of Power Sources* **2007**, *165* (2), 559-565.
34. Park, S.; Ahn, H.; Park, G.; Kim, J.; Lee, Y., Cycle mechanism and electrochemical properties of lithium manganese oxide prepared using different Mn sources. *Materials Chemistry and Physics* **2008**, *112* (2), 696-701.
35. Park, S.-H.; Sato, Y.; Kim, J.-K.; Lee, Y.-S., Powder property and electrochemical characterization of Li_2MnO_3 material. *Materials chemistry and physics* **2007**, *102* (2), 225-230.
36. Luo, K.; Roberts, M. R.; Hao, R.; Guerrini, N.; Pickup, D. M.; Liu, Y.-S.; Edström, K.; Guo, J.; Chadwick, A. V.; Duda, L. C., Charge-compensation in 3d-transition-metal-oxide intercalation cathodes through the generation of localized electron holes on oxygen. *Nature chemistry* **2016**, *8* (7), 684.
37. Hu, E.; Yu, X.; Lin, R.; Bi, X.; Lu, J.; Bak, S.; Nam, K.-W.; Xin, H. L.; Jaye, C.; Fischer, D. A., Evolution of redox couples in Li-and Mn-rich cathode materials and mitigation of voltage fade by reducing oxygen release. *Nature Energy* **2018**, *3* (8), 690.
38. Gent, W. E.; Lim, K.; Liang, Y.; Li, Q.; Barnes, T.; Ahn, S.-J.; Stone, K. H.; McIntire, M.; Hong, J.; Song, J. H., Coupling between oxygen redox and cation migration explains unusual electrochemistry in lithium-rich layered oxides. *Nature communications* **2017**, *8* (1), 2091.
39. Sathiya, M.; Abakumov, A. M.; Foix, D.; Rousse, G.; Ramesha, K.; Saubanère, M.; Doublet, M.; Vezin, H.; Laisa, C.; Prakash, A., Origin of voltage decay in high-capacity layered oxide electrodes. *Nature materials* **2015**, *14* (2), 230-238.
40. Sathiya, M.; Rousse, G.; Ramesha, K.; Laisa, C.; Vezin, H.; Sougrati, M. T.; Doublet, M.-L.; Foix, D.; Gonbeau, D.; Walker, W., Reversible anionic redox chemistry in high-capacity layered-oxide electrodes. *Nature materials* **2013**, *12* (9), 827-835.
41. Xie, Y.; Saubanere, M.; Doublet, M.-L., Requirements for reversible extra-capacity in Li-rich layered oxides for Li-ion batteries. *Energy & Environmental Science* **2017**, *10* (1), 266-274.
42. Pearce, P. E.; Perez, A. J.; Rousse, G.; Saubanère, M.; Batuk, D.; Foix, D.; McCalla, E.; Abakumov, A. M.; Van Tendeloo, G.; Doublet, M.-L., Evidence for anionic redox activity in a tridimensional-ordered Li-rich positive electrode $\beta\text{-Li}_2\text{IrO}_3$. *Nature materials* **2017**, *16* (5), 580.
43. McCalla, E.; Abakumov, A. M.; Saubanère, M.; Foix, D.; Berg, E. J.; Rousse, G.; Doublet, M.-L.; Gonbeau, D.; Novák, P.; Van Tendeloo, G., Visualization of OO peroxo-like dimers in high-capacity layered oxides for Li-ion batteries. *Science* **2015**, *350* (6267), 1516-1521.
44. Matthew, J., Surface analysis by Auger and x-ray photoelectron spectroscopy. D. Briggs and JT Grant (eds). IMPublications, Chichester, UK and SurfaceSpectra, Manchester, UK, 2003. 900 pp., ISBN 1-901019-04-7, 900 pp. *Surface and Interface Analysis: An International Journal devoted to the development and application of techniques for the analysis of surfaces, interfaces and thin films* **2004**, *36* (13), 1647-1647.
45. Seo, D.-H.; Lee, J.; Urban, A.; Malik, R.; Kang, S.; Ceder, G., The structural and chemical origin of the oxygen redox activity in layered and cation-disordered Li-excess cathode materials. *Nature chemistry* **2016**, *8* (7), 692-697.
46. Zhan, C.; Yao, Z.; Lu, J.; Ma, L.; Maroni, V. A.; Li, L.; Lee, E.; Alp, E. E.; Wu, T.; Wen, J., Enabling the high capacity of lithium-rich anti-fluorite lithium iron oxide by simultaneous anionic and cationic redox. *Nature Energy* **2017**, *2* (12), 963.
47. Hong, J.; Gent, W. E.; Xiao, P.; Lim, K.; Seo, D.-H.; Wu, J.; Csernica, P. M.; Takacs, C. J.; Nordlund, D.; Sun, C.-J., Metal-oxygen decoordination stabilizes anion redox in Li-rich oxides. *Nature materials* **2019**, *1*.
48. Dai, K.; Wu, J.; Zhuo, Z.; Li, Q.; Sallis, S.; Mao, J.; Ai, G.; Sun, C.; Li, Z.; Gent, W. E.; Chueh, W. C.; Chuang, Y.-d.; Zeng, R.; Shen, Z.-x.; Pan, F.; Yan, S.; Piper, L. F. J.; Hussain, Z.; Liu, G.; Yang,

- W., High Reversibility of Lattice Oxygen Redox Quantified by Direct Bulk Probes of Both Anionic and Cationic Redox Reactions. *Joule* **2019**, 3 (2), 518-541.
49. Zhuo, Z.; Pemmaraju, C. D.; Vinson, J.; Jia, C.; Moritz, B.; Lee, I.; Sallies, S.; Li, Q.; Wu, J.; Dai, K.; Chuang, Y. D.; Hussain, Z.; Pan, F.; Devereaux, T. P.; Yang, W., Spectroscopic Signature of Oxidized Oxygen States in Peroxides. *J Phys Chem Lett* **2018**, 9 (21), 6378-6384.
 50. Gilmore, K.; Vinson, J.; Shirley, E. L.; Prendergast, D.; Pemmaraju, C. D.; Kas, J. J.; Vila, F. D.; Rehr, J. J., Efficient implementation of core-excitation Bethe–Salpeter equation calculations. *Computer Physics Communications* **2015**, 197, 109-117.
 51. Vinson, J.; Rehr, J.; Kas, J.; Shirley, E., Bethe-Salpeter equation calculations of core excitation spectra. *Physical Review B* **2011**, 83 (11), 115106.
 52. Jimenez-Segura, M.-P.; Ikeda, A.; Yonezawa, S.; Maeno, Y., Effect of disorder on the dimer transition of the honeycomb-lattice compound Li_2RuO_3 . *Physical Review B* **2016**, 93 (7), 075133.
 53. Li, B.; Shao, R.; Yan, H.; An, L.; Zhang, B.; Wei, H.; Ma, J.; Xia, D.; Han, X., Lithium-Ion Batteries: Understanding the Stability for Li-Rich Layered Oxide Li_2RuO_3 Cathode (Adv. Funct. Mater. 9/2016). *Advanced Functional Materials* **2016**, 26 (9), 1306-1306.
 54. Sham, T., X-ray absorption spectra of ruthenium L edges in hexaammineruthenium trichloride. *Journal of the American Chemical Society* **1983**, 105 (8), 2269-2273.
 55. Alperovich, I.; Smolentsev, G.; Moonshiram, D.; Jurss, J. W.; Concepcion, J. J.; Meyer, T. J.; Soldatov, A.; Pushkar, Y., Understanding the electronic structure of 4d metal complexes: From molecular spinors to L-edge spectra of a di-Ru catalyst. *Journal of the American Chemical Society* **2011**, 133 (39), 15786-15794.
 56. Cramer, S.; DeGroot, F.; Ma, Y.; Chen, C.; Sette, F.; Kipke, C.; Eichhorn, D.; Chan, M.; Armstrong, W., Ligand field strengths and oxidation states from manganese L-edge spectroscopy. *Journal of the American Chemical Society* **1991**, 113 (21), 7937-7940.
 57. Perez, A. J.; Beer, R.; Lin, Z.; Salager, E.; Taberna, P. L.; Abakumov, A. M.; Simon, P.; Tarascon, J. M., Proton Ion Exchange Reaction in Li_3IrO_4 : A Way to New $\text{H}_3^+ \text{xIrO}_4$ Phases Electrochemically Active in Both Aqueous and Nonaqueous Electrolytes. *Advanced Energy Materials* **2018**, 8 (13), 1702855.
 58. Mori, D.; Kobayashi, H.; Okumura, T.; Nitani, H.; Ogawa, M.; Inaguma, Y., XRD and XAFS study on structure and cation valence state of layered ruthenium oxide electrodes, Li_2RuO_3 and Li_2MnO_4 , upon electrochemical cycling. *Solid State Ionics* **2016**, 285, 66-74.
 59. Yoon, W.-S.; Kim, K.-B.; Kim, M.-G.; Lee, M.-K.; Shin, H.-J.; Lee, J.-M.; Lee, J.-S.; Yo, C.-H., Oxygen contribution on Li-ion intercalation–deintercalation in LiCoO_2 investigated by O K-edge and Co L-edge X-ray absorption spectroscopy. *The Journal of Physical Chemistry B* **2002**, 106 (10), 2526-2532.
 60. Montoro, L.; Abbate, M.; Rosolen, J. M., Changes in the electronic structure of chemically deintercalated LiCoO_2 . *Electrochemical and Solid-State Letters* **2000**, 3 (9), 410-412.
 61. Nam, K. W.; Bak, S. M.; Hu, E.; Yu, X.; Zhou, Y.; Wang, X.; Wu, L.; Zhu, Y.; Chung, K. Y.; Yang, X. Q., Combining in situ synchrotron X-ray diffraction and absorption techniques with transmission electron microscopy to study the origin of thermal instability in overcharged cathode materials for lithium-ion batteries. *Advanced Functional Materials* **2013**, 23 (8), 1047-1063.
 62. Hayyan, M.; Hashim, M. A.; AlNashef, I. M., Superoxide ion: generation and chemical implications. *Chemical reviews* **2016**, 116 (5), 3029-3085.
 63. Koput, J., An ab initio study on the equilibrium structure and torsional potential energy function of hydrogen peroxide. *Chemical physics letters* **1995**, 236 (4-5), 516-520.
 64. Hong, W. T.; Stoerzinger, K. A.; Moritz, B.; Devereaux, T. P.; Yang, W.; Shao-Horn, Y., Probing LaMO_3 Metal and Oxygen Partial Density of States Using X-ray Emission, Absorption, and Photoelectron Spectroscopy. *The Journal of Physical Chemistry C* **2015**, 119 (4), 2063-2072.
 65. Dronskowski, R.; Blöchl, P. E., Crystal orbital Hamilton populations (COHP): energy-resolved visualization of chemical bonding in solids based on density-functional calculations. *The Journal of Physical Chemistry* **1993**, 97 (33), 8617-8624.

66. Deringer, V. L.; Tchougréeff, A. L.; Dronskowski, R., Crystal orbital Hamilton population (COHP) analysis as projected from plane-wave basis sets. *The journal of physical chemistry A* **2011**, *115* (21), 5461-5466.
67. Oishi, M.; Yamanaka, K.; Watanabe, I.; Shimoda, K.; Matsunaga, T.; Arai, H.; Ukyo, Y.; Uchimoto, Y.; Ogumi, Z.; Ohta, T., Direct observation of reversible oxygen anion redox reaction in Li-rich manganese oxide, Li_2MnO_3 , studied by soft X-ray absorption spectroscopy. *Journal of Materials Chemistry A* **2016**, *4* (23), 9293-9302.
68. Risch, M.; Stoerzinger, K. A.; Han, B.; Regier, T. Z.; Peak, D.; Sayed, S. Y.; Wei, C.; Xu, Z.; Shao-Horn, Y., Redox processes of manganese oxide in catalyzing oxygen evolution and reduction: An in situ soft X-ray absorption spectroscopy study. *The Journal of Physical Chemistry C* **2017**, *121* (33), 17682-17692.
69. Renfrew, S. E.; McCloskey, B. D., Residual lithium carbonate predominantly accounts for first cycle CO_2 and CO outgassing of Li-stoichiometric and Li-rich layered transition-metal oxides. *Journal of the American Chemical Society* **2017**, *139* (49), 17853-17860.
70. Mahne, N.; Renfrew, S. E.; McCloskey, B. D.; Freunberger, S. A., Electrochemical oxidation of lithium carbonate generates singlet oxygen. *Angewandte Chemie International Edition* **2018**, *57* (19), 5529-5533.
71. Wandt, J.; Freiberg, A. T.; Ogrodnik, A.; Gasteiger, H. A., Singlet oxygen evolution from layered transition metal oxide cathode materials and its implications for lithium-ion batteries. *Materials Today* **2018**, *21* (8), 825-833.
72. Li, L.; Castro, F. C.; Park, J. S.; Li, H.; Lee, E.; Boyko, T.; Freeland, J. W.; Yao, Z.; Fister, T. T.; Vinson, J., Probing Electrochemically-Induced Structural Evolution and Oxygen Redox Reactions in Layered Lithium Iridate. *Chemistry of Materials* **2019**, *31* (12), 4341-4352.
73. Horsley, J., Relationship between the area of L 2, 3 x-ray absorption edge resonances and the d orbital occupancy in compounds of platinum and iridium. *The Journal of Chemical Physics* **1982**, *76* (3), 1451-1458.
74. Yabuuchi, N.; Nakayama, M.; Takeuchi, M.; Komaba, S.; Hashimoto, Y.; Mukai, T.; Shiiba, H.; Sato, K.; Kobayashi, Y.; Nakao, A., Origin of stabilization and destabilization in solid-state redox reaction of oxide ions for lithium-ion batteries. *Nature communications* **2016**, *7*, 13814.
75. Yabuuchi, N.; Takeuchi, M.; Nakayama, M.; Shiiba, H.; Ogawa, M.; Nakayama, K.; Ohta, T.; Endo, D.; Ozaki, T.; Inamasu, T., High-capacity electrode materials for rechargeable lithium batteries: Li_3NbO_4 -based system with cation-disordered rocksalt structure. *Proceedings of the National Academy of Sciences* **2015**, *112* (25), 7650-7655.
76. James, A.; Goodenough, J., Structure and bonding in lithium ruthenate, Li_2RuO_3 . *Journal of Solid State Chemistry* **1988**, *74* (2), 287-294.
77. McCloskey, B. D.; Bethune, D. S.; Shelby, R. M.; Girishkumar, G.; Luntz, A. C., Solvents' critical role in nonaqueous lithium-oxygen battery electrochemistry. *The Journal of Physical Chemistry Letters* **2011**, *2* (10), 1161-1166.
78. Harding, J. R. Investigation of oxidation in nonaqueous lithium-air batteries. Massachusetts Institute of Technology, 2015.
79. Nowak, S. H. A., R.; Schwartz C.P.; Gallo A.; Abraham, B.; Garcia-Esparaza, A.T.; Biasin, E.; Prado, A.; Maciel, A.; Zhang, D.; D. Day; Christensen, S.; Alonso-Mori, R.; Kroll, T.; Nordlund, D.; Weng, T.-C.; Sokaras, D., A versatile Johansson-type tender X-ray emission spectrometer. *under review* **2019**.
80. Ravel, B.; Newville, M., ATHENA, ARTEMIS, HEPHAESTUS: data analysis for X-ray absorption spectroscopy using IFEFFIT. *Journal of synchrotron radiation* **2005**, *12* (4), 537-541.
81. Perdew, J. P.; Burke, K.; Ernzerhof, M., Generalized gradient approximation made simple. *Physical review letters* **1996**, *77* (18), 3865.
82. Kresse, G.; Furthmüller, J., Efficiency of ab-initio total energy calculations for metals and semiconductors using a plane-wave basis set. *Computational materials science* **1996**, *6* (1), 15-50.
83. Kresse, G.; Furthmüller, J., Efficient iterative schemes for ab initio total-energy calculations using a plane-wave basis set. *Physical review B* **1996**, *54* (16), 11169.

84. Kresse, G.; Hafner, J., Ab initio molecular dynamics for liquid metals. *Physical Review B* **1993**, *47* (1), 558.
85. Dudarev, S.; Botton, G.; Savrasov, S.; Humphreys, C.; Sutton, A., Electron-energy-loss spectra and the structural stability of nickel oxide: An LSDA+ U study. *Physical Review B* **1998**, *57* (3), 1505.
86. Wolverton, C.; Zunger, A., First-principles prediction of vacancy order-disorder and intercalation battery voltages in Li x CoO 2. *Physical review letters* **1998**, *81* (3), 606.
87. Giannozzi, P.; Baroni, S.; Bonini, N.; Calandra, M.; Car, R.; Cavazzoni, C.; Ceresoli, D.; Chiarotti, G. L.; Cococcioni, M.; Dabo, I., QUANTUM ESPRESSO: a modular and open-source software project for quantum simulations of materials. *Journal of physics: Condensed matter* **2009**, *21* (39), 395502.
88. Gonze, X.; Beuken, J.-M.; Caracas, R.; Detraux, F.; Fuchs, M.; Rignanese, G.-M.; Sindic, L.; Verstraete, M.; Zerah, G.; Jollet, F., First-principles computation of material properties: the ABINIT software project. *Computational Materials Science* **2002**, *25* (3), 478-492.

Supplementary Information

Revealing Electronic Signature of Lattice Oxygen Redox in Lithium Ruthenates and Implications for High-Energy Li-ion Battery Material Designs

Yang Yu^{a,*}, Pinar Karayaylali^b, Stanisław H. Nowak^c, Livia Giordano^{b,d}, Magali Gauthier^{d, †}, Wesley Hong^a, Ronghui Kou^e, Qinghao Li^f, John Vinson^g, Thomas Kroll^e, Dimosthenis Sokaras^{c,*}, Cheng-Jun Sun^e, Nenian Charles^d, Filippo Maglia^h, Roland Jung^h, Yang Shao-Horn^{a,b,d,*}

^a *Department of Materials Science and Engineering, MIT, Cambridge, MA 02139, USA*

^b *Department of Mechanical Engineering, MIT, Cambridge, MA 02139, USA*

^c *SLAC National Accelerator Laboratory, Menlo Park, CA, 94025, USA*

^d *Research Laboratory of Electronics, MIT, Cambridge, MA 02139, USA*

^e *Advanced Photon Source, Argonne National Laboratory, Argonne, IL 60439, USA*

^f *Advanced Light Source, Lawrence Berkeley National Laboratory, CA 94720, USA*

^g *National Institute of Standards and Technology, Gaithersburg, Maryland 20899, USA*

^h *BMW Group, Petuelring 130, 80788 Munich, Germany*

[†] *Current address: M.G.: LEEL, NIMBE, CEA, CNRS, Université Paris-Saclay, CEA Saclay 91191 Gif-sur-Yvette, France.*

Corresponding Authors

* Yang Yu (yuy@mit.edu)

* Dimosthenis Sokaras (dsokaras@slac.stanford.edu)

* Yang Shao-Horn (shaohorn@mit.edu)

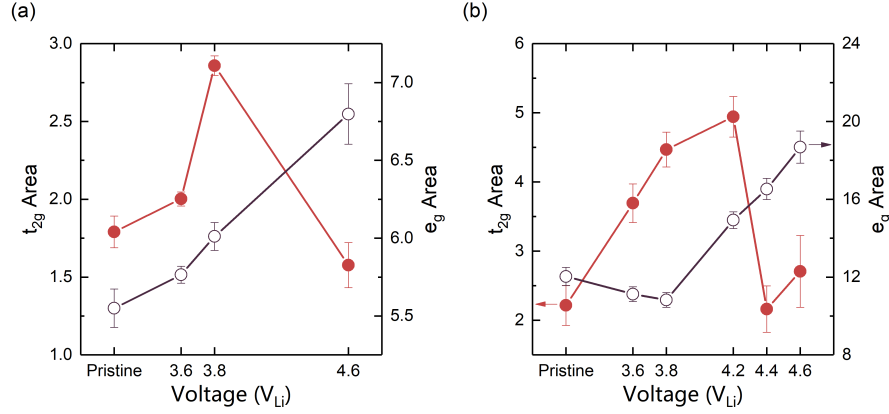


Figure S1: Integrated area underneath t_{2g} (feature a in Figure 1, closed circle) and e_g (feature b in Figure 1, open circle) peaks for (a) O K-edge and (b) Ru L₃-edge XAS, where the fitted peaks and raw spectra are shown in Figure S2 and S3.

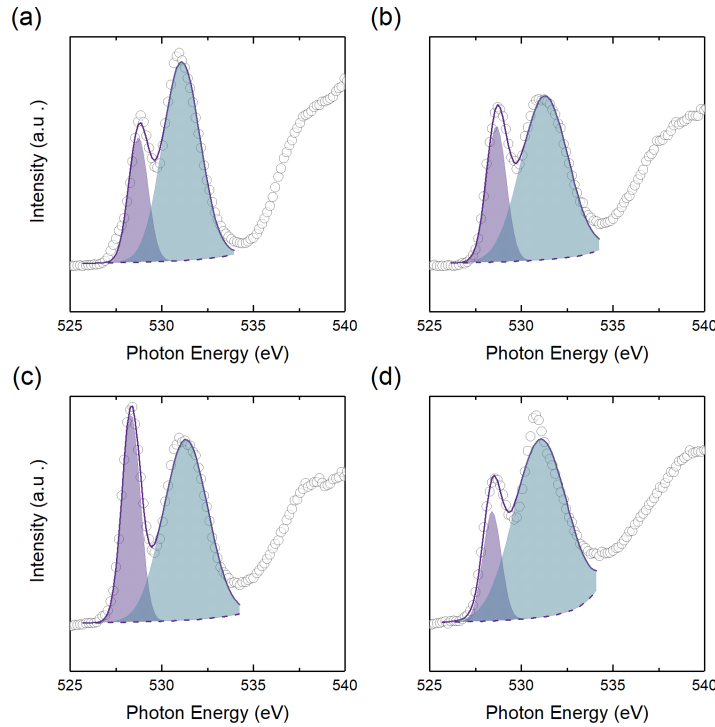


Figure S2: Fitted spectra (shaded area and line) and raw spectra (open circle) of O K-edge XAS of $Li_{2-x}RuO_3$ (a) pristine, and charged to (b) 3.6 V_{Li} (c) 3.8 V_{Li} and (d) 4.6 V_{Li} . Note that for consistency, we only fit two peaks of Gaussian shape with an arctangent background (dashed line) for all the spectra. Due to the broadening of the e_g peak, the fitting results at higher voltages is less ideal compared to fitting for the other voltages. The error of the fitting is estimated

through fitting residuals and X^2 distribution ($X^2 = \sum_{i=1}^n \frac{(y_i - f(x_i))^2}{\sigma_i^2}$). To reduce the variability of the fit, the arctangent background is constrained to have a height and width of 1 eV, with center around 536 eV for all the spectra obtained by pre-fitting with the background up to 560 eV and then fixed when fitting the pre-peak.

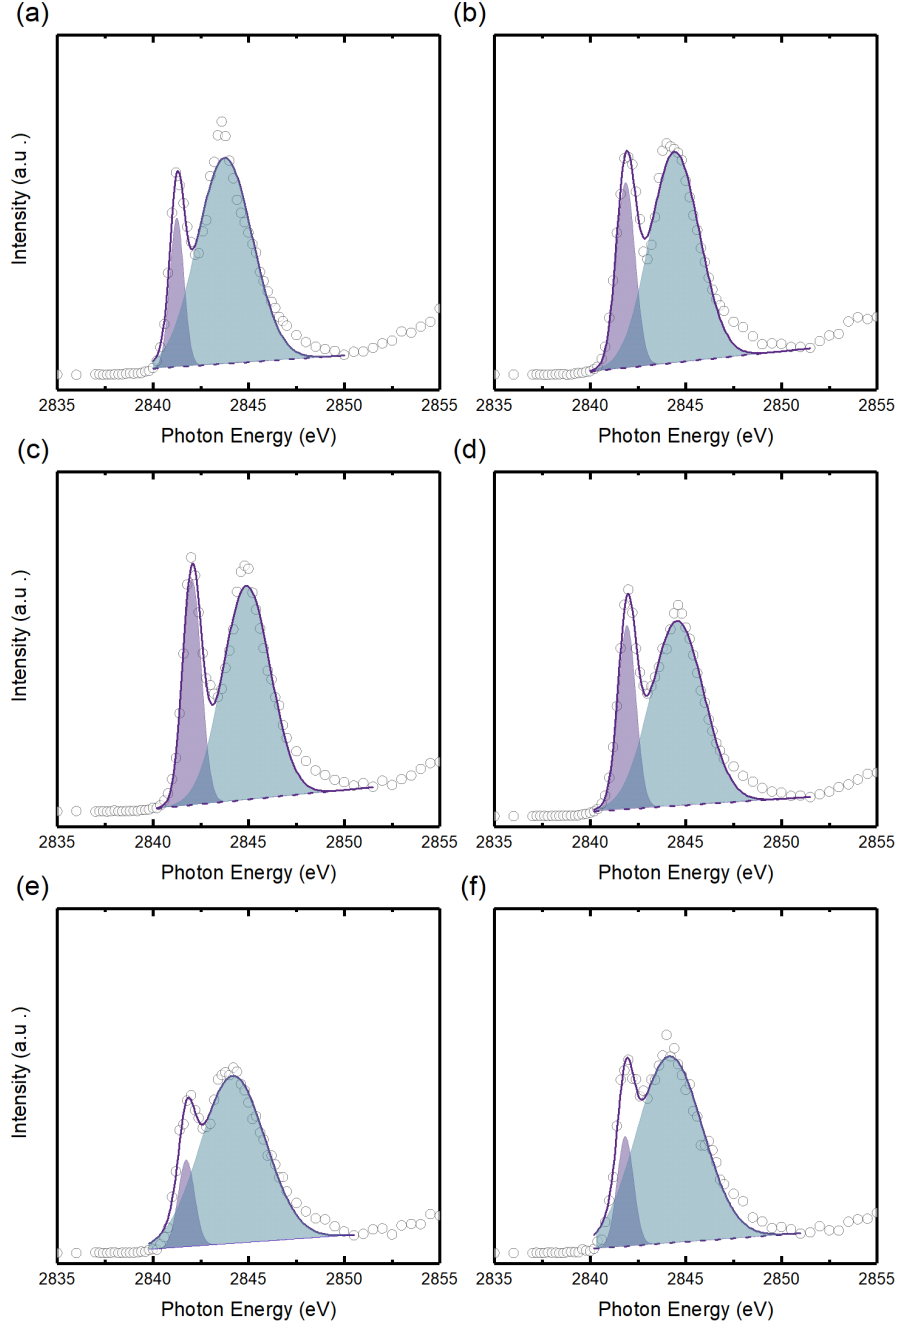


Figure S3: Fitted spectra (shaded area and line) and raw spectra (open circle) of Ru L_3 -edge XAS of $\text{Li}_{2-x}\text{RuO}_3$ (a) pristine and charged to (b) 3.6 V_{Li} (c) 3.8 V_{Li} , (d) 4.2 V_{Li} , (e) 4.4 V_{Li} and (f) 4.6 V_{Li} . Note that for consistency and the absence of obvious background, we only fit two peaks of Gaussian shape with a linear background (dashed line) for all the spectra, and due to the broadening of the e_g peak, the fitting results at higher voltages are less ideal compared to fitting for the other voltages, and the error of the fitting is estimated through fitting residuals and X^2

$$\text{distribution } (X^2 = \sum_{i=1}^n (\frac{(y_i - f(x_i))^2}{\sigma_i^2}))$$

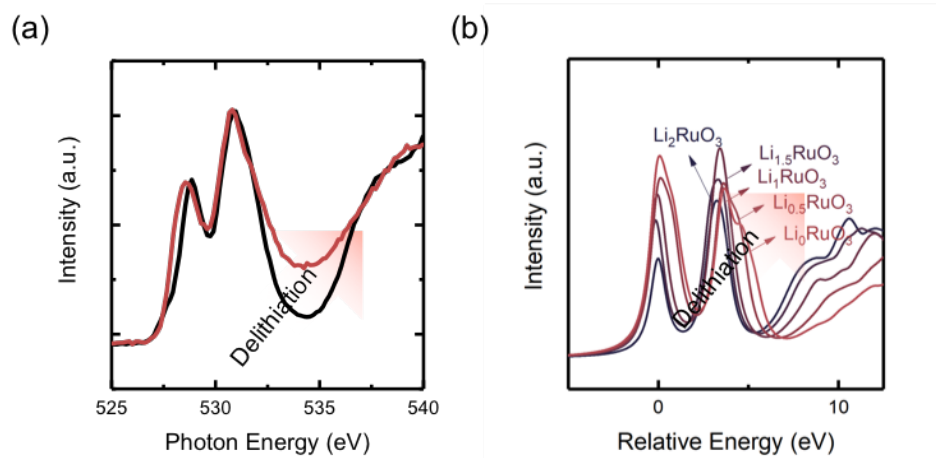


Figure S4: Experimental O K-edge XAS of pristine and charged $\text{Li}_{2-x}\text{RuO}_3$ to 4.6 V_{Li} (left) compared with computed O K-edge spectra of $\text{Li}_{2-x}\text{RuO}_3$ (right), where we observed a shoulder peak growing at higher photon energy for both the experimental and computed spectra. However, we should note that the relative intensity of the t_{2g} and e_g peaks in the computed O K-edge spectra is much higher than the experimental observed peak ratio for fully delithiated $\text{Li}_{2-x}\text{RuO}_3$.

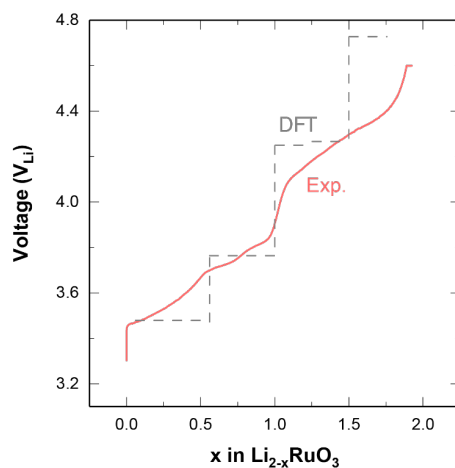


Figure S5: Calculated charge profile (by computing the energetics of the following delithiation reaction $\text{Li}_{2-x}\text{RuO}_3 = \text{Li}_{2-x-y}\text{RuO}_3 + y\text{Li}$) (grey dashed line) of delithiated $\text{Li}_{2-x}\text{RuO}_3$ structures compared to experimental charging profile (red solid line), where the DFT calculated profile matched with the experimental profile and the most stable structure calculated from each step is used for spectra simulation in Figure 2 and Figure S4.

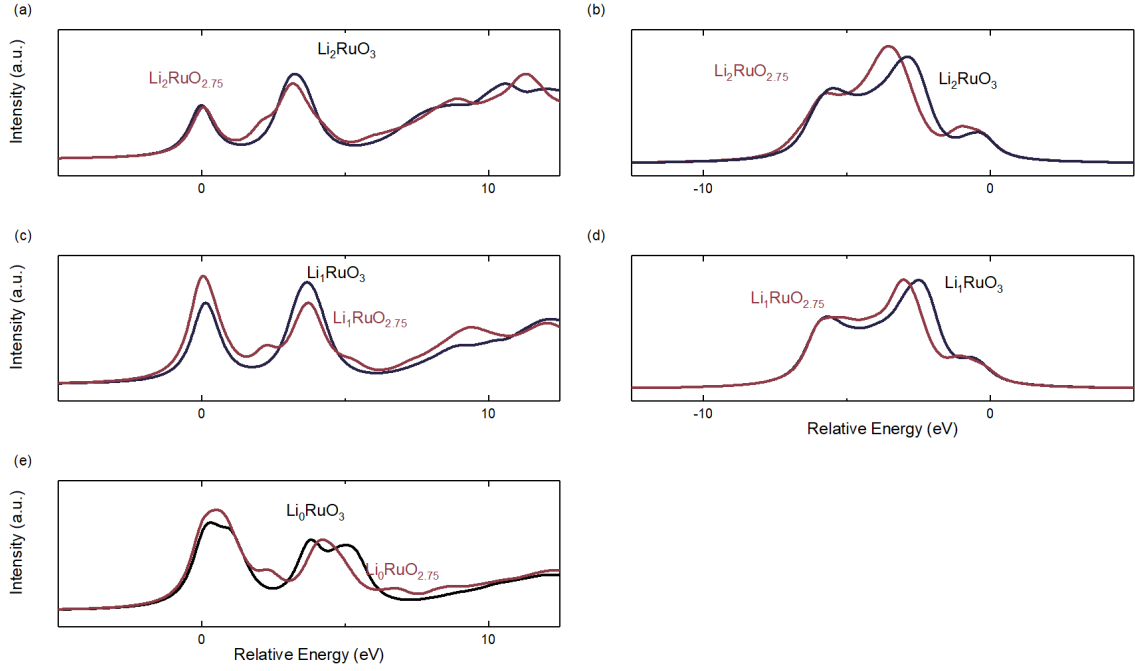


Figure S6: Simulated O K-edge XAS spectra of $\text{Li}_{2-x}\text{RuO}_3$ (black) and defective $\text{Li}_{2-x}\text{RuO}_{3-\delta}$ (red) structures ($\delta = 0.25$) for (a) $x = 0$ (c) $x = 1$, and (e) $x = 2$, and simulated O K-edge XES spectra of defective $\text{Li}_{2-x}\text{RuO}_{3-\delta}$ structures ($\delta = 0.25$) for (b) $x = 0$ and (d) $x = 1$. Similarly as in Ru L_3 -edge (Figure S7), we can note that as we introduce oxygen vacancies in the structure, in the O K-edge XAS, the e_g peak intensity decreased, while creating additional feature between the t_{2g} and e_g features at all lithium contents. In the simulated O K-edge XES, as we introduce oxygen vacancies, we only observed the shift of the non-bonding peak towards lower photon energy without creation of additional peak. Therefore, introduction of oxygen vacancies cannot explain the broadening we observed in the experimental XES data.

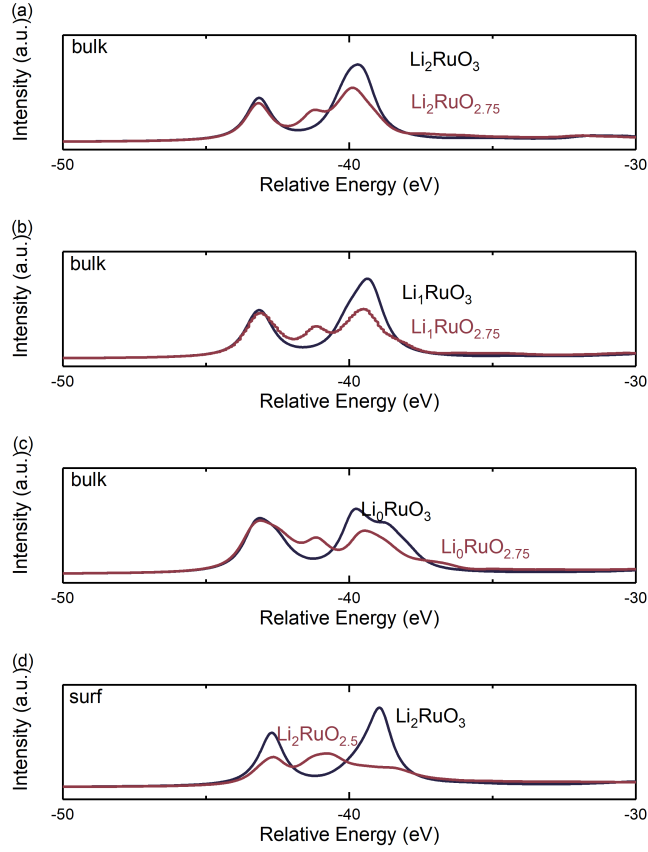


Figure S7: Simulated Ru L_3 -edge XAS spectra of $\text{Li}_{2-x}\text{RuO}_3$ (black) and defective $\text{Li}_{2-x}\text{RuO}_{3-\delta}$ structures ($\delta = 0.25$) for (a) $x = 0$ (b) $x = 1$, and (c) $x = 2$, and (d) the simulated Ru L_3 -edge XAS spectra of surface Ru atom with O vacancy concentrated on the surface is also included. We note that as we introduce oxygen vacancies in the structure, the e_g peak intensity decreased, while creating additional feature between the t_{2g} and e_g features at all lithium contents.

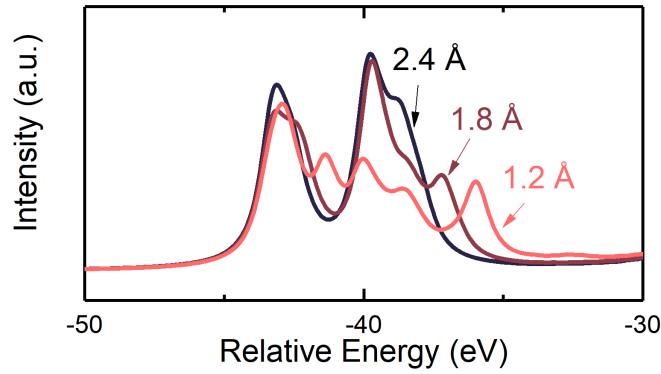


Figure S8: Simulated Ru L -edge XAS spectra of Li_0RuO_3 structure with oxygen-oxygen bond length of around 2.4 Å and hypothetical structures by forcing oxygen and oxygen bond length to 1.8 Å and 1.2 Å. We can note that as we introduce shorter oxygen-oxygen bond, the additional

shoulder we observed at high photon energy representing O-O σ^* feature shifted to higher energy, which indicates that as two oxygen atoms are forced closer together the (O-O) σ^* feature is destabilized. Moreover, by modulating the O-O bond length from 1.8 Å to 1.2 Å, the e_g peak reduces in area compared to t_{2g} feature, which is not observed at high potentials in the experimental spectra in Figure 1(b) and 2(a), therefore in $\text{Li}_{2-x}\text{RuO}_3$ system, the creation of superoxo-species (with O-O bond distance less than 1.5 Å) is not likely or not stable to be observed.

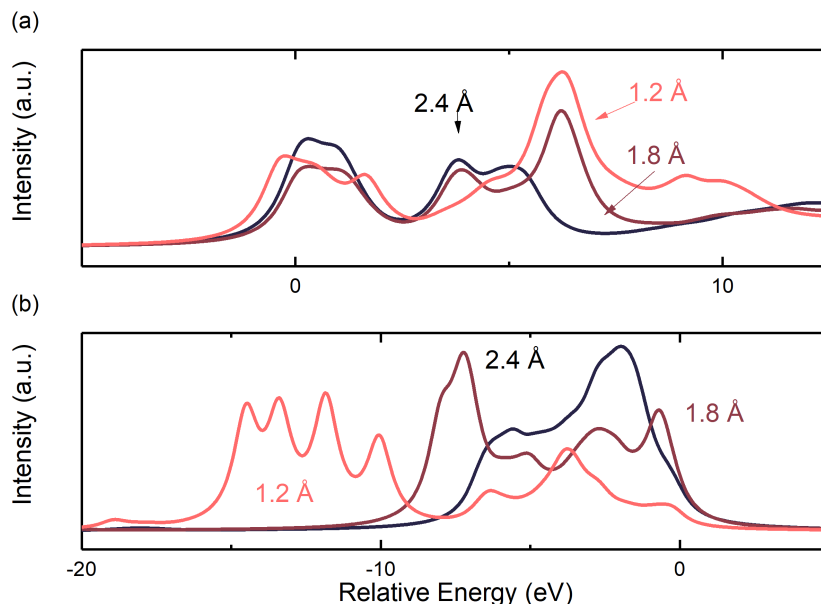


Figure S9: Simulated O K-edge (a) XAS and (b) XES spectra of Li_0RuO_3 structure with oxygen-oxygen bond length of around 2.4 Å and hypothetical structures obtained by forcing the oxygen and oxygen bond length to 1.8 Å and 1.2 Å. For XAS, we note that as we shorten the oxygen-oxygen bond, the additional shoulder we observed at high photon energy representing O-O σ^* feature shifts to higher energy and increases in intensity (see also the Ru L-edge simulation as shown in Figure S8.) This indicates that as the two oxygens are forced to be closer together, the σ^* feature is destabilized. Moreover, by modulating the O-O bond length from 1.8 Å to 1.2 Å, the e_g peak drastically reduces in area compared to t_{2g} feature, which is not observed at high potentials in the experimental spectra in Figure 1(a) and 2(a). Compared to the XAS spectra, the computed XES spectra is more sensitive to the fluctuation of oxygen bond distance. Upon decreasing the bond distance, there are more features observed in the XES spectra, potentially coming from the clear fingerprint of σ, π, π^* feature of the O-O bond due to stronger oxygen coupling. This splitting is not observed in the experimental spectra either. Therefore in $\text{Li}_{2-x}\text{RuO}_3$ system, the creation of superoxo- and peroxo-species (with O-O bond distance less than 1.5 Å) is not likely or not stable enough to be observed.

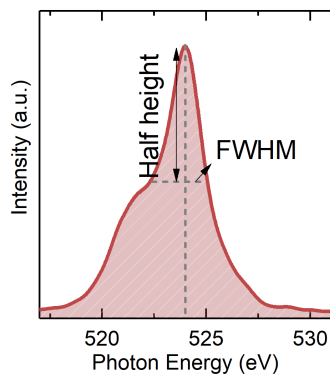


Figure S10 Schematics of an example FWHM extraction of O K-edge XES spectra. The FWHM was estimated through the width of the center peak at half height since the center non-bonding peak is much taller than the shoulder peaks, therefore we assume the shoulder peaks evolution will not have significant effect on the full width half maximum of the center non-bonding peak.

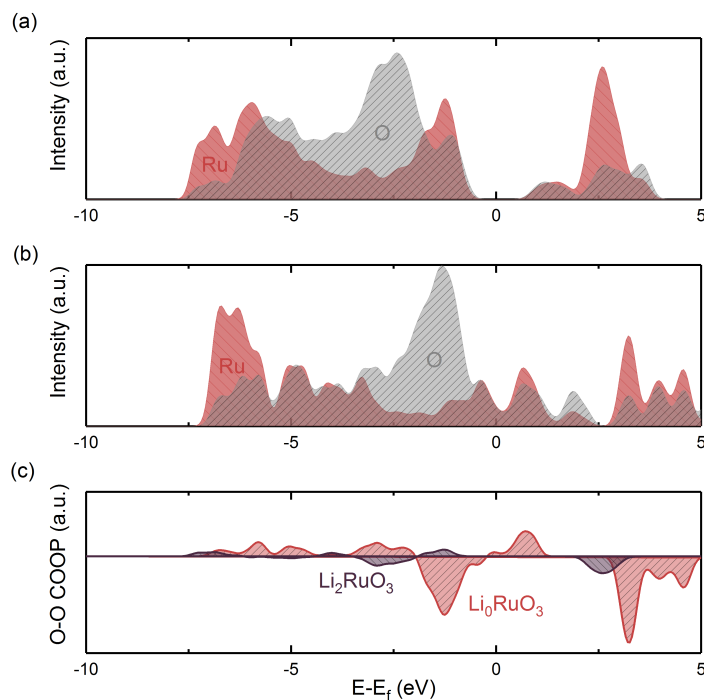


Figure S11: Calculated ground-state pDOS of (a) Li_2RuO_3 and (b) Li_0RuO_3 used for the calculation of crystal orbital overlap population (COOP) in (c), where as we delithiated the Li_2RuO_3 , there is a significant increase of O-O coupling, which can be observed in experimental Ru L_3 -edge and O K-edge XAS as well as O K-edge XES.

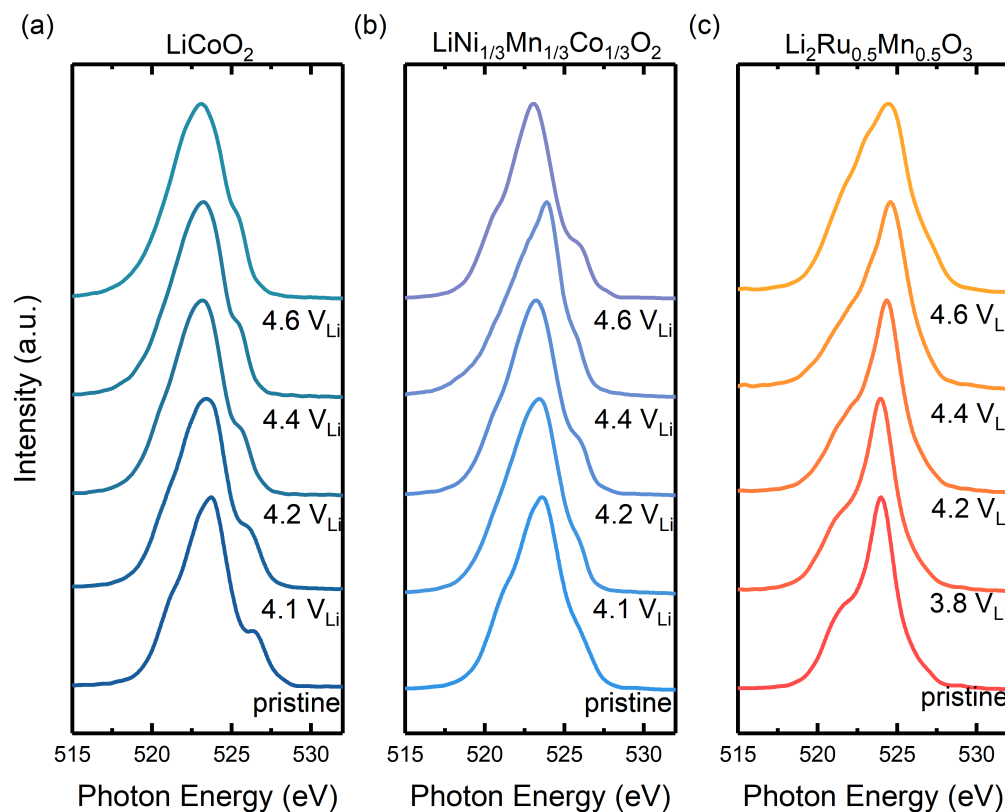


Figure S12 Experimental O K-edge XES of (a) pristine and charged $\text{Li}_{1-x}\text{CoO}_2$ to 4.1 V_{Li} , 4.2 V_{Li} , 4.4 V_{Li} , and 4.6 V_{Li} , (b) pristine and charged $\text{Li}_{1-x}\text{Ni}_{1/3}\text{Mn}_{1/3}\text{Co}_{1/3}\text{O}_2$ to 4.1 V_{Li} , 4.2 V_{Li} , 4.4 V_{Li} , and 4.6 V_{Li} , and (c) pristine and charged $\text{Li}_{2-x}\text{Mn}_{0.5}\text{Ru}_{0.5}\text{O}_3$ to 3.8 V_{Li} , 4.2 V_{Li} , 4.4 V_{Li} , and 4.6 V_{Li} , where, upon delithiation, materials exhibiting anionic redox including $\text{Li}_{2-x}\text{Ru}_{0.5}\text{Mn}_{0.5}\text{O}_3$ and $\text{Li}_{2-x}\text{RuO}_3$ showed significant broadening of non-bonding peak, in contrast with $\text{Li}_{1-x}\text{CoO}_2$ and $\text{Li}_{1-x}\text{Ni}_{1/3}\text{Mn}_{1/3}\text{Co}_{1/3}\text{O}_2$ which relied primarily on cationic redox and did not show significant changes, as shown in Figure 3(e) and Figure S13.

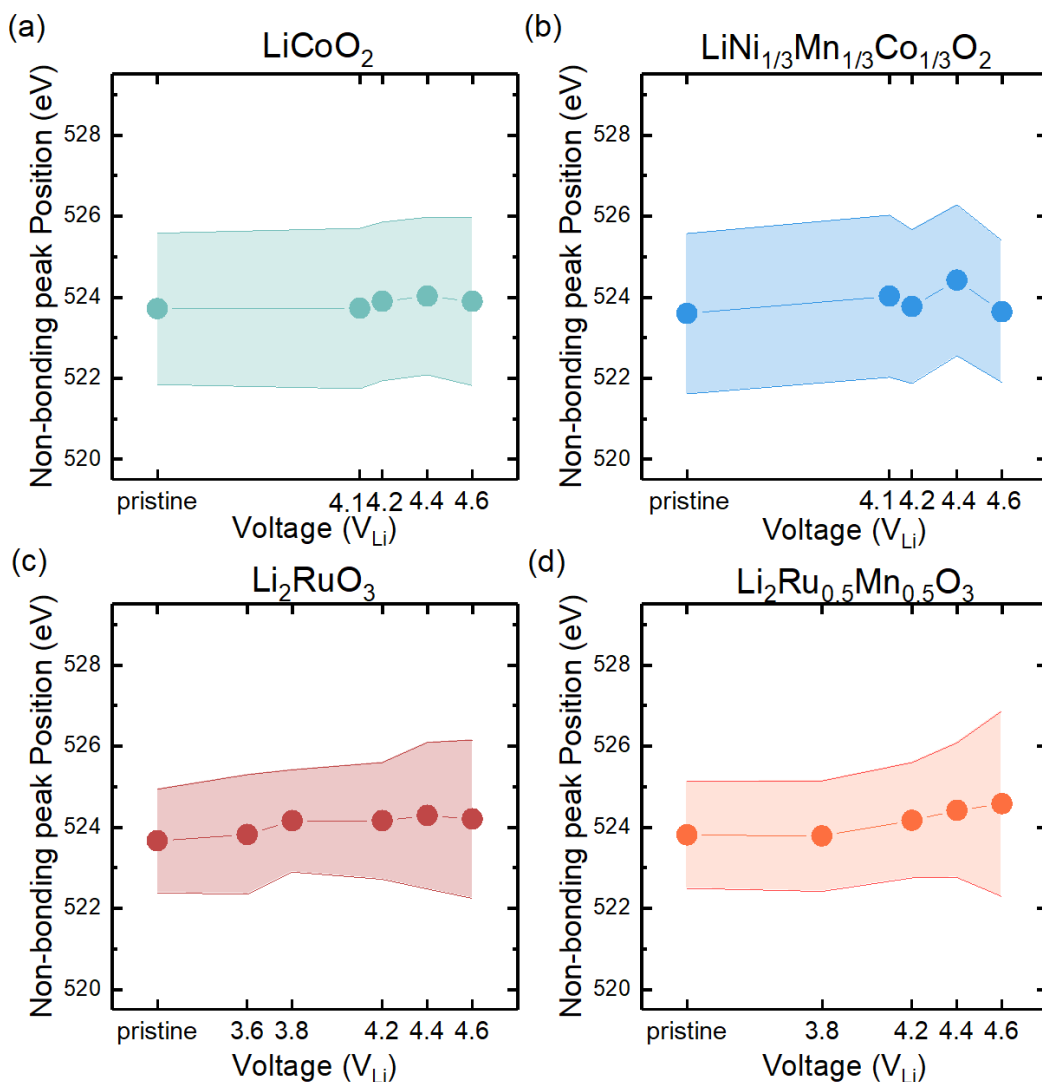


Figure S13: Non-bonding peak position (closed circle) and FWHM (colored band) of O K-edge XES of (a) pristine and charged Li_{1-x}CoO₂ to 4.1 V_{Li}, 4.2 V_{Li}, 4.4 V_{Li}, 4.6 V_{Li}, (b) pristine and charged Li_{1-x}Ni_{1/3}Mn_{1/3}Co_{1/3}O₂ to 4.1 V_{Li}, 4.2 V_{Li}, 4.4 V_{Li}, 4.6 V_{Li}, (c) pristine and charged Li_{2-x}RuO₃ to 3.6 V_{Li}, 3.8 V_{Li}, 4.2 V_{Li}, 4.4 V_{Li}, 4.6 V_{Li} and (d) pristine and charged Li_{2-x}Ru_{0.5}Mn_{0.5}O₃ to 3.8 V_{Li}, 4.2 V_{Li}, 4.4 V_{Li}, 4.6 V_{Li}, where, upon delithiation, materials exhibiting anionic redox including Li_{2-x}Ru_{0.5}Mn_{0.5}O₃ and Li_{2-x}RuO₃ showed significant broadening of non-bonding peak, in contrast with Li_{1-x}CoO₂ and Li_{1-x}Ni_{1/3}Mn_{1/3}Co_{1/3}O₂ which relied primarily on cationic redox and did not show significant changes, as shown in Figure 3(e). Here, the FWHM was extracted based on the width at the half height of the most predominant peak (non-bonding peak) as the other shoulder peaks are much smaller than non-bonding peak, thus we assume that the shoulder peaks evolution will not have significant effect on the FWHM of the center non-bonding peak, the FWHM extraction procedure is also shown schematically in Figure S10.

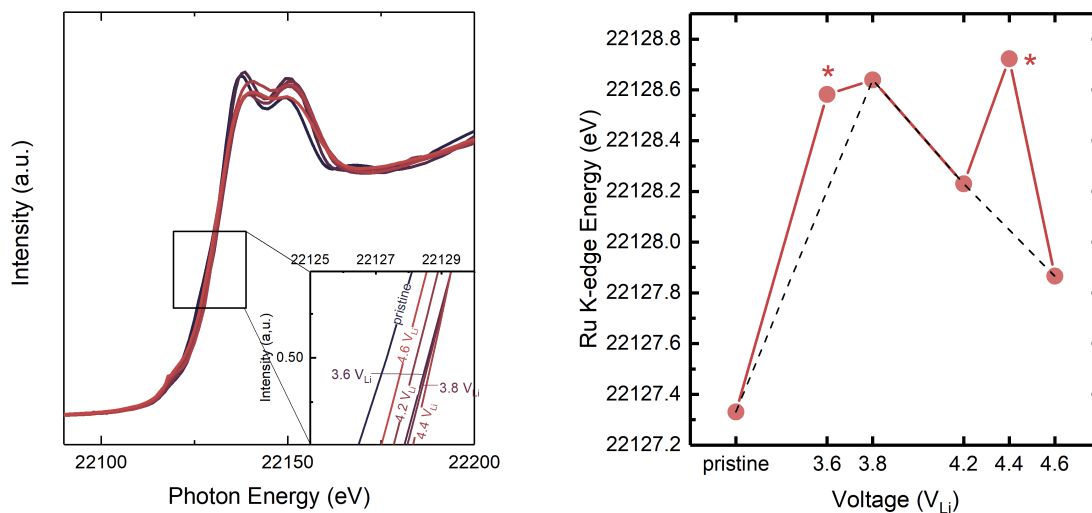


Figure S14: Ru K-edge XAS spectra (left) of pristine $Li_{2-x}RuO_3$, and charged to 3.6 V_{Li} , 3.8 V_{Li} , 4.2 V_{Li} , 4.4 V_{Li} and 4.6 V_{Li} , where the quantification of the K-edge energy is shown on the right. Here we can see that Ru K-edge shifted towards higher photon energy up to 3.8 V_{Li} by removing around 1 lithium per formula unit, representing $Ru^{4+/5+}$ oxidation, and upon further lithium de-intercalation the edge shifted toward lower photon energy as we charge up to 4.6 V_{Li} creating small shoulder in the pre-peak region around 22125 eV, signaling Ru reduction and Ru-O cage distortion. This observation matches with what we have observed in Figure 1 and Figure 2 in O K-edge, Ru L_3 -edge data and K-edge X-ray near edge absorption spectroscopy (XANES) data. All the data were aligned with a Ru metal foil reference channel. We should note that the data for $Li_{2-x}RuO_3$ charged to 3.6 V_{Li} and 4.4 V_{Li} (marked asterisk) were measured at a different beamtime, and had a slightly higher edge energy compared to the dashed line trend built by the other data even after reference channel alignment.

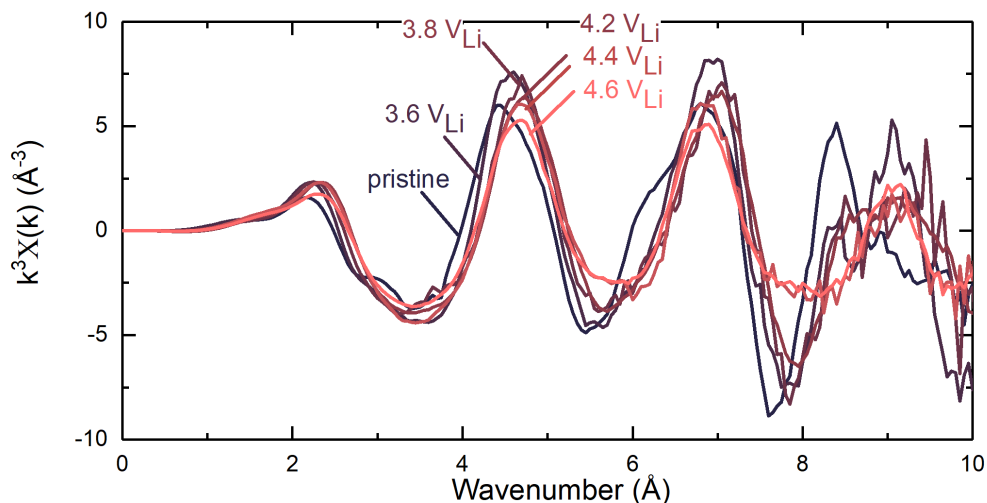


Figure S15: Ru K-edge EXAFS spectra in k-space of pristine $\text{Li}_{2-x}\text{RuO}_3$, and charged to 3.6 V_{Li} , 3.8 V_{Li} , 4.2 V_{Li} , 4.4 V_{Li} and 4.6 V_{Li} . The signal becomes rather noisy after 8 $\text{\AA}^{-1}$, and a confident fitting for the second and third coordination shell is challenging.

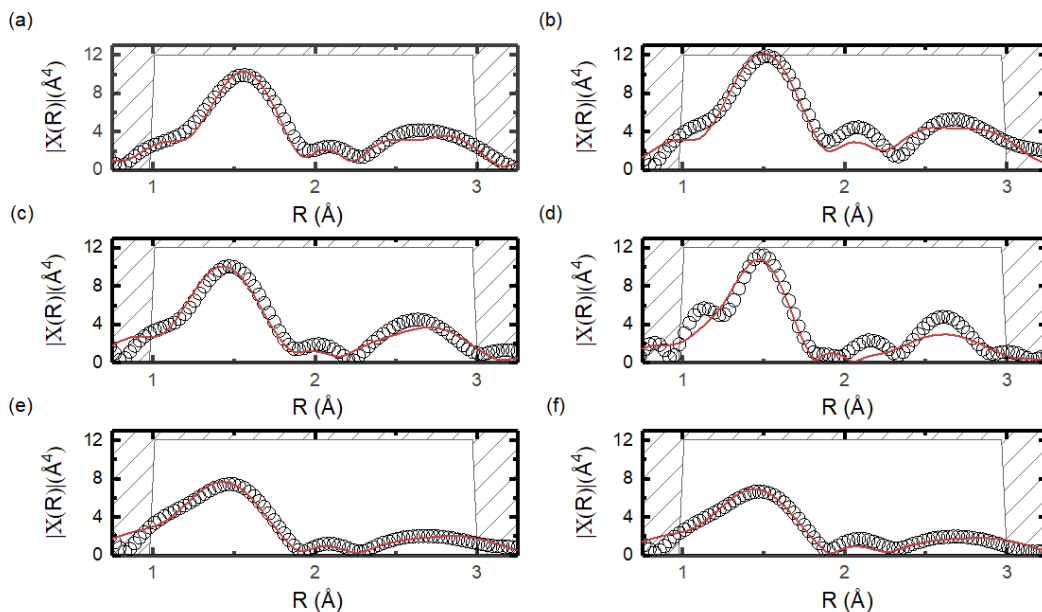


Figure S16: Fitted Ru K-edge EXAFS spectra in R-space of (a) pristine $\text{Li}_{2-x}\text{RuO}_3$, and charged to 3.6 V_{Li} (b) 3.8 V_{Li} (c) 4.2 V_{Li} (d) 4.4 V_{Li} (e) and (f) 4.6 V_{Li} , where we note that the fit for (d) 4.2 V_{Li} is very challenging.

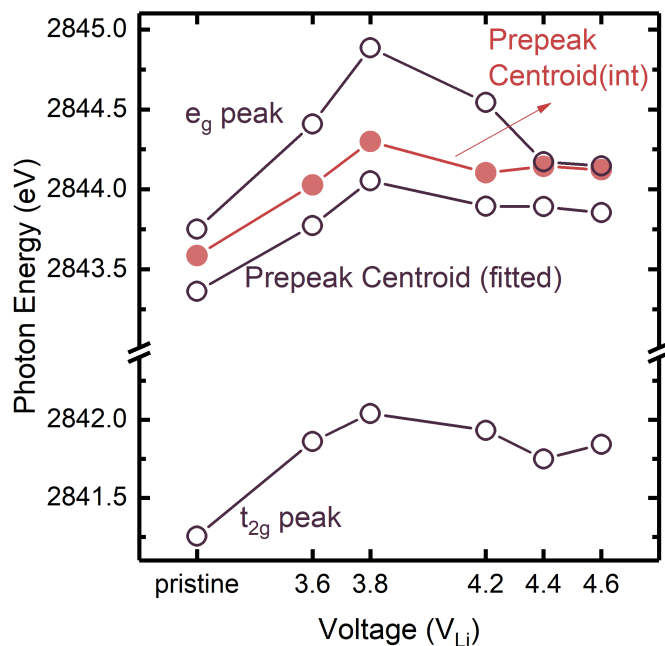


Figure S17: The t_{2g} and e_g peak (white-line) position, pre-peak centroid calculated through the fitting in Figure S3 as well as through simple integration of the area above the linear fitted background in Figure S3 of pristine $Li_{2-x}RuO_3$, and charged to 3.6 V_{Li} , 3.8 V_{Li} , 4.2 V_{Li} , 4.4 V_{Li} and 4.6 V_{Li} . Regardless of method used to process the Ru L_3 -edge spectra to obtain the oxidation state of Ru, it always shows a monotonic oxidation up to 3.8 V_{Li} and a slight reduction of Ru charging to 4.2 V_{Li} and above. We should also note that the pre-peak centroid positions calculated from fitting are always slightly lower than that computed from simple integration method because the fitting of e_g peaks do have more residuals compared to the fitting of t_{2g} peak, especially at high potentials, due to creation of high-photon energy features. To maintain consistency of fitting, we always fit only two peaks for the major two features observed in the raw spectra.

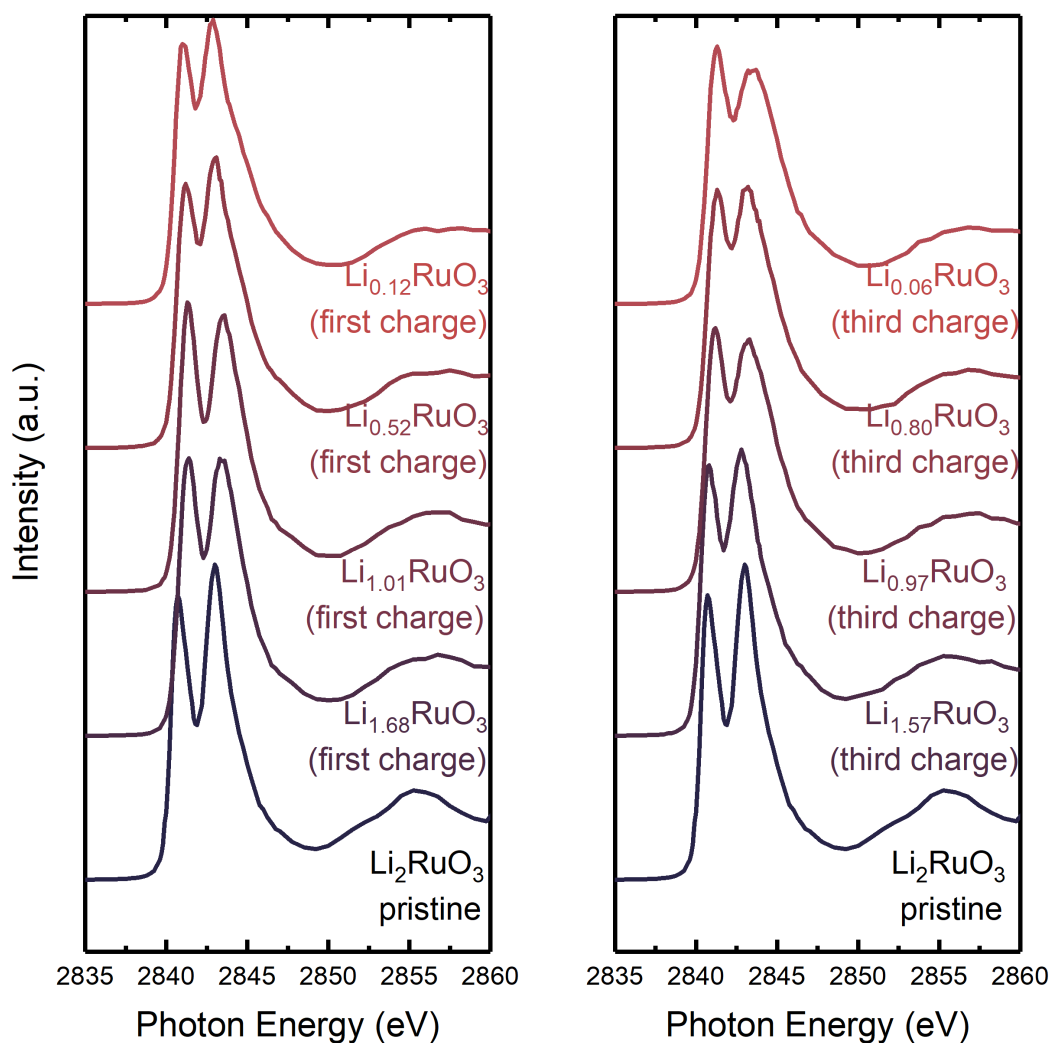


Figure S18: Ru L_3 -edge XAS of charged $\text{Li}_{2-x}\text{RuO}_3$ composite electrodes in the first and third cycle. Despite a similar state of charge in the first and third cycle, Ru started in a much more reduced state in the third cycle, shown also in Figure 5. We note that this composite electrode is much more concentrated than the pellet we prepared for the oxide-only pellets shown in Figure 1. Therefore, in fluorescence mode there is a large self-absorption effect in the composite samples. The change in the peak shape is overwhelmed by the self-absorption effect and cannot be compared directly to the oxide-only result.

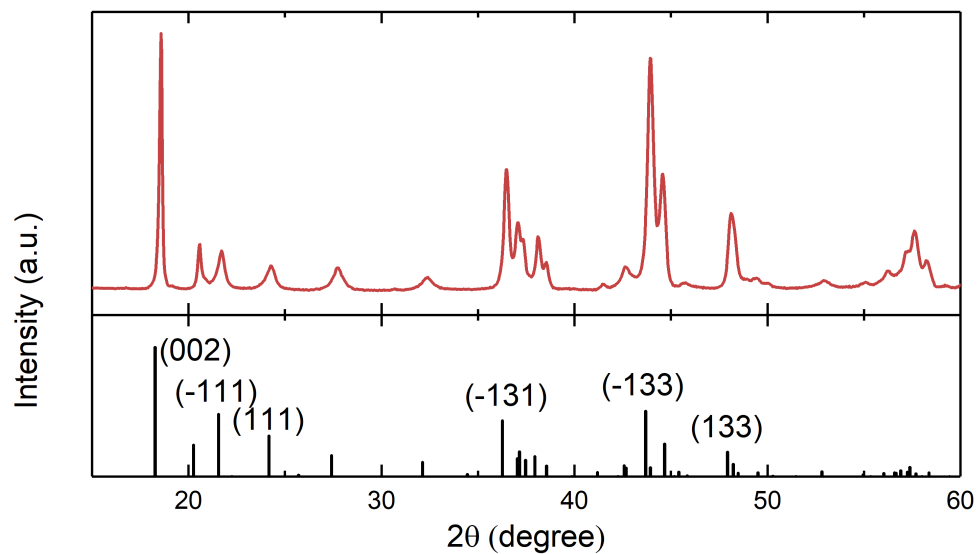


Figure S19: Powder X-ray diffraction (XRD) of the synthesized Li_2RuO_3 , where there are no impurity peaks observed. The reference XRD is shown in lower panel with respective Miller indices labeled for major peaks (Ref. 77)

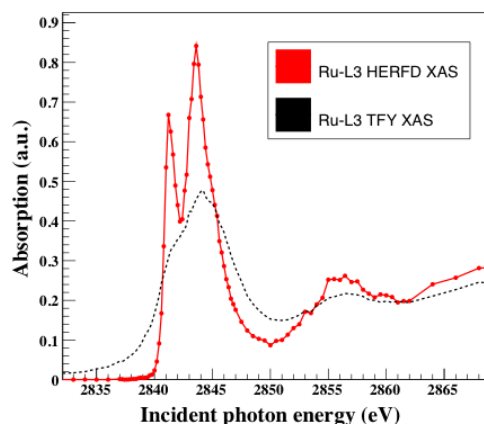


Figure S20: A comparison between conventional total fluorescence yield (TFY) and HERFD X-ray absorption of Ru L₃-edge as measured in pristine Li_2RuO_3 .

Table S1: Detailed fitting parameter for the EXAFS fitting of the first coordination shell where the coordination number, amplification reduction factor (S_0^2), bond length ($R_{\text{Ru-O}}$), energy shift (E_0) as well as the pseudo Debye-Waller factor $\sigma_{\text{Ru-O}}^2$, and their associated standard deviation (std) obtained from fitting are reported. The R window we have included 1 to 3 Å and we have also included the second coordination shell (Ru-Ru) in the fitting.

Voltage	N	S_0^2	std (S_0^2)	$R_{\text{Ru-O}}$	std($R_{\text{Ru-O}}$)	E_0	Std(E_0)	$\sigma_{\text{Ru-O}}^2$	Std($\sigma_{\text{Ru-O}}^2$)
Pristine	6	0.831	0.173	2.028	0.021	0.816	3.041	0.0035	0.0028
3.6 V_{Li}	6	0.951	0.219	1.980	0.023	-1.753	3.481	0.0030	0.0030
3.8 V_{Li}	6	0.877	0.214	1.941	0.021	-5.884	3.697	0.0039	0.0029
4.2 V_{Li}	6	0.850	0.102	1.941	0.011	-4.516	1.738	0.0044	0.0015
4.4 V_{Li}	6	1.125	0.122	1.958	0.011	-3.512	1.552	0.0093	0.0016
4.6 V_{Li}	6	0.910	0.112	1.964	0.013	-3.649	1.828	0.0080	0.0018

Table S2: Detailed fitting parameter for the EXAFS fitting of the first coordination shell where the coordination number, amplification reduction factor (S_0^2), bond length ($R_{\text{Ru-O}}$), energy shift (E_0) as well as the pseudo Debye-Waller factor $\sigma_{\text{Ru-O}}^2$, and their associated standard deviation (std) obtained from fitting are reported. The R window we have included 1 to 2.3 Å and we did not include the second coordination shell (Ru-Ru) in the fitting. We should note that the trend we observed for the Debye-Waller factor and the Ru-O bond length still holds even if we only include the first coordination shell.

Voltage	N	S_0^2	std (S_0^2)	$R_{\text{Ru-O}}$	std($R_{\text{Ru-O}}$)	E_0	Std(E_0)	$\sigma_{\text{Ru-O}}^2$	Std($\sigma_{\text{Ru-O}}^2$)
Pristine	6	0.838	0.107	2.028	0.013	0.394	1.789	0.0035	0.0016
3.6 V_{Li}	6	0.923	0.144	1.981	0.015	-1.579	2.209	0.0026	0.0020
3.8 V_{Li}	6	0.761	0.095	1.952	0.012	-3.895	1.831	0.0028	0.0015
4.2 V_{Li}	6	0.809	0.080	1.948	0.010	-3.363	1.510	0.0041	0.0013
4.4 V_{Li}	6	0.971	0.152	1.956	0.016	-3.222	2.158	0.0077	0.0024
4.6 V_{Li}	6	0.805	0.108	1.964	0.014	-3.158	1.883	0.0068	0.0020